

ReMA's ISRI SPECIFICATIONS



GUIDE FOR:

- Nonferrous
- Ferrous
- Inbound Curbside Recyclables
- Glass Cullet
- Paper Stock
- Plastic
- Tires
- Electronics



Recycled Materials
Association
Sustainable. Resilient. Essential.

JULY 2026

1250 H Street, NW Suite 400
Washington, DC 20005
T: 202.662.8500
F: 202.624.9256
recycledmaterials.org

Copyright © 2026 Institute of Scrap Recycling Industries, Inc.,
dba Recycled Materials Association. All rights reserved.

Contents

Rules Governing the Procedures for the Addition, Amendment, or Withdrawal of Specifications	1
Revisions Included in this Version	2
Guidelines for Nonferrous: NF-2025	3
Red Metals	4
Aluminum	7
Zinc	12
Magnesium	13
Lead	13
Nickel/Stainless/Hi Temp	14
Mixed Metals	16
Other	17
Guidelines for Ferrous: FS-2023	20
Electric Furnace Casting and Foundry Grades	22
Specially Processed Grades	23
Cast Iron Grades	23
Special Boring Grades	24
Ferrous – Special (Tire Wire)	24
Railroad Ferrous	25
Guidelines for Glass Cullet: GC-2023	28
MRF Glass	30
Guidelines for Paper Stock: PS-2026	32
Glossary of Paper Stock Terms	39
Guidelines for Plastic: P-2025	40
Guidelines for Electronics: ES-2023	52
Guidelines for Tire TS-2023	55
Guidelines for Metals Transactions	57
Inbound Residential Single Stream	62
Inbound Residential Dual Stream	64
ReMA Arbitration Service	66

Preface

ReMA's ISRI Specifications are intended to assist members in the buying and selling of their materials and products.

These specifications provide a common language for describing the quality and composition of recycled metals, paper, plastics, glass, and electronics. They are internationally recognized and used by buyers and sellers worldwide.

Parties to a transaction may specify particular variations or additions to these specifications suited to their needs. Any deviation from these specifications, however, should be mutually agreed upon and documented in writing.

ReMA maintains an Arbitration Service to help members settle differences between themselves or with non-members.

The "Guidelines for Metals Transactions" contain supplementary information to support business transactions. We recommend reviewing these Guidelines alongside the specifications.

For the most current version of ReMA's ISRI Specifications, visit ISRIspecs.org.

Issued by:



Recycled Materials
Association
Sustainable. Resilient. Essential.

RULES GOVERNING THE PROCEDURES FOR THE ADDITION, AMENDMENT, OR WITHDRAWAL OF SPECIFICATIONS

- 1.0 *Initiation of Request.* Any person may file a request to add, amend or withdraw a specification by submitting such request in writing to the ReMA President.
- 1.1 The President shall refer such request to the Chair of the appropriate Division Specifications Committee (the "Committee"), with copies to:
- A. ReMA's Officers;
 - B. The Chair of any ReMA Division and/or Committee that might be affected by the specification.
- 2.0 *Committee Action.* Following presentation by all interested parties, the Committee shall review the request and:
- A. Act upon it prior to the next meeting of the Board, as set forth in Section 2.1; or
 - B. Refer it to a subcommittee for review and recommendation for action by the full Committee at its next meeting.
- 2.1 The Committee shall summarize the positions advocated by the various parties interested in the request and recommend to the appropriate division and the Board of Directors what action should be taken.
- 3.0 *Notice.* A notice of the Committee recommendations shall be distributed to all ReMA members, a news release will be distributed to industry trade publications and a notice will be posted on the ReMA website at least twenty days before the request will be considered by the Board of Directors. Such notice shall state:
- A. The date, time and place at which the request will be considered by the Board;
 - B. That the proceeding at which the request will be considered shall be open to the public;
 - C. That interested parties may participate in the proceeding by personal appearance or by submitting written comments;
 - D. A summary of the specification and the matter to be considered at the meeting.
- 4.0 *Board of Directors Action.* The Board of Directors, at its meeting at which the report and recommendation of the Committee has been made, may adopt, amend or reject the recommendation or table it pending further review and recommendation by the Committee.
- 4.1 Notice of the action taken by the Board shall be given to all interested parties who actively participated in the Committee proceeding and any other persons who have requested in writing notice of the Board's action. Notice of said action also shall be distributed to all ReMA members, a news release will be distributed to industry trade publications and a notice will be posted on the ReMA website on or before ten days following the Board's action.
- 5.0 *Appeal.* On or before thirty days after the date of the notice required in Section 4.1, any party may appeal the decision of the Board by written notice to the President. Said appeal shall state the reasons for the appeal and the requested action to be taken. Notice of said appeal shall be given in accordance with Section 1.0.
- 5.1 The appeal shall be heard by the Board at its next meeting following receipt of the appeal.
- 5.2 The appellant and all interested parties shall be given at least twenty days notice of the date, time and place of the hearing, and like notice shall be inserted in the ReMA newsletter at least twenty days prior to the hearing.
- 5.3 At the hearing, the appellant and any other interested party may appear either in person or by written presentation and state their reasons for the appeal.
- 5.4 The Board, following said hearing, shall review and act upon the appeal. Notice of the Board's action shall be given in accordance with Section 4.1.
- 6.0 *Records.* ReMA shall maintain for not less than five years following the date of termination of the proceedings, records of the original request, summaries of the deliberations and recommendations of the Committee, action of the Board, summaries of the appeal and final decision, if any, of the Board, together with the positions of interested parties, copies of notices sent to interested parties and inserted in the ReMA newsletter and national trade publications, written statements, and the reasons for recommendation and final action by the Committee and the Board.
- 6.1 Said records shall be available for review by the public upon reasonable notice.

RECENT REVISIONS

The Recycled Materials Association (ReMA) Board of Directors approved the following changes to ReMA's ISRI Specifications at its Spring Meeting in Las Vegas, NV on April 13, 2026:

NONFERROUS

New Specification

GINGER

Mixed shredded cast aluminum that is mechanically segregated from Zorba and Twitch. The Material must be dry and not contain more than 1 percent max free Mg, 1 percent max free Zn, and 1 percent max free Fe. Not containing more than 1 percent max non-metallics. Material to be free of excessively oxidized material, air bag canisters, or any sealed or pressurized items. Any variation to be sold by special arrangement between buyer and seller.

FERROUS

Revised Specifications

Ferrous – Special (Tire Wire)

Processed Tire Wire grades revised to begin at 1%, raise to 3% and then 5%, and then raise by 5% each grade until 30%, with a total of 9 grades. This reflects the higher value and potential new markets available for cleaner grades of wire.

Off the Road (or OTR) added as a separate category for Pulled Bead Wire, with the same three grades as the current Truck and Passenger categories.

Specifications renamed as Ferrous – Special (Tire Wire)

The Recycled Materials Association (ReMA) Board of Directors approved the following changes to ReMA's ISRI Specifications at its Winter Meeting in Washington, DC on February 12, 2026:

INBOUND RESIDENTIAL SINGLE STREAM

HDPE rigid can and bottle carriers added to acceptable plastics list

INBOUND RESIDENTIAL DUAL STREAM

HDPE rigid can and bottle carriers added to acceptable plastics list

PAPER STOCK

Revised Specifications

Revised Preamble of the Guidelines for Paper Stock

Guidelines for Nonferrous Scrap: NF-2025

Note: When the individual scrap grades in this document, denoted by the various code words, are used, an agreement between parties is also bound by the terms of “Apple” as it appears below, unless the terms and conditions of a specific contract provide otherwise, in which case the specific contractual provisions shall govern.

CODE	ITEM	CODE	ITEM
Apple	Nonferrous Terms		
	a. Delivery of more or less of the specified quantity up to 3 percent is permissible. b. A ton shall be understood to be 2,000 pounds, unless otherwise specified. c. If any portion of the goods covered by a contract are unshipped or undelivered within the time specified in a contract, then that portion is subject to cancellation by the buyer and/or the buyer has the right to hold the seller responsible for substantiated damages. d. If, because of embargo and/or other conditions of force majeure, a delivery or shipment cannot be made by the time specified, the contract shall remain valid and shall be completed promptly upon lifting of the embargo and/or conditions of force majeure and the terms of said contract shall not be changed. e. If for any portion of a contract the buyer fails in a timely manner to open a Letter of Credit and/or fails to provide proper conveyance and/or shipping instructions as specified in the contract, then that portion is subject to cancellation by the seller and/or the seller has the right to hold the buyer responsible for substantiated damages. f. If, because of embargo and/or other conditions of force majeure, a delivery or shipment cannot be made by the time specified, the contract shall remain valid and shall be completed promptly upon lifting of the embargo and/or conditions of force majeure, and the terms of said contract shall not be changed.		g. If a significant weight or quality difference is apparent, the seller should be notified promptly and, if requested, another weight or quality determination should be taken. Seller and/or buyer should be given the opportunity to appoint an independent surveyor or a representative to verify weights and/or quality. h. For purposes of this section, the meaning of the word “significant” shall be determined by agreement between buyer and seller, depending on the commodities and their values. i. If it is mutually determined that goods delivered do not conform to the description specified in the contract, then the shipment is subject to rejection or downgrade. j. Disposition of, replacement of, and/or financial adjustment for rejected material shall be subjected to mutual agreement between buyer and seller. Seller is responsible for freight costs. k. Buyer is expected, however, to exert every effort to limit rejections only to that portion of the shipment which is unsortable and to return the rejected portion promptly upon request, if government regulations permit.

RED METALS

Heavier pieces of any size, length, and weight acceptable upon mutual agreement between buyer and seller.

CODE	ITEM
Barley	No. 1 COPPER WIRE Shall consist of No. 1 bare, uncoated, unalloyed copper wire, commonly known as Bare Bright copper wire. Wire gauge subject to agreement between buyer and seller. Green copper wire and hydraulically compacted material to be subject to agreement between buyer and seller.
Cliff	No. 2 COPPER SOLIDS AND TUBING Shall consist of miscellaneous, unalloyed copper scrap having a nominal 96% copper content (minimum 94%) as determined by electrolytic assay. Should be free of the following: Excessively leaded, tinned, soldered copper scrap; brasses and bronzes; excessive oil content, iron and non-metallics; copper tubing with other than copper connections or with sediment; copper wire from burning; insulation; hair wire; brittle burnt wire; and should be reasonably free of ash. Hydraulically briquetted copper subject to agreement.
Berry	No. 1 COPPER WIRE Shall consist of clean, untinned, uncoated, unalloyed copper wire and cable, free of brittle burnt wire. Wire gauge subject to agreement between buyer and seller. Free of copper tubing. Hydraulically briquetted copper subject to agreement.
Birch	No. 2 COPPER WIRE Shall consist of miscellaneous, unalloyed copper wire having a nominal 96% copper content (minimum 94%) as determined by electrolytic assay. Should be free of the following: Excessively leaded, tinned, soldered copper wire; brass and bronze wire; excessive oil content, iron, and non-metallics; copper wire from burning; insulation; hair wire; brittle burnt wire; and should be reasonably free of ash. Hydraulically briquetted copper subject to agreement.
Birch/Cliff	COMBINATION A combination of No. 2 copper wire and copper as defined in Birch and Cliff. See above.
Candy	No. 1 HEAVY COPPER SOLIDS AND TUBING Shall consist of clean, unalloyed, uncoated copper clippings, punchings, bus bars, commutator segments, and clean copper tubing. Hydraulically briquetted copper subject to agreement.

CODE	ITEM
Berry/Candy	Candy/Berry COMBINATION A combination of copper wire and heavy copper as defined in Berry and Candy. See above.
Clove	No. 1 COPPER WIRE NODULES Shall consist of No. 1 bare, uncoated, unalloyed copper wire scrap nodules, chopped or shredded, free of tin, lead, zinc, aluminum, iron, other metallic impurities, insulation, and other foreign contamination. Minimum copper 99%. Gauge smaller than No. 16 B & S wire and hydraulically compacted material subject to agreement between buyer and seller.
Cobra	No. 2 COPPER WIRE NODULES Shall consist of No. 2 unalloyed copper wire scrap nodules, chopped or shredded, minimum 97% copper. Maximum metal impurities not to exceed 0.50% aluminum and 1% each of other metals or insulation. Hydraulically compacted material subject to agreement between buyer and seller.
Cocoa	COPPER WIRE NODULES Shall consist of unalloyed copper wire scrap nodules, chopped or shredded, minimum 99% copper. Shall be free of excessive insulation and other non-metallics. Maximum metal impurities as follows: Aluminum .05%, Tin .25%, Nickel .05%, Antimony .01%, Iron .05%. Hydraulically compacted material subject to agreement between buyer and seller.
Dream	LIGHT COPPER Shall consist of miscellaneous, unalloyed copper scrap having a nominal 92% copper content (minimum 88%) as determined by electrolytic assay and shall consist of sheet copper, gutters, downspouts, kettles, boilers, and similar scrap. Should be free of the following: Burnt hair wire; copper clad; plating racks; grindings; copper wire from burning, containing insulation; radiators and fire extinguishers; refrigerator units; electrotype shells; screening; excessively leaded, tinned, soldered scrap; brasses and bronzes; excessive oil, iron and non-metallics; and should be reasonably free of ash. Hydraulically briquetted copper subject to agreement. Any items excluded in this grade are also excluded in the higher grades above.
Drink	REFINERY BRASS Shall contain a minimum of 61.3% copper and maximum 5% iron and to consist of brass and bronze solids and turnings, and alloyed and contaminated copper scrap. Shall be free of insulated wire, grindings, electrotype shells and non-metallics. Hydraulically briquetted material subject to agreement.

CODE	ITEM	CODE	ITEM
Droid	INSULATED COPPER WIRE SCRAP Shall consist of No. 2 copper wire (see Birch) with various types of insulation. To be sold on a sample or recovery basis, subject to agreement between buyer and seller. Existence of jelly wire subject to agreement between buyer and seller.	Eland	HIGH GRADE—LOW LEAD BRONZE/BRASS SOLIDS It is recommended these materials be sold by analysis.
Drove	COPPER-BEARING SCRAP Shall consist of miscellaneous copper-containing skimmings, grindings, ashes, irony brass and copper, residues and slags. Shall be free of insulated wires; copper chlorides; unprepared tangled material; large motors; pyrophoric material; asbestos brake linings; furnace bottoms; high lead materials; graphite crucibles; and noxious and explosive materials. Fine powdered material by agreement. Hydraulically briquetted material subject to agreement.	Elder	GENUINE BABBITT-LINED BRASS BUSHINGS Shall consist of red brass bushings and bearings from automobiles and other machinery, shall contain not less than 12% high tin-base babbitt, and shall be free of iron-backed bearings.
Druid	INSULATED COPPER WIRE SCRAP Shall consist of No. 1 bare, uncoated, unalloyed copper wire (see Barley), not smaller than No. 16 B & S wire gauge (unless smaller wire gauge is mutually agreed upon), with various types of insulation. To be sold on sample or recovery basis, subject to agreement between buyer and seller.	Elias	HIGH LEAD BRONZE SOLIDS AND BORINGS It is recommended that these materials be sold on sample or analysis.
Ebony	COMPOSITION OR RED BRASS Shall consist of red brass scrap, valves, machinery bearings and other machinery parts, including miscellaneous castings made of copper, tin, zinc, and/or lead. Shall be free of semi-red brass castings (78% to 81% copper); railroad car boxes and other similar high-lead alloys; cocks and faucets; closed water meters; gates; pot pieces; ingots and burned brass; aluminum, silicon, and manganese bronzes; iron and non-metallics. No piece to measure more than 12" over any one part or weigh over 100 lbs. Heavier pieces acceptable upon mutual agreement between buyer and seller.	Enerv	RED BRASS COMPOSITION TURNINGS Shall consist of turnings from red brass composition material and should be sold subject to sample or analysis.
Ebulent	LEAD-FREE BISMUTH BRASS SOLIDS Shall consist of scrap castings alloyed with copper, tin, bismuth, and zinc. Castings shall be free of leaded brass attachments and have less than 0.2% alloyed lead or as agreed between buyer and seller. Examples that meet this specification include, but are not limited to, CDA 89833/35/36/37/41/42 and 45.	Engel	MACHINERY OR HARD BRASS SOLIDS Shall have a copper content of not less than 75%, a tin content of not less than 6%, and a lead content of not less than 6% nor more than 11%, and total impurities, exclusive of zinc, antimony, and nickel of not more than 0.75%; the antimony content not to exceed 0.50%. Shall be free of lined and unlined standard red car boxes.
Ecstatic	LEAD-FREE BISMUTH BRASS TURNINGS Shall consist of scrap borings and turnings alloyed with copper, tin, bismuth, and zinc. Turnings shall be unmixed and have less than 0.2% alloyed lead or as agreed between buyer and seller. Examples that meet this specification include, but are not limited to, CDA 89833/35/36/37/41/42 and 45.	Erin	MACHINERY OR HARD BRASS BORINGS Shall have a copper content of not less than 75%, a tin content of not less than 6%, and a lead content of not less than 6% nor more than 11%, and the total impurities, exclusive of zinc, antimony, and nickel of not more than 0.75%; the antimony content not to exceed 0.50%.
		Fence	UNLINED STANDARD RED CAR BOXES (CLEAN JOURNALS) Shall consist of standard unlined and/or sweated railroad boxes and unlined and/or sweated car journal bearings, free of yellow boxes and iron-backed boxes.
		Ferry	LINED STANDARD RED CAR BOXES (LINED JOURNALS) Shall consist of standard babbitt-lined railroad boxes and/or babbitt-lined car journal bearings, free of yellow boxes and iron-backed boxes.
		Grape	COCKS AND FAUCETS Shall consist of mixed clean red and yellow brass, including chrome or nickel-plated, free of gas cocks, beer faucets, and aluminum and zinc base die cast material, and to contain a minimum of 35% semired.

CODE	ITEM	CODE	ITEM
Honey	YELLOW BRASS SCRAP Shall consist of mixed yellow brass solids, including brass castings, rolled brass, rod brass, tubing and miscellaneous yellow brasses, including plated brass. Must be free of manganese-bronze, aluminum-bronze, unsweated radiators or radiator parts, iron, and excessively dirty and corroded materials. Must also be free of any type of munitions including, but not limited to, bullet casings.	Maize	MIXED NEW NICKEL SILVER CLIPPINGS Shall consist of one or more nickel silver alloys and the range of nickel content to be specified, free of chrome or any other plating material. Leaded nickel silver clippings should be packed and sold separately. Not to contain more than 10% of clean punchings under 1/4 inch.
Ivory	YELLOW BRASS CASTINGS Shall consist of yellow brass castings in crucible shape, no piece to measure more than 12 inches over any one part; and shall be free of brass forgings, silicon bronze, aluminum bronze and manganese bronze, and not to contain more than 15% nickel plated material.	Major	NEW NICKEL SILVER CLIPPINGS AND SOLIDS Shall consist of new, clean nickel silver clippings, plate, rod and forgings, and other rolled shapes, free of chrome or any other plating material. Must be sold on nickel content specifications such as 10%–12%–15%–18%–20%. Leaded nickel silver clippings should be packed and sold separately. A description as to its physical characteristics should be made in offering all nickel silver material.
Label	NEW BRASS CLIPPINGS Shall consist of the cuttings of new unleaded yellow brass sheet or plate, to be clean and free from foreign substances and not to contain more than 10% of clean brass punchings under 1/4 inch. To be free of Muntz metal and naval brass.	Malar	NEW SEGREGATED NICKEL SILVER CLIPPINGS Shall consist of one specified nickel silver alloy. Not to contain more than 10% of clean punchings under 1/4 inch.
Lace	BRASS SHELL CASES WITHOUT PRIMERS Shall consist of clean fired 70/30 brass shell cases free of primers and any other foreign material. For material to be exported from the United States, all shells must be sufficiently mutilated to prevent reuse and reloading.	Malic	OLD NICKEL SILVER Shall consist of old nickel silver sheet, pipe, rod, tubes, wire, screen, soldered or unsoldered. Must not be trimmed seams alone, and must also be free of foreign substances, iron rimmed material and other metals.
Lady	BRASS SHELL CASES WITH PRIMERS Shall consist of clean fired 70/30 brass shell cases containing the brass primers, and containing no other foreign material. For material to be exported from the United States, all shells must be sufficiently mutilated to prevent reuse and reloading.	Melon	BRASS PIPE Shall consist of brass pipe free of plated and soldered materials or pipes with cast brass connections. To be sound, clean pipes free of sediment and condenser tubes.
Lake	BRASS SMALL ARMS AND RIFLE SHELLS, CLEAN FIRED Shall consist of clean fired 70/30 brass shells free of bullets, iron and any other foreign material. For material to be exported from the United States, all shells must be sufficiently mutilated to prevent reuse and reloading.	Naggy	NICKEL SILVER CASTINGS To be packed and sold separately.
Lamb	BRASS SMALL ARMS AND RIFLE SHELLS, CLEAN MUFFLED (POPPED) Shall consist of clean muffled (popped) 70/30 brass shells free of bullets, iron and any other foreign material. For material to be exported from the United States, all shells must be sufficiently mutilated to prevent reuse and reloading.	Nascent	LEADED BRASS SCRAP TURNINGS Shall consist of scrap borings and turnings alloyed with copper, zinc, and lead. Turnings shall be unmixed and have less than 0.01% alloyed bismuth and silicon each and other impurities as agreed between buyer and seller.
Lark	YELLOW BRASS PRIMER Shall consist of clean yellow brass primers, burnt or unburnt. Shall be free of iron, excessive dirt, corrosion and any other foreign material.	Niche	LEADED BRASS SCRAP ROD ENDS AND FORGINGS Shall consist of scrap rod ends and forgings alloyed with copper, zinc, and lead. Solids shall have less than 0.01% alloyed bismuth and silicon each and other impurities as agreed between buyer and seller.
		Niece	NICKEL SILVER TURNINGS To be sold by sample or analysis.

CODE	ITEM
Night	YELLOW BRASS ROD TURNINGS Shall consist strictly of rod turnings, free of aluminum, manganese, composition, Tobin and Muntz metal turnings; not to contain over 3% free iron, oil or other moisture; to be free of grindings and babbitts; to contain not more than 0.30% tin and not more than 0.15% alloyed iron.
Noble	NEW YELLOW BRASS ROD ENDS Shall consist of new, clean rod ends from free turning brass rods or forging rods, not to contain more than 0.30% tin and not more than 0.15% alloyed iron. To be free of Muntz metal and naval brass or any other alloys. To be in pieces not larger than 12" and free of foreign matter.
Nomad	YELLOW BRASS TURNINGS Shall consist of yellow brass turnings, free of aluminum, manganese and composition turnings, not to contain over 3% of free iron, oil or other moisture; to be free of grindings and babbitts. To avoid dispute, to be sold subject to sample or analysis.
Ocean	MIXED UNSWEATED AUTO RADIATORS Shall consist of mixed automobile radiators, to be free of aluminum radiators, and iron-finned radiators. All radiators to be subject to deduction of actual iron. The tonnage specification should cover the gross weight of the radiators, unless otherwise specified.
Pales	BRASS CONDENSER TUBES Shall consist of clean condenser tubing which may be plated or unplated, free of excessive corroded material as mutually agreed. Upon mutual agreement between buyer and seller, may be in the form of whole bundles including iron and/or brass heads as well as iron and/or brass baffles.
Pallu	ALUMINUM BRASS CONDENSER TUBES Shall consist of clean sound condenser tubing which may be plated or unplated, free of nickel alloy and corroded material.
Palms	MUNTZ METAL TUBES Shall consist of clean sound Muntz metal tubing which may be plated or unplated, free of nickel alloy, aluminum alloy, and corroded material.
Parch	MANGANESE BRONZE SOLIDS Shall have a copper content of not less than 55%, a lead content of not more than 1%, and shall be free of aluminum bronze and silicon bronze.

ALUMINUM

Heavier pieces of any size, length, and weight acceptable upon mutual agreement between buyer and seller.

CODE	ITEM
Ginger	SHREDDED ALUMINUM CAST Mixed shredded cast aluminum that is mechanically segregated from Zorba and Twitch. The Material must be dry and not contain more than 1 percent max free Mg, 1 percent max free Zn, and 1 percent max free Fe. Not containing more than 1 percent max non-metallics. Material to be free of excessively oxidized material, air bag canisters, or any sealed or pressurized items. Any variation to be sold by special arrangement between buyer and seller.
Tablet	CLEAN ALUMINUM LITHOGRAPHIC SHEETS To consist of 1000 and/or 3000 series alloys, to be free of paper, plastic, excessively inked sheets, and any other contaminants. Minimum size of 3" (8 cm) in any direction.
Tabloid	NEW, CLEAN ALUMINUM LITHOGRAPHIC SHEETS To consist of 1000 and/or 3000 series alloys, uncoated, unpainted, to be free of paper, plastic, ink, and any other contaminants. Minimum size of 3" (8 cm) in any direction.
Taboo	MIXED LOW COPPER ALUMINUM CLIPPINGS AND SOLID Shall consist of new, clean, uncoated and unpainted low copper aluminum scrap of two or more alloys with a minimum thickness of 0.015 inches (.38 mm) and to be free of 2000 and 7000 series, hair wire, wire screen, punchings less 1/2 inch (1.25 cm) diameter, dirt, and other non-metallic items. Grease and oil not to total more than 1%. Variations to this specification should be agreed upon prior to shipment between the buyer and seller.
Taint/Tabor	CLEAN MIXED OLD ALLOY SHEET ALUMINUM Shall consist of clean old alloy aluminum sheet of two or more alloys, free of foil, venetian blinds, castings, hair wire, screen wire, food or beverage containers, radiator shells, airplane sheet, bottle caps, plastic, dirt, and other non-metallic items. Oil and grease not to total more than 1%. Up to 10% Tale permitted.
Take	NEW ALUMINUM CAN STOCK Shall consist of new low copper aluminum can stock and clippings, clean, lithographed or not lithographed, and coated with clear lacquer but free of lids with sealers, iron, dirt and other foreign contamination. Oil not to exceed 1%.

CODE	ITEM	CODE	ITEM
Talc	POST-CONSUMER ALUMINUM CAN SCRAP Shall consist of old aluminum food and/or beverage cans. The material is to be free of other scrap metals, foil, tin cans, plastic bottles, paper, glass, and other non-metallic items. Variations to this specification should be agreed upon prior to shipment between the buyer and seller.	Taldon	BALED ALUMINUM USED BEVERAGE CAN (UBC) SCRAP Shall have a minimum density of 14 pounds per cubic foot (225 kg/m ³), and a maximum density of 17 pounds per cubic foot (273 kg/m ³) for unflattened UBC and 22 pounds per cubic foot (353 kg/m ³) for flattened UBC. Size: Minimum 30 cubic feet (.85 m ³), with bale range dimensions of 24" to 40" (61 to 132 cm) by 30" to 52" (76 to 132 cm) by 40" to 84" (102 to 213 cm). The only acceptable tying method shall be as follows: four to six 5/8" (1.6 cm) x .020" (5 mm) steel bands, or six to ten #13 gauge steel wires (aluminum bands or wires are acceptable in equivalent strength and number). Use of skids and/or support sheets of any material is not acceptable. Must be magnetically separated material and free of steel, lead, bottle caps, plastic cans and other plastic, glass, wood, dirt, grease, trash, and other foreign substances. Any free lead is basis for rejection. Any and all aluminum items, other than used beverage cans, are not acceptable. Variations to this specification should be agreed upon prior to shipment between the seller and buyer.
Talcred	SHREDDED ALUMINUM USED BEVERAGE CAN (UBC) SCRAP Shall have a density of 12 to 17 pounds per cubic foot (193 to 273 kg/m ³). Material should contain maximum 5% fines less than 4 mesh (U.S. standard screen size) (6.35 mm). Must be magnetically separated material and free of steel, lead, bottle caps, plastic cans and other plastics, glass, wood, dirt, grease, trash, and other foreign substances. Any free lead is basis for rejection. Any and all aluminum items, other than used beverage cans, are not acceptable. Variations to this specification should be agreed upon prior to shipment between the seller and buyer.		
Taldack	DENSIFIED ALUMINUM USED BEVERAGE CAN (UBC) SCRAP Shall have a biscuit density of 35 to 50 pounds per cubic foot (562 to 802 kg/m ³). Each biscuit not to exceed 60 pounds (27.2 kg). Nominal biscuit size range from 10" to 13" x 10 1/4" (25.4 x 33 x 26 cm) to 20" x 6 1/4" x 9" (50.8 x 15.9 x 22.9 cm). Shall have banding slots in both directions to facilitate bundle banding. All biscuits comprising a bundle must be of uniform size. Size: Bundle range dimensions acceptable are 41" to 44" x 51" (104 to 112 cm) to 54" x 54" (137 x 137 cm) to 56" (142 cm) high. The only acceptable tying method shall be as follows: Using minimum 5/8" (1.6 cm) wide by .020" (.05 cm) thick steel straps, the bundles are to be banded with one vertical band per row and a minimum of two firth (horizontal) bands per bundle. Use of skids and/or support sheets of any material is not acceptable. Must be magnetically separated material and free of steel, lead, bottle caps, plastic cans and other plastic, glass, wood, dirt, grease, trash, and other foreign substances. Any free lead is basis for rejection. Any and all aluminum items, other than used beverage cans, are not acceptable. Items not covered in the specifications, including moisture, and any variations to this specification should be agreed upon prior to shipment between the seller and buyer.	Taldork	BRIQUETTED ALUMINUM USED BEVERAGE CAN (UBC) SCRAP Shall have a briquette density of 50 pounds per cubic foot (800 kg/m ³) minimum. Nominal briquette size shall range from 12" to 24" (30.5 x 61 cm) x 12" to 24" (30.5 x 61 cm) in uniform profile with a variable length of 8" (20.3 cm) minimum and 48" (122 cm) maximum. Briquettes shall be bundled or stacked on skids and secured with a minimum of one vertical band per row and a minimum of one girth band per horizontal layer. Briquettes not to overhang pallet. Total package height shall be 48" (122 cm) maximum. Banding shall be at least 5/8" (1.6 cm) wide by .020" (5 mm) thick steel strapping or equivalent strength. The weight of any bundle shall not exceed 4,000 pounds (1.814 mt). Material must be magnetically separated and free of steel, plastic, glass, dirt and all other foreign substances. Any and all aluminum items other than UBC are unacceptable. Any free lead is basis for rejection. Items not covered in the specification, including moisture, and any variations to this specification should be agreed upon prior to shipment between the buyer and seller.
		Tale	PAINTED SIDING Shall consist of clean, low copper aluminum siding scrap, painted one or two sides, free of plastic coating, iron, dirt, corrosion, fiber, foam, or fiberglass backing or other non-metallic items.

CODE	ITEM	CODE	ITEM
Talk	ALUMINUM COPPER RADIATORS Shall consist of clean aluminum and copper radiators, and/or aluminum fins on copper tubing, free of brass tubing, iron and other foreign contamination.	Tarry C	IRONY ALUMINUM PISTONS Shall consist of aluminum pistons with non-aluminum attachments to be sold on a recovery basis or by special arrangement between buyer and seller.
Tall	E.C. ALUMINUM CHOPS AND STRAWS Shall consist of clean, 1350 and/or 1050 alloy, E.C. aluminum, chops or straws, free of screening, hairwire, iron, copper, insulation and other non-metallic items. Must be free of minus 20 mesh material. Must contain 99.45% aluminum content.	Tassel	OLD MIXED ALUMINUM WIRE AND CABLE Shall consist of old, unalloyed aluminum wire and cable which may contain up to 10% 6000 series wire and cable with not over 1% free oxide or dirt and free from hair wire, wire screen, iron, insulation and other non-metallic items.
Tally	ALL ALUMINUM RADIATORS FROM AUTOMOBILES Shall consist of clean aluminum radiators and/or condensers. Should be free of all other types of radiators. All contaminants including iron, plastic, and foam not to exceed 1% of weight. Any deviation to this specification, including oxidation and aluminum content, to be negotiated between buyer and seller.	Taste	OLD PURE ALUMINUM WIRE AND CABLE Shall consist of old, unalloyed aluminum wire and cable containing not over 1% free oxide or dirt and free from hair wire, wire screen, iron, insulation and other non-metallic items.
Talon	E.C. ALUMINUM WIRE AND CABLE Shall consist of new, clean, 1350 and/or 1050, E.C. aluminum wire or cable free from hair wire, ACSR, wire screen, tape, iron, insulation and other non-metallic items. Must contain 99.45% aluminum content.	Tata	NEW PRODUCTION ALUMINUM EXTRUSIONS Shall consist of one alloy (typically 6063). Material may contain "butt ends" from the extrusion process but must be free of any foreign contamination. Anodized material is acceptable. Painted material or alloys other than 6063 must be agreed upon by buyer and seller.
Tank	ALUMINUM CHOPS AND STRAWS Shall consist of clean aluminum, chops or straws, free of screening, hair-wire, iron, copper, insulation and other non-metallic items. Must be free of minus 20 mesh material. Must contain 99% aluminum content.	Tease	ALUMINUM WIRE AND CABLE Shall consist of new, clean, aluminum wire or cable free from hair wire, ACSR, wire screen, iron, insulation and other non-metallic items. Must contain 99% aluminum content.
Tann	NEW MIXED ALUMINUM WIRE AND CABLE Shall consist of new, clean, unalloyed aluminum wire or cable which may contain up to 10% 6000 series wire and cable free from hair wire, wire screen, iron, insulation and other non-metallic items.	Teens	SEGREGATED ALUMINUM BORINGS AND TURNINGS Shall consist of aluminum borings and turnings of one specified alloy. Material should be free of oxidation, dirt, free iron, stainless steel, magnesium, oil, flammable liquids, moisture and other non-metallic items. Fines should not exceed 3% through a 20 mesh (U.S. standard) screen.
Tarry A	CLEAN ALUMINUM PISTONS Shall consist of clean aluminum pistons to be free from struts, bushings, shafts, iron rings and nonmetallic items. Oil and grease not to exceed 2%.	Telic	MIXED ALUMINUM BORINGS AND TURNINGS Shall consist of clean, uncorroded aluminum borings and turnings of two or more alloys and subject to deductions for fines in excess of 3% through a 20 mesh screen and dirt, free iron, oil, moisture and all other non-metallic items. Material containing iron in excess of 10% and/or free magnesium or stainless steel or containing highly flammable cutting compounds will not constitute good delivery. To avoid dispute, material should be sold on basis of definite maximum zinc, tin and magnesium content.
Tarry B	CLEAN ALUMINUM PISTONS WITH STRUTS Shall consist of clean whole aluminum pistons with struts. Material is to be free from bushings, shafts, iron and non-metallic items. Oil and grease not to exceed 2%.	Tense	MIXED ALUMINUM CASTINGS Shall consist of all clean aluminum castings which may contain auto and airplane castings but no ingots, and to be free of iron, brass, dirt and other non-metallic items. Oil and grease not to total more than 2%.

CODE	ITEM	CODE	ITEM
Tepid	AIRCRAFT SHEET ALUMINUM Should be sold on recovery basis or by special arrangements with purchaser.	Tooth	SEGREGATED NEW ALUMINUM ALLOY CLIPPINGS AND SOLIDS Shall consist of new, clean, uncoated and unpainted aluminum scrap of one specified aluminum alloy with a minimum thickness of .015" (.38 mm) and to be free of hair wire, wire screen, dirt and other nonmetallic items. Oil and grease not to total more than 1%. Also free from punchings less than 1/2" (1.27 cm) in size.
Terse	NEW ALUMINUM FOIL Shall consist of clean, new, pure, uncoated 1000 and/or 3000 and/or 8000 series alloy aluminum foil, free from anodized foil, radar foil and chaff, paper, plastics, or any other non-metallic items. Hydraulically briquetted material and other alloys by agreement between buyer and seller.	Toto	ALUMINUM EXTRUSIONS "10/10" Material to consist of new production and old/used 6063 extrusions that may contain up to (but not exceed) 10 percent painted extrusions and 10 percent 6061 alloy extrusions. Must not contain other alloys of aluminum. Material should be free of zinc corners, iron attachments, felt, plastic, paper, cardboard, thermo break, and dirt and other contaminants.
Tesla	POST CONSUMER ALUMINUM FOIL Shall consist of baled old household aluminum foil and formed foil containers of uncoated 1000, 3000 and 8000 series aluminum alloy. Material may be anodized and contain a maximum of 5% organic residue. Material must be free from radar chaff foil, chemically etched foil, laminated foils, iron, paper, plastic and other non-metallic contaminants.	Tough	MIXED NEW ALUMINUM ALLOY CLIPPINGS AND SOLIDS Shall consist of new, clean, uncoated and unpainted aluminum scrap of two or more alloys with a minimum thickness of .015" (.38 mm) and to be free of hair wire, wire screen, dirt and other non-metallic items. Oil and grease not to total more than 1%. Also free from punchings less than 1/2" (1.27 cm) in size.
Tetra	NEW COATED ALUMINUM FOIL Shall consist of new aluminum foil coated or laminated with ink, lacquers, paper, or plastic. Material shall be clean, dry, free of loose plastic, PVC and other non-metallic items. This foil is sold on a metal content basis or by sample as agreed between buyer and seller.	Tread	SEGREGATED NEW ALUMINUM CASTINGS, FORGINGS AND EXTRUSIONS Shall consist of new, clean, uncoated aluminum castings, forgings, and extrusions of one specified alloy only and to be free from sawings, stainless steel, zinc, iron, dirt, oil, grease and other non-metallic items.
Thigh	ALUMINUM GRINDINGS Should be sold on recovery basis or by special arrangements with purchaser.	Trill	ACSR Aluminum Conductor Steel Reinforced (ACSR) wire is a combination of steel and aluminum wire, of various configurations, with the expected aluminum recovery agreed upon by the buyer and the seller. Material to be free of other wires and cables unless mutually agreed upon.
Thirl	ALUMINUM DROSSES, SPATTERS, SPILLINGS, SKIMMINGS AND SWEEPINGS Should be sold on recovery basis or by special arrangements with purchaser.	Troma	ALUMINUM AUTO OR TRUCK WHEELS Shall consist of clean, single-piece, unplated aluminum wheels of a single specified alloy, free of all inserts, steel, wheel weights, valve stems, tires, grease and oil and other non-metallic items. Variations to this specification should be agreed upon prior to shipment between the buyer and seller.
Thorn	ALUMINUM BREAKAGE Shall consist of aluminum with miscellaneous contaminants like iron, dirt, plastic and other types of contaminants. Material can either be sold based on aluminum recovery or content as agreed upon by buyer and seller. Must contain a minimum of 33% aluminum unless otherwise agreed upon by buyer and seller.	Trump	ALUMINUM AUTO CASTINGS Shall consist of all clean automobile aluminum castings of sufficient size to be readily identified and to be free from iron, dirt, brass, bushings, and non-metallic items. Oil and grease not to total more than 2%.
Throb	SWEATED ALUMINUM Shall consist of aluminum scrap which has been sweated or melted into a form or shape such as an ingot, sow or slab for convenience in shipping; to be free from corrosion, dross or any non-aluminum inclusions. Should be sold subject to sample or analysis.		

CODE	ITEM	CODE	ITEM
Tutu	ALUMINUM EXTRUSION DEALER GRADE Shall consist of old extruded aluminum of one alloy, typically alloy 6063, 6061, or 7075. Material must be free of iron, thermo break, saw chips, zinc corners, dirt, paper, cardboard, and other foreign contamination. Percentages of paint or other alloys to be agreed upon by buyer and seller.	Twist	ALUMINUM AIRPLANE CASTINGS Shall consist of clean aluminum castings from airplanes and to be free from iron, dirt, brass, bushings, and non-metallic items. Oil and grease not to total more than 2%.
Twang	IAW Insulated aluminum wire, which may or may not contain other wires or metal shielding, with the expected aluminum recovery agreed upon by the buyer and the seller. The material to be free of other wires and cables unless mutually agreed upon.	Twitch	FLOATED FRAGMENTIZER ALUMINUM SCRAP (FROM AUTOMOBILE SHREDDERS) Derived from wet or dry media separation device, the material must be dry and not contain more than 1% maximum free zinc, 1% maximum free magnesium, and 1% maximum of analytical iron. Not to contain more than a total 2% maximum of non-metallics, of which no more than 1% shall be rubber and plastics. To be free of excessively oxidized material, air bag canisters, or any sealed or pressurized items. Any variation to be sold by special arrangement between buyer and seller.
Tweak	FRAGMENTIZER ALUMINUM SCRAP (FROM AUTOMOBILE SHREDDERS) Derived from either mechanical or hand separation, the material must be dry and not contain more than 4% maximum free zinc, 1% maximum free magnesium, and 1.5% maximum of analytical iron. Not to contain more than a total 5% maximum of non-metallics, of which no more than 1% shall be rubber and plastics. To be free of excessively oxidized material, air bag canisters, or any sealed or pressurized items. Any variation to be sold by special arrangement between buyer and seller.	Vesper	VESPER Can be made up of aluminum sheet, extrusion and/or plate grades (wrought aluminum) segregated from zorba or twitch. The material must be dry and not contain more than 1 percent max free Mg [magnesium], 1 percent max free Zn [zinc] and 0.5 percent analytical Fe [ferrous]. Not containing more than 1 percent max nonmetallics. Material to be free of excessively oxidized material, air bag canisters or any sealed or pressurized items. Any variation to be sold by special arrangement between buyer and seller.
Twire	BURNT FRAGMENTIZER ALUMINUM SCRAP (FROM AUTOMOBILE SHREDDERS) Incinerated or burned material must be dry and not contain more than X% (% to be agreed upon by buyer and seller) ash from incineration, 4% maximum free zinc, 1% maximum free magnesium, and 1.5% maximum of analytical iron. Not to contain more than a total 5% maximum of non-metallics, of which no more than 1% shall be rubber and plastics. To be free of excessively oxidized material, air bag canisters, or any sealed pressurized items. Any variation to be sold by special arrangement between buyer and seller.	Zorba	SHREDDED NONFERROUS SCRAP (PREDOMINANTLY ALUMINUM) Shall be made up of a combination of the nonferrous metals: aluminum, copper, lead, magnesium, stainless steel, nickel, tin, and zinc, in elemental or alloyed (solid) form. The percentage of each metal within the nonferrous concentrate shall be subject to agreement between buyer and seller. Material generated by eddy current, air separation, flotation, screening, other segregation technique(s), or a combination thereof. Shall have passed one or more magnets to reduce or eliminate free iron and/or large iron attachments. Shall be free of radioactive material, dross, or ash. Material to be bought/sold under this guideline shall be identified as "Zorba" with a number to follow indicating the estimated percentage nonferrous metal content of the material (e.g., "Zorba 90" means the material contains approximately 90% nonferrous metal content). May also be screened to permit description by specific size ranges. (Refer also to Zorba under Mixed Metals.)
Twirl 2.0	FRAGMENTIZER AIRCRAFT ALUMINUM SCRAP (2000 AND 7000 SERIES) The material as received must be dry and not to contain more than 2% free zinc, 1% maximum free magnesium, and 1.5% maximum free iron and stainless with a maximum of 2% analytical iron. Not to contain more than a total 5% maximum of non-metallics, of which no more than 1% shall be rubber and plastics. To be free of excessively oxidized material. Any variations to be sold by special arrangement between buyer and seller. This is the new version for 2023 of Twirl.		

ZINC

Heavier pieces of any size, length, and weight acceptable upon mutual agreement between buyer and seller.

CODE	ITEM	CODE	ITEM
Saves	OLD ZINC DIE CAST SCRAP Shall consist of miscellaneous old zinc base die castings, with or without iron and other foreign attachments. Material can include zinc dies/molds for shoes or other industrial purposes. Must be free of borings, turnings, dross pieces, chunks, melted pieces and skimmings. All unmeltables, dirt, foreign attachments, and volatile substances (such as rubber, cork, plastic, grease, etc.) are deductible. Material containing in excess of 30% iron will not constitute good delivery.	Scroll	UNSORTED ZINC DIE CAST SCRAP Produced from automobile fragmentizers. Material to contain about 55% zinc-bearing scrap. Other nonferrous metals such as aluminum, stainless steel, brass/copper/copper alloys, etc., to be about 40%. Insulated copper wire about 1%. Trash, dirt, glass, rubber, oil, iron, not to exceed 5%. Any variations to be sold by special arrangement between buyer and seller.
Scabs	NEW ZINC DIE CAST SCRAP Shall consist of new or unused, clean, zinc base die castings. Castings to be unplated, unpainted, and free from corrosion.	Scrub	HOT DIP GALVANIZERS SLAB ZINC DROSS (BATCH PROCESS) Shall consist only of galvanizers unsweated zinc dross in slab form from hot dip galvanizing (Batch Process) with a minimum zinc content of 92% and shall be free of skimmings and tramp iron. Broken pieces under 2" in diameter shall not exceed 10% of the weight of each shipment. Slabs shall not weigh over 100 pounds each. Heavier pieces acceptable upon mutual agreement between buyer and seller. Material from continuous galvanizing operation is not acceptable. Blocks are acceptable upon mutual agreement.
Scoot	ZINC DIE CAST AUTOMOTIVE GRILLES Shall consist of clean, old or used zinc base die cast automotive grilles, free from soldered material. All foreign attachments and extraneous materials are deductible.	Scul	ZINC DIE CAST SLABS OR PIGS Shall consist of melted zinc base die cast materials, in smooth clean solid slabs or pigs. Material to be free from drosses and to contain a minimum zinc content of 90%. To contain a maximum of 0.1% nickel and maximum of 1% lead. Blocks are acceptable upon mutual agreement.
Scope	NEW PLATED ZINC DIE CAST SCRAP Shall consist of new or unused clean, plated zinc base die castings, free from corrosion.	Seal	CONTINUOUS LINE GALVANIZING SLAB ZINC TOP DROSS Shall consist of unsweated zinc dross removed from the top of a continuous line galvanizing bath, in slab form not weighing in excess of 100 pounds each, with a minimum zinc content of 90%. Heavier pieces acceptable upon mutual agreement between buyer and seller. Shall be free of skimmings. Broken pieces under 2" in diameter shall not exceed 10% of the weight of each shipment.
Score	OLD SCRAP ZINC Shall consist of clean dry scrap zinc, such as sheets, jar lids, clean unalloyed castings and anti-corrosion plates. Borings and turnings are not acceptable. Material must not be excessively corroded or oxidized. All foreign attachments and extraneous materials are deductible.	Seam	CONTINUOUS LINE GALVANIZING SLAB ZINC BOTTOM DROSS Shall consist of unsweated zinc dross removed from the bottom of a continuous line galvanizing bath, in slab form not weighing in excess of 100 pounds each, with a minimum zinc content of 92%. Heavier pieces acceptable upon mutual agreement between buyer and seller. Shall be free of skimmings. Broken pieces under 2" in diameter shall not exceed 10% of the weight of each shipment.
Screen	NEW ZINC CLIPPINGS Shall consist of any new pure zinc sheets or stampings free from corrosion. To contain no foreign material or attachments. Printers zinc, such as engravers zinc, lithograph sheets and addressograph plates subject to special arrangements. Printers zinc to be free of routings.	Shelf	PRIME ZINC DIE CAST DROSS Shall consist of metal skimmed from the top of pot of molten zinc die cast metal. Must be unsweated, unfluxed, shiny, smooth, metallic and free from corrosion or oxidation. Should be poured in molds or in small mounds weighing not over 75 pounds each.
Scribe	CRUSHED CLEAN SORTED FRAGMENTIZERS DIE CAST SCRAP, AS PRODUCED FROM AUTOMOBILE FRAGMENTIZERS To be clean, free of dirt, oil, glass, rubber, and trash. To contain a maximum of 5% unmeltables such as free iron, copper, aluminum and other metals.		

MAGNESIUM

Heavier pieces of any size, length, and weight acceptable upon mutual agreement between buyer and seller.

CODE	ITEM
Wafer	MAGNESIUM CLIPS Shall consist of clean magnesium clips in crucible size, free of copper, aluminum, and zinc flashings and excessive oil and grease. To be free of all foreign attachments.
Walnut	MAGNESIUM SCRAP Shall consist of magnesium castings, magnesium engine blocks and transmission casings, bomber and car wheels, extrusions, and sheet. Material to be free from brass and copper inserts and all foreign attachments. To be free of anodes, hollow castings and explosives. Percentages of and penalties for dirt, oil, grease, and iron to be subject to agreement between buyer and seller. Excessively large pieces to be negotiated between buyer and seller.
Wine	MAGNESIUM ENGRAVER PLATES To be free of copper, aluminum, zinc, and electrotype plates. To be clean and free of all foreign attachments. Magnesium plates shipped loose by agreement between buyer and seller.
Wood	MAGNESIUM DOCKBOARDS Shall consist of clean magnesium dockboard cut or broken to size agreed upon by buyer and seller. To be free of all foreign attachments.
World	MAGNESIUM TURNINGS It is recommended that these materials be sold by special arrangement between buyer and seller.

LEAD

Heavier pieces of any size, length, and weight acceptable upon mutual agreement between buyer and seller.

CODE	ITEM
Racks	SCRAP LEAD—SOFT Shall consist of clean soft scrap lead, free of other materials such as drosses, battery plates, lead covered cable, hard lead, collapsible tubes, foil, type metals, aluminum, zinc, iron and brass fittings, dirty chemical lead and radioactive materials. Review packaging specifications and regulatory status pertaining to shipping with buyer prior to sale.

CODE	ITEM
Radio	MIXED HARD/SOFT SCRAP LEAD Shall consist of clean lead solids and lead shots, free of other materials, such as drosses, battery plates, lead covered cable, collapsible tubes, type metals, aluminum, zinc, iron and brass fittings, dirty chemical lead and radioactive materials. Review packaging specifications and regulatory status pertaining to shipping with buyer prior to sale.
Rains	SCRAP DRAINED/DRY WHOLE INTACT LEAD To be free of any liquid. Cases to be either plastic or rubber and be complete including caps. Non-lead (nicad, ni-fe, carbonaire, etc.) not acceptable. Industrial, steel cased, aircraft (aluminum cased) and partial, cracked or broken batteries and batteries without caps subject to special agreement. Review packaging specifications and regulatory status pertaining to shipping with buyer prior to sale.
Rakes	BATTERY LUGS To be free of scrap lead, wheel weights, battery plates, rubber and/or plastic case material and other foreign material. A minimum of 97% metallic content is required. Review packaging specifications and regulatory status pertaining to shipping with buyer prior to sale.
Reels	MIXED NONFERROUS WHEEL WEIGHTS To consist of nonferrous wheel weights that are a minimum of 35% (overall) Nonferrous and no more than 65% Iron (Fe). Anticipated Nonferrous material may be both Lead and Zinc weights. To be free of foreign material. Final material specifications to be determined between buyer and seller.
Relay	LEAD COVERED COPPER CABLE Free of armored covered cable and foreign material subject to negotiation between buyer and seller.
Rents	LEAD DROSS Should be clean and reasonably free of other materials such as iron, dirt, harmful chemicals or other metals. To be free of radioactive materials, aluminum and zinc. May be bought on an assay basis or as agreed to by buyer and seller. Other metals present such as antimony, tin, etc., to be accounted for as agreed between buyer and seller. Material to be readily dumped from drums. An extra charge may be assessed if material has to be mechanically removed. Review packaging specification and regulatory status pertaining to shipping with buyer prior to sale.

CODE	ITEM
Rink	SCRAP WET WHOLE INTACT LEAD BATTERIES Consisting of SLI (starting, lighting & ignition), automotive, truck, 8-D and commercial golf cart and marine-type batteries. Cases to be either plastic or rubber and to be complete. Non-lead (i.e., ni-cad, ni-fe, carbonaire, etc.) not acceptable. Other types i.e. aircraft (aluminum) gel-cel, lawnmower, etc., and partial, cracked or broken batteries or batteries without caps and the amount of liquid content and any variations to the specification subject to special agreement. Review packaging specifications and regulatory status pertaining to shipping with buyer prior to sale.
Rono	SCRAP INDUSTRIAL INTACT LEAD CELLS Consisting of plates enclosed by some form of complete plastic case. Partial, cracked or broken cells, cells without caps and the amount of liquid content and any variations to the specification subject to special agreement. Review packaging specifications and regulatory status pertaining to shipping with buyer prior to sale.
Roper	SCRAP WHOLE INTACT INDUSTRIAL LEAD BATTERIES Consisting of bus, diesel, locomotive, telephone and/or steel cased batteries. Submarine batteries subject to negotiation. Partial, cracked, broken batteries or batteries without caps and the amount of liquid content and any variations to the specification subject to special agreement. Review packaging specifications and regulatory status pertaining to shipping with buyer prior to sale.
Ropes	LEAD WHEEL WEIGHTS To consist of lead wheel weights with or without iron clips. Not to include scrap lead, lugs or plates unless specifically agreed to. To be free of foreign material. Final material specifications to be determined between buyer and seller.

NICKEL/STAINLESS/HI TEMP

Heavier pieces of any size, length, and weight acceptable upon mutual agreement between buyer and seller.

CODE	ITEM
Aroma	NEW NICKEL SCRAP Shall consist of clean new sheet, plate, bar, tube, and any other wrought nickel scrap solids. Nickel minimum 99%; Cobalt maximum 0.25%; Copper maximum 0.50%. Free of castings, as well as any foreign attachments or other contamination.

CODE	ITEM
Burly	OLD NICKEL SCRAP Shall consist of old and/or new sheet, plate, bar, tube, and any other wrought nickel scrap solids. Material to contain a minimum of 98% nickel; Copper maximum 0.50%. This grade to be free of castings, soldered, brazed, sweated, or painted material, other metallic coating, foreign attachments, or any other contamination.
Dandy	NEW CUPRO NICKEL CLIPS AND SOLIDS Shall consist of clean, new, segregated (normally accepted analysis grades) either 70/30, 80/20, or 90/10 cupro nickel tube, pipe, sheet, plate, or other wrought solid forms. Must be free of foreign attachments or any other contamination.
Daunt	CUPRO NICKEL SOLIDS Shall consist of old, and/or new, segregated (normally accepted analysis grades) either 70/30, 80/20, 90/10 cupro nickel tube, pipe, sheet, plate, or other wrought solid forms. Maximum 2% sediment allowable. Any other forms of cupro nickel solids such as castings, gates, risers, spills, etc., packaged separately, may or may not be included, only upon agreement between buyer and seller. Must be free of foreign attachments and all other contamination. Other particulars concerning physical description, analysis and packaging to be agreed upon between buyer and seller.
Decoy	CUPRO NICKEL SPINNINGS, TURNINGS, BORINGS Shall consist of clean, segregated (normally accepted analysis grades) either 70/30, 80/20, 90/10 cupro nickel spinnings, turnings, or borings. Particulars concerning physical description, analysis, and packaging, to be agreed upon between buyer and seller.
Delta	SOLDERED CUPRO NICKEL SOLIDS Shall consist of segregated (normally accepted analysis grades) either 70/30, 80/20, 90/10 cupro nickel solids, soldered, brazed, or sweated material. Must be free of trimmed seams and edges and all other contamination.
Depth	MISCELLANEOUS NICKEL-COPPER AND NICKEL-COPPER IRON Shall consist of miscellaneous scrap in which the basic elements, by weight, are nickel and copper, such as copper nickel peelings, plating racks, and hangers, and all nickel and copper in attached or combined form. In all cases, miscellaneous nickel copper scrap should be sold by description and analysis.
Hitch	NEW R-MONEL CLIPPINGS AND SOLIDS Shall consist of clean, new, R-Monel sheet, plate, bar, rod, tube, pipe, or any other wrought scrap. Must be free of any foreign attachments or all other contamination.

CODE	ITEM	CODE	ITEM
House	NEW MIXED MONEL SOLIDS AND CLIPPINGS Shall consist of new, clean R and K-Monel solids and clippings. Free of cast material, foreign attachments and all other contamination.	Saint	NICKEL BEARING SCRAP Any nickel bearing alloy scrap that contains a minimum of 3% recovered nickel. Nickel content to be determined by recovery after buyer's evaluation minus any non-conforming material and/or contamination. Balance of elements contained to be discussed between buyer and seller. Material is to be free of any foreign material. Final material specifications to be determined between buyer and seller.
Ideal	OLD MONEL SHEET AND SOLIDS Shall consist of clean R and K-Monel solids such as sheet, plate, pipe, rods, forgings, screen and wire cloth. Must be free of soldered, brazed, welded, or sweated material, cast material, foreign attachments, and all other contamination.	Ultra	STAINLESS STEEL TURNINGS Shall consist of clean 18-8 type stainless steel turnings containing a minimum 7% nickel and 16% chrome, and to be free of nonferrous metals, nonmetallics, excessive iron, oil and other contaminants. Particulars concerning physical description, assay, and packaging to be agreed upon between buyer and seller.
Indian	K-MONEL SOLIDS Shall consist of clean K-Monel solids.	Vaunt	EDISON BATTERIES Nickel-iron batteries to be sold free of crates, copper terminal connectors, and excess liquid. Must be free of nickel cadmium batteries.
Junto	SOLDERED MONEL SHEET AND SOLIDS Shall consist of soldered and/or brazed miscellaneous grades of Monel alloys in either wrought or cast form. Must be free of trimmed seams and edges, non-metallic filling, foreign attachments, and all other contamination. Particulars concerning physical description, assay, and packaging to be agreed upon between buyer and seller.	Zurik	SHREDDED NONFERROUS SENSOR SORTED SCRAP (PREDOMINANTLY STAINLESS STEEL) Shall be made up of a combination of the nonferrous metals: stainless steel, insulated copper wire, aluminum, copper, lead, magnesium, nickel, tin, and zinc, in elemental or alloyed (solid) form. The percentage of each metal within the nonferrous concentrate shall be subject to agreement between buyer and seller. Material generated by computer sensing equipment (e.g., induction sensor sorting or X-ray) technique(s). Shall have passed one or more magnets to reduce or eliminate free iron and/or large iron attachments. Shall be free of radioactive material, dross, or ash. Material to be bought/sold under this guideline shall be identified as "Zurik" with a number to follow indicating the estimated percentage nonferrous content of the material (e.g., "Zurik 90" means the material contains approximately 90% nonferrous metal content). May also be screened to permit description by specific size ranges. (Refer also to Zurik under Mixed Metals.)
Lemon	MONEL CASTINGS Shall consist of various types of clean Monel castings, assaying minimum 60% nickel. Must be free of foreign attachments or any other contamination.		
Lemur	MONEL TURNINGS Shall consist of mixed Monel turnings and borings containing a minimum of 60% nickel content, on a dry basis.		
Pekoe	200 SERIES STAINLESS STEEL SCRAP SOLIDS Shall consist of all types of clean AISI Series Stainless Steel Scrap Solids, which contain a maximum of .5% copper, free of foreign attachments and other contamination.		
Sabot	STAINLESS STEEL SCRAP Shall consist of clean 18-8 type stainless steel clips and solids containing a minimum 7% nickel, 16% chrome, and have a maximum of .50% molybdenum, .50% copper, .045% phosphorous, and .03% sulfur, and otherwise free of harmful contaminants. Particulars concerning physical description, grading, additional analysis, and preparation to be agreed upon between buyer and seller.		

MIXED METALS

Heavier pieces of any size, length, and weight acceptable upon mutual agreement between buyer and seller.

CODE	ITEM
Darth	BALLASTS (FLUORESCENT) Shall consist of whole and complete fluorescent light ballasts containing copper inside. Must not contain polychlorinated biphenyls (PCBs). Electronic ballasts subject to agreement between buyer and seller.
Vader	SEALED UNITS Shall consist of whole steel-cased compressors originating from condensers from air conditioner units, freezers, refrigerators or the like, containing a motor inside. Free of hazardous materials, including chlorofluorocarbons (CFCs) or other refrigerants and polychlorinated biphenyls (PCBs). No loose iron or extra iron attachments such as framework permitted.
Elmo	MIXED ELECTRIC MOTORS Shall consist of whole electric motors and/or dismantled electric motor parts that are primarily copperwound. May contain some aluminum-wound material, subject to agreement between buyer and seller. No excessive steel attachments such as gear reducers, iron bases, and pumps, or loose free iron allowed. Specification not to include sealed units or cast iron compressors.
Sheema	SHREDDED ELECTRIC MOTORS (ALSO CALLED "SHREDDER PICKINGS" OR "MEATBALLS") Shall consist of mixed copper and aluminum bearing material from ferrous shredding, comprised of motors without cases. May contain insulated copper harness wire, subject to agreement between buyer and seller. Trace percentages of other contaminants and fines may be present. No free iron or sealed units.
Shelmo	SHREDDED ELECTRIC MOTORS (ALSO CALLED "SHREDDER PICKINGS" OR "MEATBALLS") Shall consist of mixed copper-bearing material from ferrous shredding, comprised of motors without cases. May contain up to 5 percent aluminum-wound material and may contain insulated copper harness wire, subject to agreement between buyer and seller. Trace percentages of other contaminants and fines may be present. No free iron or sealed units.

CODE	ITEM
Small Elmo	ELECTRIC MOTORS Shall be sized to approximately basketball size or smaller and shall consist of whole electric motors and/or dismantled electric motor parts that are primarily copper-wound. May contain some aluminum-wound material, subject to agreement between buyer and seller. No excessive steel attachments such as gear reducers, iron bases, and pumps, or loose free iron allowed. Specification not to include sealed units or cast iron compressors.
Zebra	(HIGH DENSITY) Shall consist of high-density nonferrous metals produced by media separation technology containing brass, copper, zinc, nonmagnetic stainless steel, and copper wire. Material to be dry and free from excess oxidation. The percentage and types of metals other than these, as well as the percentage and types of nonmetallic contamination, are to be agreed upon between the buyer and seller.
Zeppelin	(LIGHT DENSITY) Shall consist of light-density nonferrous metals produced by media separation technology and contain thin-gauge aluminum and magnesium. Material to be dry and free from excess oxidation. The percentage and types of metals other than aluminum and magnesium, as well as the percentage and types of nonmetallic contamination, are to be agreed upon between the buyer and seller.
Zeyda	SHREDDED INSULATED COPPER WIRE Shall consist predominantly of recovered ICW (Insulated Copper Wire) that has been derived by either mechanical or physical separation. This material is likely to have other metals, in small percentages (should be less than 5%) that were not successfully separated. The percentage of each metal within the overall product shall be subject to agreement between buyer and seller. Shall have passed one or more magnets to reduce or eliminate free iron and/or large iron attachments. Shall be free of radioactive material, dross, or ash. Material to be bought/sold under this guideline shall be identified as "Zeyda" with two numbers to follow, indicating the estimated percentage recoverable copper wire and the second indicating the maximum amount of other metals or contaminants expected. (e.g., "Zeyda 45/3" means the material contains approximately 45% copper and up to 3% other material). May also be screened to permit description by specific size ranges.

CODE	ITEM
Zorba	SHREDDED NONFERROUS SCRAP (PREDOMINANTLY ALUMINUM) Shall be made up of a combination of the nonferrous metals: aluminum, copper, lead, magnesium, stainless steel, nickel, tin, and zinc, in elemental or alloyed (solid) form. The percentage of each metal within the nonferrous concentrate shall be subject to agreement between buyer and seller. Material generated by eddy current, air separation, flotation, screening, other segregation technique(s), or a combination thereof. Shall have passed one or more magnets to reduce or eliminate free iron and/or large iron attachments. Shall be free of radioactive material, dross, or ash. Material to be bought/sold under this guideline shall be identified as "Zorba" with a number to follow indicating the estimated percentage nonferrous metal content of the material (e.g., "Zorba 90" means the material contains approximately 90% nonferrous metal content). May also be screened to permit description by specific size ranges. (Refer also to Zorba under Aluminum.)
Zurik	SHREDDED NONFERROUS SENSOR SORTED SCRAP (PREDOMINANTLY STAINLESS STEEL) Shall be made up of a combination of the nonferrous metals: stainless steel, insulated copper wire, aluminum, copper, lead, magnesium, nickel, tin, and zinc, in elemental or alloyed (solid) form. The percentage of each metal within the nonferrous concentrate shall be subject to agreement between buyer and seller. Material generated by computer sensing equipment (e.g., induction sensor sorting or X-ray) technique(s). Shall have passed one or more magnets to reduce or eliminate free iron and/or large iron attachments. Shall be free of radioactive material, dross, or ash. Material to be bought/sold under this guideline shall be identified as "Zurik" with a number to follow indicating the estimated percentage nonferrous content of the material (e.g., "Zurik 90" means the material contains approximately 90% nonferrous metal content). May also be screened to permit description by specific size ranges. (Refer also to Zurik under Nickel/Stainless/Hi Temp.)

OTHER

Heavier pieces of any size, length, and weight acceptable upon mutual agreement between buyer and seller.

CODE	ITEM
Ranch	BLOCK TIN Block tin must assay minimum of 98% tin, and to be free of liquids, solder, and brass connections, pewter, pumps, pot pieces, and dirt.
Ranks	PEWTER Shall consist of tableware and soda-fountain boxes but should contain a minimum of 84% tin. Siphon tops to be accounted for separately. Material must be free of brass, zinc, and other foreign metals.
Raves	HIGH TIN BASE BABBITT Shall contain a minimum of 78% tin and be free of brassy or zincy metals.
Roses	MIXED COMMON BABBITT Shall consist of lead base bearing metal containing not less than 8% tin, free from Allens metal, ornamental, antimonial and type metal. Must be free from all zinc and excessive copper in the alloy.

IDENTIFICATION CHECKLIST FOR PRECIOUS METALS

This Identification Check List for Precious Metals sets up a general basis for identifying types and grades of precious metals scrap by the scrap processor who will be familiar both to the precious metals refiner and to the plants generating precious metals scrap.

By checking this identification list, the scrap processor gives the refiner a fairly accurate conception of the material the processor has on hand and offers a basis for the refiner to quote an estimated price for the material.

Due to the high values and the constantly changing character of precious metal scrap, it is often the practice in the industry to require a sample to be submitted before giving refining schedules.

I. SCRAP SOURCES

REFINED SILVER METAL—99.9 MIN. PERCENT

Silver-bearing materials:

Anodes Assemblies—Electrical Batteries
Silver/Copper Plated
Silver/Cadmium
Silver/Zinc
Silver/Magnesium
Blanking Scrap—Punchings
Brazing Alloys Brushes—Electric Motors
Bullion
Chemical Salts
Clad Bi-Metal Parts
Coin Silver Contacts
Dental Amalgam Films
Industrial X-Ray
Medical X-Ray
Lithographic
Photographic Negatives
Filters—Plating
Flake—From Hypo Solution Recovery Systems
Hooks—Plating—Nodules
Jewelry Sweeps
Paints—Paste Paper—Reproduction Plated Parts—Electrical—Electronic
Plated Serving Pieces
Plated Utensils Plated Wire
Powders—Granulated
Punchouts Relays—Electrical
Resins
Silver Lined Bearings—Diesel Locomotives and Aircraft
Sludges—Plating and Precipitates
Solutions—Plating
Sterling Silver
Tin Lead Alloys—Contaminated Turnings
Wave Guides
Wiping Rags

REFINED GOLD METAL—99.5 MIN. PERCENT REFINED GOLD SPONGE—99.5 MIN. PERCENT

Gold-bearing materials:

Brazing Alloys

Clad Metal Parts
Contacts
Dental Alloys
Dental Scrap
Dental Sweeps and Grindings
Diodes
Filled Scrap
Filters—Plating
Flakes
Flashings
Foil Hooks—Plating—Nodules
Jewelry Scrap
Jewelry Sweeps and Grindings
Paints and Paste
Peelings
Placer Gold
Plated Parts—Electrical
Plated Wire
Powders
Printed Circuit Boards
Printed Circuit Boards with Components
Punchouts
Resins—Plating
Salts—Chemical
Sludges—Plating
Solutions
Sponge
Tin Lead Alloys—Contaminated
Transistors
Wiping Rags
Wire

REFINED PALLADIUM METAL—99.9 MIN. PERCENT REFINED PALLADIUM SPONGE—99.9 MIN.

Palladium-bearing materials:

Catalysts
Chemical Salts
Clad Materials
Contact Points
Dental Alloys
Dental Scraps
Dental Sweeps
Jewelry Scrap (Sweeps)
Paste
Plated Parts
Powders
Relays—Electrical Sludges
Solutions
Wire

REFINED PLATINUM METAL—99.9 MIN. PERCENT REFINED PLATINUM SPONGE—99.9 MIN. PERCENT

Platinum-bearing materials:

Catalysts
Chemicals
Clad Materials
Contacts
Dental Alloys
Dental Scrap
Dental Sweeps, Grindings
Jewelry Scrap
Jewelry Sweeps
Laboratory Ware
Magneto Points
Powders and Paste
Solutions—Plating
Spark Plugs—Aircraft
Thermocouple Wire

Scrap containing combinations of precious metals (gold, silver, platinum and palladium):

Assemblies—Components Bullion
Carbon
Catalysts
Chemicals
Chips
Drillings
Electronic Scrap
High Temperature Resistant Alloys
Paints
Paste
Powders
Relays—Electrical
Resins
Ribbons
Rings
Salts
Solutions
Sweeps
Telephone Switching Scrap
Thick Film
Wire

II. SCRAP CATEGORIES

A. SOLUTION

1. Acid
2. Basic
3. Matrix if known

B. RESIN

C. SLUDGES

D. BURNABLE MATERIAL

1. Carbon
2. Filters
3. Film
4. Papers
5. Unprepared Sweeps
6. Others

E. SWEEPS (PREPARED)**F. PRINTED CIRCUIT BOARD**

1. Punch Outs
2. Non Assembled
3. Assembled

G. GLASS TO METAL TUBES, ETC.

1. Solid Precious Metal Parts
2. Alloyed Metal Parts
3. Plated Metal Parts
4. Ceramics
5. Thick Film
6. Other...

H. METAL SCRAP*I. Non-Magnetic*

1. Impure Gold
2. Impure Silver
3. Copper Base
4. Aluminum Base
5. Brass Base
6. Bronze Base
7. Molybdenum Base
8. Beryllium Base
9. Lead Base
10. Tin Base
11. Other....

II. Magnetic

1. Kovar Base
2. Stainless Steel Base
3. Iron Base
4. Nickel Base
5. Other....

I. CATALYST

1. Carbon
2. Alumina
3. Rare Earth
4. Silica
5. Other

Guidelines for Ferrous Scrap: FS-2023

GENERAL INFORMATION

a. **Cleanness.** All grades shall be free of dirt, nonferrous metals, or foreign material of any kind, and excessive rust and corrosion. However, the terms “free of dirt, nonferrous metals, or foreign material of any kind” are not intended to preclude the accidental inclusion of negligible amounts where it can be shown that this amount is unavoidable in the customary preparation and handling of the particular grade involved.

b. **Off-grade material.** The inclusion in a shipment of a particular grade of iron and steel scrap of a negligible amount of metallic material which exceeds to a minor extent the applicable size limitations, or which fails to a minor extent to meet the applicable requirements as to quality or kind of material, shall not change the classification of the shipment, provided it can be shown that the inclusion of such off-grade material is unavoidable in the customary preparation and handling of the grade involved.

c. **Residual alloys.** Wherever the term “free of alloys” is used in the classifications given herein, it shall mean that any alloys contained in the steel are residual and have not been added for the purpose of making an alloy steel. Steel scraps shall be considered free of alloys when the residual alloying elements do not exceed the following percentages:

Nickel	0.45%	Molybdenum	0.10%
Chromium	0.20%	Manganese	1.65%

The combined residuals other than manganese shall not exceed a total of 0.60 percent.

d. **Deviations.** Any deviations from the general classifications of iron and steel scrap may be consummated by mutual agreement between buyer and seller.

CODE

ITEM

202

NO. 1 HEAVY MELTING STEEL 5 FEET X 18 INCHES

Wrought iron and/or steel scrap 1/4 inch and over in thickness. Individual pieces not over 60 x 18 inches (charging box size) prepared in a manner to insure compact charging.

203

NO. 2 HEAVY MELTING STEEL*¹

Wrought iron and steel scrap, black and galvanized, 1/8 inch and over in thickness, charging box size to include material not suitable as No. 1 heavy melting steel. Prepared in a manner to insure compact charging.

204

NO. 2 HEAVY MELTING STEEL*

Wrought iron and steel scrap, black and galvanized, maximum size 36 x 18 inches. May include all automobile scrap properly prepared.

205

NO. 2 HEAVY MELTING STEEL 3 FEET X 18 INCHES

Wrought iron and steel scrap, black and galvanized, maximum size 36 x 18 inches. May include automobile scrap, properly prepared; however, to be free of sheet iron or thin gauged material.

206

NO. 2 HEAVY MELTING STEEL 5 FEET X 18 INCHES

Wrought iron and steel scrap, black and galvanized, maximum size 60 x 18 inches. May include automobile scrap, properly prepared; however, to be free of sheet iron or thin gauged material.

207

NO. 1 BUSHING

Clean steel scrap, maximum size 2 feet by 5 feet, including new factory bushing (for example, sheet clippings, stampings, etc.). May not include old auto body and fender stock. Free of metal coated, lined, vitreous enameled, and electrical sheet containing over 0.5 percent silicon.

207A

NEW BLACK SHEET CLIPPINGS

For direct charging, maximum size 8 feet by 18 inches, free of old automobile body and fender stock, metal coated, lined, vitreous enameled and electrical sheet containing over 0.5 percent silicon. Must lay reasonably flat in car.

CODE

ITEM

200

NO. 1 HEAVY MELTING STEEL

Wrought iron and/or steel scrap 1/4 inch and over in thickness. Individual pieces not over 60 x 24 inches (charging box size) prepared in a manner to insure compact charging.

201

NO. 1 HEAVY MELTING STEEL 3 FEET X 18 INCHES

Wrought iron and/or steel scrap 1/4 inch and over in thickness. Individual pieces not over 36 x 18 inches (charging box size) prepared in a manner to insure compact charging.

* The identical designations given for these two classifications are in accordance with established industry practices in specifying the materials desired.

CODE	ITEM	CODE	ITEM
208	NO. 1 BUNDLES New black steel sheet scrap, clippings or skeleton scrap, compressed or hand bundled, to charging box size, and weighing not less than 75 pounds per cubic foot. (Hand bundles are tightly secured for handling with a magnet.) May include Stanley balls or mandrel wound bundles or skeleton reels, tightly secured. May include chemically detinned material. May not include old auto body or fender stock. Free of metal coated, limed, vitreous enameled, and electrical sheet containing over 0.5 percent silicon.	216	TERNE PLATE BUNDLES New terne plate sheet scrap, clippings or skeleton scrap, compressed or hand bundled, to charging box size, and weighing not less than 75 pounds per cubic foot. (Hand bundles are tightly secured for handling with a magnet.) May include Stanley balls or mandrel wound bundles or skeleton reels, tightly secured.
209	NO. 2 BUNDLES Old black and galvanized steel sheet scrap, hydraulically compressed to charging box size and weighing not less than 75 pounds per cubic foot. May not include tin or lead-coated material or vitreous enameled material.	217	BUNDLED NO. 1 STEEL Wrought iron and/or steel scrap 1/8 inch or over in thickness, compressed to charging box size and weighing not less than 75 pounds per cubic foot. Free of all metal-coated material.
210	SHREDDED SCRAP Homogeneous iron and steel scrap, magnetically separated, originating from automobiles, unprepared No. 1 and No. 2 steel, miscellaneous baling and sheet scrap. Average density 50 pounds per cubic foot.	218	BUNDLED NO. 2 STEEL Wrought iron or steel scrap, black or galvanized, 1/8 inch and over in thickness, compressed to charging box size and weighing not less than 75 pounds per cubic foot. Auto body and fender stock, burnt or hand stripped, may constitute a maximum of 60 percent by weight. (This percent based on makeup of auto body, chassis, driveshafts, and bumpers.) Free of all coated material, except as found on automobiles.
211	SHREDDED SCRAP Homogeneous iron and steel scrap magnetically separated, originating from automobiles, unprepared No. 1 and No. 2 steel, miscellaneous baling and sheet scrap. Average density 70 pounds per cubic foot.	219	MACHINE SHOP TURNINGS Clean steel or wrought iron turnings, free of iron borings, nonferrous metals in a free state, scale, or excessive oil. May not include badly rusted or corroded stock.
212	SHREDDED CLIPPINGS Shredded 1000 series carbon steel clippings or sheets. Material should have an average density of 60 pounds per cubic foot.	220	MACHINE SHOP TURNINGS AND IRON BORINGS Same as machine shop turnings but including iron borings.
213	STEEL CAN BUNDLES Steel can scrap compressed to charging box size and weighing not less than 75 pounds per cubic foot. Cans may be baled without removal of paper labels, but free of other non-metallics. May include up to 5 gallon tin coated containers.	221	SHOVELING TURNINGS Clean short steel or wrought iron turnings, drillings, or screw cuttings. May include any such material whether resulting from crushing, raking, or other processes. Free of springy, bushy, tangled or matted material, lumps, iron borings, nonferrous metals in a free state, grindings, or excessive oil.
214	NO. 3 BUNDLES Old sheet steel, compressed to charging box size and weighing not less than 75 pounds per cubic foot. May include all coated ferrous scrap not suitable for inclusion in No. 2 bundles.	222	SHOVELING TURNINGS AND IRON BORINGS Same as shoveling turnings but including iron borings.
215	INCINERATOR BUNDLES Tin can scrap, compressed to charging box size and weighing not less than 75 pounds per cubic foot. Processed through a recognized garbage incinerator.	223	IRON BORINGS Clean cast iron or malleable iron borings and drillings, free of steel turnings, scale, lumps or excessive oil.
		224	AUTO SLABS Clean automobile slabs, cut 3 feet x 18 inches and under.
		225	AUTO SLABS Clean automobile slabs, cut 2 feet x 18 inches and under.

CODE	ITEM
226	BRIQUETTED IRON BORINGS Analysis and density to consumer's specifications.
227	BRIQUETTED STEEL TURNINGS Analysis and density to consumer's specifications.
228	MILL SCALE Dark colored, ranging from blue to black, ferromagnetic iron oxide forming on the surface of steel articles during heating and working.

ELECTRIC FURNACE CASTING AND FOUNDRY GRADES

CODE	ITEM
229	BILLET, BLOOM AND FORGE CROPS Billet, bloom, axle, slab, heavy plate and heavy forge crops, containing not over 0.05 percent phosphorus or sulphur and not over 0.5 percent silicon, free from alloys. Dimensions not less than 2 inches in thickness, not over 18 inches in width, and not over 36 inches in length.
230	BAR CROPS AND PLATE SCRAP Bar crops, plate scrap, forgings, bits, jars, and tool joints, containing not over 0.05 percent phosphorus or sulphur, not over 0.5 percent silicon, free from alloys. Dimensions not less than 1/2 inch in thickness, not over 18 inches in width, and not over 36 inches in length.
231	PLATE AND STRUCTURAL STEEL, 5 FEET AND UNDER Cut structural and plate scrap, 5 feet and under. Clean open hearth steel plates, structural shapes, crop ends, shearings, or broken steel tires. Dimensions not less than 1/4 inch thickness, not over 5 feet in length and 18 inches in width. Phosphorus or sulphur not over 0.05 percent.
232	PLATE AND STRUCTURAL STEEL, 5 FEET AND UNDER Cut structural and plate scrap, 5 feet and under. Clean open hearth steel plates, structural shapes, crop ends, shearings, or broken steel tires. Dimensions not less than 1/4 inch thickness, not over 5 feet in length and 24 inches in width. Phosphorus or sulphur not over 0.05 percent.
233	CAST STEEL Steel castings not over 48 inches long or 18 inches wide, and 1/4 inch and over in thickness, containing not over 0.05 percent phosphorus or sulphur, free from alloys and attachments. May include heads, gates, and risers.

CODE	ITEM
234	PUNCHINGS AND PLATE SCRAP Punchings or stampings, plate scrap, and bar crops containing not over 0.05 percent phosphorous or sulphur and not over 0.5 percent silicon, free from alloys. All materials cut 12 inches and under, and with the exception of punchings or stampings, at least 1/8 inch in thickness. Punchings or stampings under 6 inches in diameter may be any gauge.
235	ELECTRIC FURNACE BUNDLES New black steel sheet scrap hydraulically compressed into bundles of size and weight as specified by consumer.
236	CUT STRUCTURAL AND PLATE SCRAP, 3 FEET AND UNDER Clean open hearth steel plates, structural shapes, crop ends, shearings, or broken steel tires. Dimensions not less than 1/4 inch in thickness, not over 3 feet in length and 18 inches in width. Phosphorus or sulphur not over 0.05 percent.
237	CUT STRUCTURAL AND PLATE SCRAP, 2 FEET AND UNDER Same as cut structural and plate scrap, 3 feet and under, except for length.
238	CUT STRUCTURAL AND PLATE SCRAP, 1 FOOT AND UNDER Same as cut structural and plate scrap, 3 feet and under, except for length.
239	SILICON BUSHELING Clean silicon bearing steel scrap, not exceeding 12 inches in any dimension, including new factory busheling (for example, sheet clippings, stampings, etc.), having a silicon content of 0.05 percent to 5.0 percent.
240	SILICON CLIPPINGS Clean steel scrap, including new factory busheling (for example, sheet clippings, stampings, etc.), may not include old auto body and fender stock. Free of metal coated, limed, vitreous enameled, and electrical sheet containing minimum 1 percent silicon.
241	CHARGEABLE INGOTS AND INGOT BUTTS Chargeable ingots and ingot butts for material to be suitable and acceptable to the consumer containing not over 0.05 percent phosphorus or sulphur and not over 0.05 percent silicon free of alloys.
242	FOUNDRY STEEL, 2 FEET AND UNDER Steel scrap 1/8 inch and over in thickness, not over 2 feet in length or 18 inches in width. Individual pieces free from attachments. May not include nonferrous metals, cast or malleable iron, cable, vitreous enameled, or metal coated material.

CODE	ITEM
243	FOUNDRIY STEEL, 1 FOOT AND UNDER Same specifications as 2-foot material, except for length.
243A	LOW RESIDUAL, BLACK FOUNDRIY BUSHELING 1000 series black carbon steel scrap, 1/8 inch and over in thickness, not more than 12 inch x 24 inch, manganese content not more than 0.50 percent. Other parameters subject to agreement between supplier and consumer.
243B	LOW RESIDUAL, DUCTILE QUALITY SHREDDED CLIPS Shredded black 1000 series carbon steel scrap, 1/8 inch and over in thickness, minimum average density of 75 PCF, manganese content not more than 0.50 percent. Other parameters subject to agreement between supplier and consumer.
244	SPRINGS AND CRANKSHAFTS Clean automotive springs and crankshafts, either new or used.
245	ALLOY FREE TURNINGS Clean shoveling steel turnings free from lumps, tangled or matted material, iron borings, or excessive oil containing not more than 0.05 percent phosphorus or sulphur, and free of alloys.
246	ALLOY FREE SHORT SHOVELING STEEL TURNINGS Clean shoveling steel turnings, free of lumps, tangled or matted material, iron borings, or excessive oil, containing not more than 0.05 percent phosphorus or sulphur, and free of alloys.
247	ALLOY FREE MACHINE SHOP TURNINGS Clean steel turnings, free of iron borings or excessive oil, containing not more than 0.05 percent phosphorus or sulphur, and free of alloys. May not include badly rusted or corroded stock.
248	HARD STEEL CUT 30 INCHES AND UNDER Automotive steel consisting of rear ends, crankshafts, driveshafts, front axles, springs, and gears prepared 30 inches and under. May not include miscellaneous small shoveling steel or any pieces too bulky for gray iron foundry use.
249	CHARGEABLE SLAB CROPS Chargeable slab crops for material to be suitable and acceptable to the consumer containing not over 0.05 percent phosphorus and 0.05 percent sulphur and not over 0.05 percent silicon and free of alloys.
250	SILICON BUNDLES Silicon sheet scrap, clippings or skeleton scrap, compressed or hand bundled, to charging box size, and weighing not less than 75 pounds per cubic foot, having a silicon content of 0.50 percent to 5.0 percent.

CODE	ITEM
251	HEAVY TURNINGS Short, heavy steel turnings, containing not over 0.05 percent phosphorus or sulphur and free of alloys. May include rail chips. May not include machine shop or other light turnings and must weigh not less than 75 pounds per cubic foot in the original state of production.

SPECIALLY PROCESSED GRADES TO MEET CONSUMER REQUIREMENTS

Grades of scrap prepared especially to meet with steel mill or foundry requirements, individual specifications to be agreed on between consumer and supplier.

Cast Iron Grades

CODE	ITEM
252	CUPOLA CAST Clean cast iron scrap such as columns, pipes, plates, and castings of a miscellaneous nature, including automobile blocks and cast iron parts of agricultural and other machinery. Free from stove plate, burnt iron, brake shoes or foreign material. Cupola size, not over 24 inches x 30 inches, and no piece over 150 pounds in weight.
253	CHARGING BOX CAST Clean cast iron scrap in sizes not over 60 inches in length or 30 inches in width, suitable for charging into an open hearth furnace without further preparation. Free from burnt iron, brake shoes, or stove plate.
254	HEAVY BREAKABLE CAST Cast iron scrap over charging box size or weighing more than 500 pounds. May include cylinders and driving wheel centers. May include steel which does not exceed 10 percent of the casting by weight.
255	HAMMER BLOCK OR BASES Cast iron hammer blocks or bases.
256	BURNT IRON Burnt cast iron scrap, such as stove parts, grate bars, and miscellaneous burnt iron. May include sash weights or window weights.
257	MIXED CAST May include all grades of cast iron except burnt iron. Dimensions not over 24 inches x 30 inches and no piece over 150 pounds in weight.
258	STOVE PLATE, CLEAN CAST IRON STOVE Free from malleable and steel parts, window weights, plow points, or burnt cast iron.

CODE	ITEM
259	CLEAN AUTO CAST Clean auto blocks; free of all steel parts except camshafts, valves, valve springs, and studs. Free of nonferrous and non-metallic parts.
260	UNSTRIPPED MOTOR BLOCKS Automobile or truck motors from which steel and nonferrous fittings may or may not have been removed. Free from driveshafts and all parts of frames.
261	DROP BROKEN MACHINERY CAST Clean heavy cast iron machinery scrap that has been broken under a drop. All pieces must be of cupola size, not over 24 inches x 30 inches, and no piece over 150 pounds in weight.
262	CLEAN AUTO CAST, BROKEN, NOT DEGREASED Clean auto blocks, free of all steel parts except camshafts, valves, valve springs and studs. Free of nonferrous and non-metallic parts, and must be broken to cupola size, 150 pounds or less.
263	CLEAN AUTO CAST, DEGREASED Free of all steel parts except camshafts, valves, valve springs, and studs. Free of nonferrous and non-metallic parts, and must be broken into cupola size, 150 pounds or less.
264	MALLEABLE Malleable parts of automobiles, railroad cars, locomotives, or miscellaneous malleable iron castings. Free from cast iron and steel parts and other foreign material.
265	BROKEN INGOT MOLDS AND STOOLS Broken ingot molds and stools, cast iron, maximum size 2 feet x 3 feet x 5 feet.
266	UNBROKEN INGOT MOLDS AND STOOLS Unbroken ingot molds and stools, cast iron.

Special Boring Grades

CODE	ITEM
267	NO. 1 CHEMICAL BORINGS New clean cast or malleable iron borings and drillings containing not more than 1 percent oil, free from steel turnings, or chips, lumps, scale, corroded or rusty material.
268	BRIQUETTED CAST IRON BORINGS, HOT PROCESS Cast iron borings, heated, briquetted, to a density of approximately 85 percent, oil and water content under 1 percent.

CODE	ITEM
269	BRIQUETTED CAST IRON BORINGS, COLD PROCESS Cast iron boring briquettes, free of steel and nonferrous material, hydraulically compressed into a cohesive solid, reasonably free of oil, and having a density of not less than 60 percent.
270	MALLEABLE BORINGS Clean malleable iron borings and drillings, free of steel turnings, scale, lumps and excessive oil.
271	NO. 2 CHEMICAL BORINGS New clean cast or malleable iron borings and drillings, containing not more than 1.5 percent oil, free from steel turnings, or chips, lumps, scale, corroded or rusty material.

Ferrous – Special (Tire Wire)

General Guidelines

Items not covered in the specifications, and any variations in the specification, are subject to special arrangement between buyer and seller. Percentages listed below are by weight.

Preparation

Consumer and supplier to agree upon preparation for transport, such as the following:

LOOSE—WHOLE.

LOOSE—CHOPPED. If wire is chopped or shredded, parties may wish to specify the means of processing and/or characteristics of the final product (density, length of pieces, etc.).

BALED. Bales of wire should maintain their form during loading, shipment, unloading, storage, and handling typical of that done at a consuming facility, unless otherwise specified.

- **BALED—HIGH DENSITY.** Hydraulically compressed, no dimension larger than 24", density of at least 75 pounds per square foot.
- **BALED—HRB/LOW DENSITY.** Density of less than 75 pounds per square foot. Each bale secured with sufficient number of bale ties drawn tight to insure a satisfactory, delivery.

OTHER MEANS OF PREPARATION. Individual specifications to be agreed upon between consumer and supplier.

CODE	ITEM
272	PULLED BEAD WIRE (TRUCK)—GRADE 1 Not chopped; made up of loops of wire. Less than five percent (<5%) rubber/fiber.
273	PULLED BEAD WIRE (TRUCK)—GRADE 2 Not chopped; made up of loops of wire. Five to ten percent (5–10%) rubber/fiber.

CODE	ITEM
274	PULLED BEAD WIRE (TRUCK)—GRADE 3 Not chopped; made up of loops of wire. Greater than ten percent (>10%) rubber/fiber.
275	PULLED BEAD WIRE (PASSENGER)—GRADE 1 Not chopped; made up of loops of wire. Less than five percent (<5%) rubber/fiber.
276	PULLED BEAD WIRE (PASSENGER)—GRADE 2 Not chopped; made up of loops of wire. Five to ten percent (5–10%) rubber/fiber.
277	PULLED BEAD WIRE (PASSENGER)—GRADE 3 Not chopped; made up of loops of wire. Greater than ten percent (>10%) rubber/fiber.
278	PROCESSED TIRE WIRE (FERROUS)—GRADE 1 Chopped. One percent or less ($\leq 1\%$) rubber/fiber.
279	PROCESSED TIRE WIRE (FERROUS)—GRADE 2 Chopped. One to three percent (1–3%) rubber/fiber.
280	PROCESSED TIRE WIRE (FERROUS)—GRADE 3 Chopped. Three to five percent (3–5%) rubber/fiber.
281	PROCESSED TIRE WIRE (FERROUS)—GRADE 4 Chopped. Five to ten percent (5–10%) rubber/fiber.
282	PROCESSED TIRE WIRE (FERROUS)—GRADE 5 Chopped. Ten to fifteen percent (10–15%) rubber/fiber.
283	PROCESSED TIRE WIRE (FERROUS)—GRADE 6 Chopped. Fifteen to twenty percent (15–20%) rubber/fiber.
284	PROCESSED TIRE WIRE (FERROUS)—GRADE 7 Chopped. Twenty to twenty-five percent (20–25%) rubber/fiber.
285	PROCESSED TIRE WIRE (FERROUS)—GRADE 8 Chopped. Twenty-five to thirty percent (25–30%) rubber/fiber.
286	PROCESSED TIRE WIRE (FERROUS)—GRADE 9 Chopped. Greater than thirty percent (>30%) rubber/fiber.
287	PULLED BEAD WIRE (Off the Road/ OTR)—GRADE 1 Not chopped; made up of loops of wire. Less than five percent (<5%) rubber/fiber.
288	PULLED BEAD WIRE (Off the Road/ OTR)—GRADE 2 Not chopped; made up of loops of wire. Five to ten percent (5–10%) rubber/fiber.
289	PULLED BEAD WIRE (Off the Road/ OTR)—GRADE 3 Not chopped; made up of loops of wire. Greater than ten percent (>10%) rubber/fiber.

Railroad Ferrous Scrap*²

Specifications of Association of American Railroads promulgated by its Purchases and Materials Management Division (Revised 1973)

CODE	ITEM
(2)	AXLES, STEEL Solid car and/or locomotive friction bearing, 8 inch diameter and under (free of axles with key-way between wheel seats, no axles of shorter lengths than distance between wheel seats to be included).
(2A)	AXLES, STEEL Solid car and/or locomotive friction bearing over 8 inch diameter (free of axles with key-way between wheel seats, no axles of shorter length than distance between wheel seats to be included).
(3)	AXLES, STEEL Roller bearing 8 inch diameter and under (no axles of shorter lengths than distance between wheel seats to be included).
(3A)	AXLES, STEEL Roller bearing over 8 inch diameter (no axles of shorter length than distance between wheel seats to be included).
(4)	SPIKES, TRACK BOLTS AND NUTS, AND LOCK WASHERS May include Rail Anchors.
(5)	TIE PLATES Steel.
(6)	RAIL JOINTS, ANGLE AND/OR SPLICE BARS Steel.
(9)	BOLSTERS AND/OR TRUCK SIDES, FRAMES: UNCUT Cast steel.
(11)	CAST STEEL, NO. 2 Steel castings, over 18 inches wide and/or over 5 feet long.
(11A)	CAST STEEL, NO. 1 Steel castings, 18 inches and under, not over 5 feet long, including cut truck side frames and bolsters.
(12)	CAST IRON, NO. 1 Cast iron scrap, such as columns, pipes, plates, and/or castings of miscellaneous nature, but free from stove plates, brake shoes, and burnt scrap. Must be cupola size, not over 24 x 30 inches in dimension and no piece to weigh over 150 pounds. Must be free from foreign material.

^{2*} Specifications in force as of publication date.

CODE	ITEM	CODE	ITEM
(13)	CAST IRON, NO. 2 Pieces weighing over 150 pounds, but not more than 500 pounds. Free from burnt cast.	(28C)	RAIL, STEEL NO. 2 CROPPED RAIL ENDS Standard section, original weight 50 pounds per yard and over, 3 feet long and under.
(14)	CAST IRON, NO. 3 Pieces weighing over 500 pounds; includes cylinders, driving wheel centers and/or all other castings. (Free from hammer blocks or bases.)	(29)	RAIL, STEEL NO. 3 Standard section tee, girder, and/or guard rails, to be free from frog and switch rails not cut apart, and contain no manganese, cast, welds, or attachments of any kind except angle bars. Free from concrete, dirt, and foreign material of any kind.
(15)	CAST IRON, NO. 4 Burnt cast iron scrap, such as grate bars, stove parts and/or miscellaneous burnt scrap.	(30)	SHEET SCRAP, NO. 1 Under 3/16 inch thick, may include hoops, band iron and/or steel, scoops and/or shovels (free of wood). Must be free from burnt or metal coated material, cushion, or other similar springs.
(16)	CAST IRON BRAKE SHOES Brakes shoes of all types except composition-filled shoes.	(31)	SHEET SCRAP, NO. 2 Galvanized or tinned material and/or gas retorts, and/or any other iron or steel material not otherwise classified.
(17)	COUPLERS AND/OR KNUCKLES Railroad car and/or locomotive steel couplers, knuckles and/or locks stripped clean of all other attachments.	(32)	STEEL, TOOL (Specify kind in offering.)
(18)	FROGS AND/OR SWITCHES, UNCUT Steel frogs and switches that have not been cut apart, exclusive of manganese.	(33)	STEEL, MANGANESE All kinds of manganese, rail, guard rails, frogs and/or switch points, cut or uncut.
(18A)	RAILBOUND MANGANESE FROGS AND SWITCH POINTS With manganese inserts that have not been cut apart.	(34)	STEEL, SPRING Coil and/or elliptical, minimum thickness 1/4 inch, may be assembled or cut apart.
(23)	MALLEABLE Malleable parts of automobiles, railroad cars, locomotive and/or miscellaneous malleable castings.	(34A)	STEEL, SPRING Coil only.
(24)	MELTING STEEL, RAILROAD NO. 1 Clean wrought iron or steel scrap, 1/4 inch and over in thickness, not over 18 inches in width, and not over 5 feet in length. May include pipe ends and material 1/8 inch to 1/4 inch in thickness, not over 15 inches x 15 inches. Individual pieces cut so as to lie reasonably flat in charging box.	(35)	STRUCTURAL, WROUGHT IRON AND/OR STEEL UNCUT All steel or steel mixed with iron from bridges, structures and/or equipment that has not been cut apart, may include uncut bolsters, brakebeams, steel trucks, underframes, channel bars, steel bridge plates, frog and/or crossing plates and/or other steel of similar character.
(27)	RAIL, STEEL NO. 1 Standard section tee rails, original weight 50 pounds per yard or heavier, 10 feet long and over. Suitable for rerolling into bars and shapes. Free from bent and twisted rails, frog, switch, and guard rails, or rails with split heads and broken flanges. Continuous welded rail may be included provided no weld is over 9 inches from the end of the piece of rail.	(36)	TIRES All locomotive, not cut to specified lengths.
(28A)	RAIL, STEEL NO. 2 CROPPED RAIL ENDS Standard section, original weight of 50 pounds per yard and over, 18 inches long and under.	(38)	TURNINGS, NO. 1 Heavy turnings from wrought iron and/or steel railroad axles or heavy forgings and/or rail chips, to weigh not less than 75 pounds per cubic foot. Free from dirt or other foreign material of any kind. Alloy steel scrap may be excluded from these specifications by mutual agreement between buyer and seller.
(28B)	RAIL, STEEL NO. 2 CROPPED RAIL ENDS Standard section, original weight of 50 pounds per yard and over, 2 feet long and under.	(38A)	TURNINGS, DRILLINGS AND/OR BORINGS, NO. 2 Cast, wrought, steel and/or malleable iron borings, turnings and/or drillings mixed with other metals.

CODE	ITEM
(40)	WHEELS, NO. 1 Cast iron car wheels.
(42)	WHEELS, NO. 3 Solid cast steel, forged, pressed and/or rolled steel car and/or locomotive wheels, not over 42 inches diameter. (Specify kind in offering.)
(45)	DESTROYED STEEL CARS Bodies of steel cars cut apart sufficiently to load. (Specify kind.)
(45A)	DESTROYED STEEL CAR SIDES AND BOX CAR ROOFS Cut to a maximum length of... and a maximum width of... suitable for use in super presses and shears without additional preparation.

Guidelines for Glass Cullet: GC-2023

Container Glass Cullet Specifications

PREAMBLE

All grades shall be free of dirt, nonferrous metals, or foreign material of any kind, and excessive rust and corrosion. However, the terms “free of dirt, nonferrous metals, or foreign material of any kind” are not intended to preclude the accidental inclusion of negligible amounts where it can be shown that this amount is unavoidable in the customary preparation and handling of the particular grade involved.

SCRAP GLASS DEFINITIONS

CONTAINER GLASS CULLET: crushed or whole scrap soda-lime-silica container glass.

UNPROCESSED CONTAINER GLASS CULLET: broken or whole scrap glass containers that comply with the proper ReMA's ISRI glass specifications.

PROCESSED (FURNACE READY) CONTAINER GLASS CULLET: crushed and whole contaminate-free scrap container glass that complies with the proper ReMA's ISRI glass specifications.

ORGANIC MATTER: consists of organic materials that are non-container glass items; for example, paper labels should not exceed 0.2%.

FERROUS MATERIALS: are magnetic metals, i.e. steel, iron, etc., and therefore must be removed during scrap glass processing.

NON-FERROUS MATERIALS: are non-magnetic metals, i.e. aluminum, lead, copper, etc., and therefore must be removed during glass processing.

The Purchase Agreement

Each transaction covering the purchase or sale of container glass cullet should be confirmed in writing and include agreement on the following items:

1. **PRODUCT**—Where possible, each container glass cullet grade shall be specified in accordance with the grade as defined.
2. **QUANTITY**—Where possible, the quantity shall always be specified in terms of a definite number of tons of 2,000 pounds each.
 - A. If the quantity is specified in tons, the order shall be considered completed when aggregate shipments are 5% under or over the quantity ordered.
 - B. If the quantity is specified in carloads or truck-loads, a “load” shall be defined as a truck, trailer, or railroad car loaded to full visible capacity not to exceed established legal weight limits.

4. **PACKAGING**—It should be stated whether shipped units are to be in boxes, or in bulk by railroad car, truck, or trailer. Where possible, approximate weights should be specified.
5. **PRICE UNITS**—The price agreed upon shall be clearly stated in US dollars and cents per 2,000 pounds or in US dollars and cents per hundred weight.
6. **TERMS**—Terms shall be “net cash 30 days after date of shipment” unless otherwise agreed upon.

Arbitration

In the event of a total disagreement between buyer and seller, the dispute should be submitted to ReMA arbitration.

In all cases, the cost of arbitration shall be borne by the party found to be at fault, or split in the event of compromise, as determined by the arbitrators.

Unprocessed Flint Container Glass Cullet Specifications

COMPOSITION: Soda-lime-silica beverage or food container glass.

CULLET COLORS SEGREGATION: Flint Cullet

Flint	95–100%
Green	0–5%
Amber	0–5%
Other Colors	0–5%

SIZE: Cullet may be broken but not pulverized.

MOISTURE: Cullet should be free of excess moisture.

CONTAMINANT LISTINGS:

Outthrow Materials: Normal container labels; ring and metal closures where processing capabilities permit.

Prohibitive Materials: Non-acceptable items include non-container glass (vision ware, light bulbs, crystal, windows, mirrors, drinking glasses, ceramic, milk glass, etc.) metals, ores, minerals, bricks, clay, grinding and refractory materials, rocks, clay and ceramic closures.

GENERAL: The quality of the unprocessed flint container glass cullet must be such that after beneficiation with a conventional container glass cullet processor it will be suitable for the production of glass containers.

Unprocessed Amber Container Glass Cullet Specifications

COMPOSITION: Soda-lime-silica beverage or food container glass.

CULLET COLORS SEGREGATION: Amber Cullet

Amber 90–100%

Green 0–5%

Flint 0–5%

Other Colors 0–5%

SIZE: Cullet may be broken but not pulverized.

MOISTURE: Cullet should be free of excess moisture.

CONTAMINANT LISTINGS:

Outthrow Materials: Normal container labels; ring and metal closures where processing capabilities permit.

Prohibitive Materials: Non-acceptable items include non-container glass (vision ware, light bulbs, crystal, windows, mirrors, drinking glasses, ceramic, milk glass, etc.) metals, ores, minerals, bricks, clay, grinding and refractory materials, rocks, clay and ceramic closures.

GENERAL: The quality of the unprocessed amber container glass cullet must be such that after beneficiation with a conventional container glass cullet processor it will be suitable for the production of glass containers.

Unprocessed Green Container Glass Cullet Specifications

COMPOSITION: Soda-lime-silica beverage or food container glass.

CULLET COLORS SEGREGATION: Green Cullet

Green 90–100%

Amber 0–10%

Flint 0–10%

Other Colors 0–5%

SIZE: Cullet may be broken but not pulverized.

MOISTURE: Cullet should be free of excess moisture.

CONTAMINANT LISTINGS:

Outthrow Materials: Normal container labels; ring and metal closures where processing capabilities permit.

Prohibitive Materials: Non-acceptable items include non-container glass (vision ware, light bulbs, crystal, windows, mirrors, drinking glasses, ceramic, milk glass, etc.) metals, ores, minerals, bricks, clay, grinding and refractory materials, rocks, clay and ceramic closures.

GENERAL: The quality of the unprocessed green container glass cullet must be such that after beneficiation with a conventional container glass cullet processor it will be suitable for the production of glass containers.

Processed (Furnace Ready) Flint Container Glass Cullet Specifications

COMPOSITION: Soda-lime-silica container glass.

CONTAINER GLASS CULLET COLORS SEGREGATION: Flint Cullet

Flint 95–100%

Amber 0–5%

Green 0–1%

Other Colors 0–.5%

Total NON-Flint Cullet ≤5%

SIZE: Various sizes from whole glass containers to –100 Mesh.

However, the ideal material size is 3/8" to 3/4" with a 10% minimum of fine particles. Material size is based upon buyer and seller's agreement.

CONTAMINANT LISTINGS:

Outthrow Materials: Organic Matter, allowable percentage based upon buyer and seller's agreement.

Prohibitive Materials:

- Ferrous Metals
- Nonferrous Metals
- Ceramics (such as cups, saucers, dinnerware, pottery, etc.)
- Other Glass (for example, plate window glass, heat-resistant glass—such as Pyrex—and lead-based glass—such as crystal ware, television tubes, vision ware, etc.)
- Other Materials (such as bricks, rocks, etc.)

Processed (Furnace Ready) Amber Container Glass Cullet Specifications

COMPOSITION: Soda-lime-silica container glass

CONTAINER GLASS CULLET COLORS SEGREGATION: Amber Cullet

Amber 90–100%

Flint 0–10%

Green 0–10%

Other Colors 0–5%

Total NON-Amber Cullet ≤10%

SIZE: Various sizes from whole glass containers to –100 Mesh.

However, the ideal material size is 3/8" to 3/4" with a 10% minimum of fine particles. Material size is based upon buyer and seller's agreement.

CONTAMINANT LISTINGS:

Outthrow Materials: Organic Matter, allowable percentage based upon buyer and seller's agreement.

Prohibitive Materials:

- Ferrous Metals
- Nonferrous Metals
- Ceramics (such as cups, saucers, dinnerware, pottery, etc.)
- Other Glass (for example, plate window glass, heat-resistant glass—such as Pyrex—and lead-based glass—such as crystal ware, television tubes, vision ware, etc.)
- Other Materials (such as bricks, rocks, etc.)

Processed (Furnace Ready) Green Container Glass Cullet Specifications

COMPOSITION: Soda-lime-silica container glass

CONTAINER GLASS CULLET COLORS SEGREGATION: Green Cullet

Green 70–100%

Flint 0–15%

Amber 0–15%

Other Colors 0–10%

Total NON-Green Cullet = <30%

The color green typically consists of a variety of shades, for example: emerald green or lime green.

SIZE: Various sizes from whole glass containers to -100 Mesh. However, the ideal material size is 3/8" to 3/4" with a 10% minimum of fine particles. Material size is based upon buyer and seller's agreement.

CONTAMINANT LISTINGS:

Outthrow Materials: Organic Matter, allowable percentage based upon buyer and seller's agreement.


Prohibitive Materials:

- Ferrous Metals
- Nonferrous Metals
- Ceramics (such as cups, saucers, dinnerware, pottery, etc.)
- Other Glass (for example, plate window glass, heat-resistant glass—such as Pyrex—and lead based glass—such as crystal ware, television tubes, vision ware, etc.)
- Other Materials (such as bricks, rocks, etc.)

Material Recovery Facility (MRF) Glass

MATERIAL RECOVERY FACILITY-DERIVED 3-COLOR MIXED CONTAINER GLASS ("MRF GLASS"):

MRF Glass consists of crushed or whole scrap Flint (clear), Amber (brown), and Green (emerald) container/ bottle glass made from soda-lime-silica. These standards and practices apply to 3-color mixed glass for purchase or sale in the United States and Canada. Transactions covering shipments to or from other countries may also be in accordance with these standards and practices and may be modified by mutual agreement between buyer and seller. These specifications are guidelines for buying and selling MRF glass and are always subject to the buyer and seller's agreement. It is recognized that MRF Glass may be mixed with other materials as a result of recycling collection convenience and efficiency, and that quality levels vary widely based on the amount of contamination mixed in with the glass.

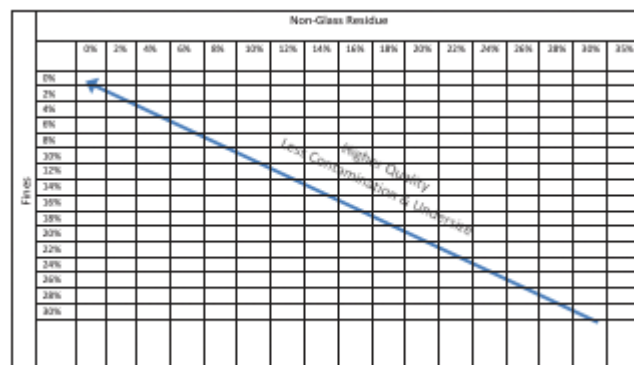

Since there are many different generations of Material Recovery Facilities (MRFs), cleaning equipment in operation, and curbside collection programs, the quality generated by MRFs varies widely. Processors evaluate this heterogeneous material by evaluating the amount of:

- Residue (non-glass residue): Higher amounts of residue result in a lower rank as the processor must separate this residue and dispose of it.
- Undersize: Undersize is otherwise known as "fines". Higher amounts of undersize result in quality issues as very small pieces of glass can't be optically sorted. If a disproportional amount of the stream is too small, it can overwhelm the processor's capabilities.

CONTAMINATION:

Non-Glass Residue—Materials found in dual stream and single stream curbside collection programs entering a Material Recovery Facility (MRF). Examples of this material may be: paper, wood, food or organic material, metal/plastic closures, labels, corks, rock, dirt, and other inert materials. Maximum tolerance—35%.

Undersized or Pulverized Material ("Fines")—This material consists of mixed color glass particles crushed so small as to render current optical sortation unfeasible. Glass particles less than 1/8" are typically considered to be fines. Maximum tolerance—30%.

Ceramics—This material consists of broken bits of household ceramic. Examples of ceramic materials are dinner plates, mugs, cups, etc. Maximum tolerance—2%.

Moisture—This is considered excessive water mixed with glass. Examples of moisture are small fibers soaked by rain, ice or snow. Organic materials and dirt can also contain moisture. Maximum tolerance—5%.

PROHIBITIVES: This material is not allowed and can subject a load to rejection procedure.

- 0.25% of total load allowed:
 - Pyro Ceramics (Fireplace glass)
 - Gypsum, wallboard, drywall, glass from construction & demolition debris mixed with CaCO₃ fines
 - Common moisture-absorbing desiccants (silica gels beads, alumina pellets, closet paks, etc.)
- 0% of total load allowed:
 - CRT glass

- Lead glass
- Tempered window glass
- Flammables
- Radioactive waste
- Weapons
- Medical Waste
- Insecticides
- Poisons
- Heavy Metals
- Asbestos
- Other materials that can be classified as hazardous or harmful to human health or the environment

Guidelines for Paper Stock: PS-2026

PREAMBLE

These standards and practices apply to paper stock for re-pulping. Transactions may be modified by mutual agreement between Buyer and Seller. Once Buyer and Seller come to an agreement regarding the transaction there will either be a purchase or sales agreement outlining the transaction, terms and conditions which will be used for the signed transactions. This agreement will serve as the “governing document” for the transaction.

“Good Faith” Relationship between Buyer-Seller

The following principles of “good faith” have been established:

1. Seller must use due diligence to ascertain that shipments consist of properly packed paper stock and that shipments are made during the period specified.
2. Arbitrary deductions, cancellations and/or rejections by the Buyer are counter to acceptable good trade practices.
3. Seller shall provide the quality of paper stock agreed upon but shall not be responsible for the use of the paper stock or of the manufactured product.

I. THE PURCHASE AGREEMENT

Each transaction covering the purchase or sale of paper stock shall be confirmed by either a purchase or sales agreement which may include the following:

1. **QUALITY**—Where possible, purchases shall be specified in accordance with the grade as defined in the latest paper stock section of ReMA's ISRI Scrap Specifications. Any deviation from the grade listed in the circular should be otherwise specified and agreed upon by both parties in the purchase or sales agreement.
2. **QUANTITY**
 - a. The Buyer and Seller shall establish minimum weights for each load. Any light load fees may be agreed upon by buyer and seller prior to shipment, (i.e., predetermined formula or flat/ton rate under minimum).
 - b. The quantity for the purchase or sale of the paper stock shall always be specified in terms of a definite number of short tons of 2000 pounds each or metric tons of 2204.6 pounds each. In addition, the number of loads shall be specified.
 - c. Packing unit type, such as bales, skids, roles, pallets, boxes, securely tied bundles or loose, should be specified in the Agreement.
3. **PRICING AND TERMS**—Each transaction covering the purchase or sale of paper stock shall be confirmed in writing stating the negotiated price and payment terms agreed to by both the buyer and seller.
4. **SHIPPING PERIOD, TERMS AND INSTRUCTIONS**

- a. Period shall be understood to be within 30 days of the date of the order unless otherwise specified and subsequently agreed to by both buyer and seller.
- b. Shipping terms shall be indicated in accordance with the International Chamber of Commerce's Incoterms for shipping that can be found in the addendum at the end of the preamble.
- c. The Shipping instructions for each load should clearly specify shipping schedule routes, carrier and destination. Shipping instructions shall be provided by the buyer at the time of the order. These instructions should also be included on the bill of lading when shipping for export. Information should include documentation, inspection requirements and pictures if required.

II. FULFILLMENT BY THE SELLER

The practice of the Seller shall be in accordance with the following:

1. **ACCEPTANCE**—All orders shall be confirmed.
2. **GRADING**—Paper stock which is sold under the grade names appearing in the paper stock section of ReMA's ISRI Scrap Specifications shall conform to those grading definitions.
3. **PACKING**—Each unit must be sufficiently secured to ensure a satisfactory delivery.
4. **TARE**—If agreed to by the Buyer, sides and headers may be used to make a satisfactory delivery of the bales but must not be excessive. The weight of skids, Gaylord boxes and other similar materials shall be deducted from the gross invoice weight.
5. **LOADING**—Paper stock shall be loaded as follows:
 - a. Prior to loading, railcars, trucks, trailers and containers shall be free from objectionable materials and odors, and shall have clean sound floors and doors.
 - b. All loads should consist entirely of one grade of paper stock unless otherwise agreed to. When two or more grades are included in the same load, units of each grade should be kept together in a separate part of the railcar, truck, trailer or container.
 - c. Paper stock must be loaded in a manner that will minimize shifting and breakage. Excessive breakage due to improper loading can be cause for a claim or rejection.
 - d. Paper stock shall be loaded in accordance with the customer's preferred safe loading practices or industry safety best practices such as outlines in the ISRI/AF&PA Shipping Guide for Baled Paper Products as a reference.
6. **SHIPPING NOTICE/BILL OF LADING**—A bill of lading or shipping notice shall accompany each shipment to the Buyer and should include the following:
 - a. Date of shipment

- b. Release number (if applicable)
 - c. Number of units
 - d. Grade of paper units
 - e. Weight of load—For combination loads, individual unit weights may be indicated.
 - f. Name of trucking company, trailer, rail car or container number and driver's signature
 - g. Routing Instruction (If applicable)
 - h. Destination (If applicable)
 - i. Shipper's signature
7. **INVOICING**—Invoices, if required, should conform to instructions on the order and include the following data:
- a. Date of shipment
 - b. Railcar, truck number or container number
 - c. Customer's order number
 - d. Release Number (if applicable)/Bill of Lading number
 - e. Shipper's invoice number
 - f. Point of sale
 - g. Number of units
 - h. Weight and grade
 - i. Price and extension
 - j. Payment terms, including credit terms and discounts
8. **Downgrade Claims/Rejections**—When notified of a claim/rejection, the Seller should advise the Buyer, within two business days, as to which of the following procedures the Seller has decided upon:
- a. Agree with the Buyer to a compromise acceptance and settlement.
 - b. Buyer is entitled to full or partial FOB freight reimbursements from seller for downgraded or rejected shipments.
 - c. Inspect the quality of the rejected material. The inspection and final disposition by the Seller should take place within five business days of the notification. By mutual agreement, this time limit may be extended.
 - d. Order repossession of the material (if applicable).
 - e. Request that the Buyer agree to submit the rejected shipment to arbitration.

III. FULFILLMENT BY THE BUYER

The practice of the Buyer shall be in accordance with the following:

1. **THE BUYER WILL CONFIRM ALL ORDERS**
2. **UNLOADING**
 - While unloading the shipment the buyer should inspect the contents as thoroughly as possible.
 - If the shipment appears to be in accordance with the purchase or sales agreement, the buyer shall proceed with the unloading.

- The Buyer is obligated to supply the Seller with the weight of all the received material.
- If the shipment does not appear to be in accordance with the purchase or sales agreement, the Buyer shall immediately notify the Seller.

3. **CLAIMS AND REJECTIONS**—Buyer shall communicate timeframe which is agreed upon by Seller in advance. In the event of a claim or rejection, the Buyer shall be responsible for any paper stock used and the freight thereon. The buyer should use due diligence to maintain all controversial or rejected paper stock from external deterioration or contamination.

IV. MISCELLANEOUS PRACTICES

1. **OWNERSHIP**
 - a. When loaded the shipment is purchased “ex works” shipping point (INCOTerm—EXW) and is in accordance with the purchase agreement covering the transaction, it becomes the property of the Buyer.
 - b. When the shipment is purchased on a “delivered” basis and is in accordance with the purchase or sales agreement covering the transaction, it remains the property of the Seller until it is delivered to the Buyer and verified with proof of delivery.
2. **CARRIER SELECTION**
 - a. When shipment is on FOB or Ex Works, the selection of the carrier is at the discretion of the Buyer unless otherwise agreed.
 - b. When the shipment is on a delivered basis, selection of the carrier is at the discretion of the Seller unless otherwise agreed.
3. **EXCESS FREIGHT AND CHARGES**
 - a. Any excess freight charges accruing on a shipment due to the failure by the Seller to adhere to the purchase agreement is the liability of the Seller and includes switching and freight charges.
 - b. Any excess freight charges accruing on a shipment due to the failure of the Buyer to adhere to the purchase agreement is the liability of the Buyer and includes switching and freight charges
 - c. Any demurrage accruing on a shipment due to the failure of the seller to ship in accordance with the purchase agreement except with respect to quality is the liability of the seller
 - d. In the event that a rejection for quality stands, any demurrage accruing on the shipment prior to notification to the Seller shall be the Buyer's liability.
4. **WEIGHT DISCREPANCIES**
 - In the event of a weight discrepancy between the buyer and seller, the buyer's weight will govern as long as the weight is taken from a certified scale.
 - Upon notification of a weight discrepancy, buyer and seller shall work to reach a resolution within 15 days. If a resolution can't be met, weight will default to certified scale weight of buyer.

- If the buyer does not have a certified weight ticket then the seller's weight will govern as long as it is produced from a certified scale.
- No adjustments shall be made on any shipment of paper stock when the weight variation is 1% or less for domestic loads and 2% or less for export loads.
- If the variation exceeds 1% for domestic loads or 2% for export loads, the Seller may initiate a Weight Review by submitting a certified scale weight (showing the gross, tare and net of the load) and/or a loading tally showing individual bale weights. The Buyer shall then review the data and either:
 - a. Adjust the received weight, or
 - b. Decline the appeal, in which case the Buyer's weight shall prevail.

5. MOISTURE CONTENT

- All paper must be packed dry with a moisture content of 12% which is deemed to be the maximum moisture limit. If Buyer and Seller agree to a different moisture content percentage prior to shipment the buyer and seller shall agree to a moisture percentage and a method by which moisture is to be tested. The agreement is to be confirmed through the purchase agreement and/or the shipping agreement.
- Where and when excess moisture is suspected and determined to be present in the shipment, the Buyer has the right to request an adjustment and if a settlement cannot be reached, the Buyer has the right to reject the shipment. The buyer will conduct testing either by using the mutually agreed upon method or in accordance with the American Forest & Paper Association's Moisture Guide for Measuring Moisture in Recovered Paper Bales. In the event that excess moisture is detected the buyer has the right to request a weight adjustment and if a settlement cannot be reached, the buyer has the right to reject the shipment.

Information: www.afandpa.org

V. ARBITRATION

In the event of a dispute where agreement cannot be reached between Buyer and Seller, the dispute may be submitted to ReMA arbitration as long as one of the parties is a member of the association. Refer to ReMA Arbitration Services section of this document for further information.

VI. GRADE DEFINITIONS

The definitions which follow describe grades as they should be sorted and packed. Consideration should be given to the fact that paper stock, as such, is a secondary material produced manually and may not be technically perfect. Definitions may not specifically address all

types of processes used in the manufacture or recycling of paper products. Specific requirements should be discussed between Buyer and Seller during negotiations.

1. **OUTTHROWS**—The term "Outthrows" as used throughout this section is defined as "all papers that will make the pack

undesirable and unsuitable for consumption as the grade specified."

2. **PROHIBITIVE MATERIALS**—The term "Prohibitive Materials" as used throughout this section is defined as:
 - a. Any materials which by their presence in a packing of paper stock, in excess of the amount allowed, will make the pack unacceptable and unusable as the grade specified.
 - b. Any materials that may be damaging to equipment.
3. **ZERO TOLERANCE**—The term "Zero Tolerance" as used throughout this section is defined as:
Any material that contains any amount of Medical, Organic, Food Waste, Hazardous, Poisonous, Radioactive or Toxic waste and other harmful substances or liquids.
4. **Other Acceptable Papers**—The term "Other Acceptable Papers" as used throughout this section is defined as "all other papers that are deemed acceptable by the buyer and allowed in that buyer's pack up to the percentage allowed."
5. **GLOSSARY OF TERMS**—A supplemental glossary of paper stock terms is located at the end of the Guidelines for Paper Stock. The purpose of this limited list of terms is to help the user better understand specific grade definitions contained within these Guidelines.

CODE ITEM

(4) BOXBOARD CUTTINGS

Consists of new cuttings of paperboard used in the manufacture of folding cartons, set-up boxes and similar boxboard products.

Prohibitive Materials may not exceed 1/2 of 1%.

Outthrows plus prohibitives may not exceed 2%.

(5) MILL WRAPPERS

Consists of paper used as outside wrap for rolls, bundles, or skids of finished paper.

Prohibitive Materials may not exceed 1/2 of 1%.

Outthrows plus prohibitives may not exceed 3%.

(9) OVER-ISSUE NEWS (OI OR OIN)

Consists of unused, overrun newspapers printed on newsprint, containing not more than the normal percentage of rotogravure and colored sections.

Prohibitive Materials: None permitted.

Outthrows plus prohibitives: None permitted.

(10) MAGAZINES (OMG)

Consists of coated magazines, catalogues, and similar printed materials. May contain a small percentage of uncoated news-type paper.

Prohibitive Materials may not exceed 1%.

Outthrows plus prohibitives may not exceed 3%.

(11) OLD CORRUGATED CONTAINERS (OCC)

Consists of corrugated containers having liners of either test liner or kraft.

Prohibitive Materials may not exceed 1%.

Outthrows plus prohibitives may not exceed 5%.

CODE ITEM

- (12) **DOUBLE-SORTED OLD CORRUGATED (DS OCC)**
Consists of double-sorted corrugated containers, generated from supermarkets and/or industrial or commercial facilities, having liners of test liner or kraft. Material has been specially sorted to be free of boxboard, off-shore corrugated, plastic, and wax.
Prohibitive Materials may not exceed 1/2 of 1%.
Outthrows plus prohibitives may not exceed 2%.
- (13) **NEW DOUBLE-LINED KRAFT CORRUGATED CUTTINGS (DLK)**
Consists of new corrugated cuttings having liners of either test liner or kraft. Treated medium or liners, insoluble adhesives, butt rolls, slabbed or hogged medium, are not acceptable in this grade.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 2%.
- (14) **FIBER CORES**
Consists of paper cores made from either recycled paperboard and/or linerboard, single or multiple plies. Metal or plastic end caps, wood plugs, and textile residues are not acceptable in this grade.
Prohibitive Materials may not exceed 1%.
Outthrows plus prohibitives may not exceed 5%.
- (15) **USED BROWN KRAFT**
Consists of brown kraft bags free of objectionable liners and original contents.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 1/2 of 1%.
- (16) **MIXED KRAFT CUTTINGS**
Consists of new brown kraft cuttings, sheets and bag scrap free of stitched paper.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 1%.
- (17) **CARRIER STOCK**
Consists of printed or unprinted, unbleached new beverage carrier sheets and cuttings. May contain wet strength additives.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 1%.
- (18) **NEW COLORED KRAFT**
Consists of new colored kraft cuttings, sheets and bag scrap, free of stitched papers.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 1%.
- (19) **KRAFT GROCERY BAG (KGB)**
Consists of new brown kraft bag cuttings, sheets and misprint bags.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 1%.

CODE ITEM

- (20) **NEW KRAFT MULTI-WALL BAG**
Consists of new brown kraft multi-wall bag cuttings, sheets, and misprint bags, free of stitched papers.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 1%.
- (21) **NEW BROWN KRAFT ENVELOPE CUTTINGS**
Consists of new unprinted brown kraft envelopes, cuttings or sheets.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed .1%.
- (22) **MIXED FLYLEAF SHAVINGS**
Consists of trim of magazines, catalogs, inserts and similar printed matter, not limited with respect to groundwood, uncoated or coated stock, and may contain the bleed of cover and insert stock as well as beater-dyed paper and solid color printing.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 2%.
- (23) **TELEPHONE DIRECTORIES**
Consists of clean telephone directories printed for or by telephone directory publishers.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 1/2 of 1%.
- (24) **WHITE BLANK NEWS (WBN)**
Consists of unprinted cuttings and sheets of white newsprint or other uncoated white groundwood paper of similar quality.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 1%.
- (25) **GROUNDWOOD COMPUTER PRINTOUT (GW CPO)**
Consists of groundwood papers which are used in forms manufactured for use in data processing machines. This grade may contain colored stripes and impact or nonimpact (e.g., laser) computer printing.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 2%.
- (26) **PUBLICATION BLANKS (CPB)**
Consists of unprinted cuttings or sheets of white coated or filled groundwood content paper.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 1%.
- (27) **COATED FLYLEAF SHAVINGS**
Consists of lightly printed trim from magazines, catalogs and similar printed matter, not limited with respect to groundwood, uncoated or coated stock. The bleed of cover, insert card stock, and beater-dyed paper may not exceed 2%.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 1%.

CODE ITEM

- (28) COATED SOFT WHITE SHAVINGS (SWS)**
Consists of unprinted, coated, and uncoated shavings and sheets of white groundwood-free printing paper. May contain a small percentage of groundwood.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 1%.
- (29) (GRADE NOT CURRENTLY IN USE)**
- (30) HARD WHITE SHAVINGS (HWS)**
Consists of shavings or sheets of unprinted, untreated white groundwood-free paper.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 1/2 of 1%.
- (31) HARD WHITE ENVELOPE CUTTINGS (HWEC)**
Consists of groundwood-free cuttings, shavings, or sheets of unprinted, untreated, and uncoated white envelope paper.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 1/2 of 1%.
- (32) (GRADE NOT CURRENTLY IN USE)**
- (33) NEW COLORED ENVELOPE CUTTINGS**
Consists of groundwood-free cuttings, shavings, or sheets of untreated, uncoated bleachable colored envelope paper.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 2%.
- (34) (GRADE NOT CURRENTLY IN USE)**
- (35) SEMI BLEACHED CUTTINGS**
Consists of sheets and cuttings of unprinted, untreated, groundwood-free paper such as file folder stock, untreated milk carton stock, or manila tag.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 2%.
- (36) UNSORTED OFFICE PAPER (UOP)**
Consists of printed or unprinted paper typically generated in an office environment that may include a document destruction process. This grade may contain white, colored, coated and uncoated papers, manila and pastel colored file folders.
Prohibitive Materials may not exceed 2%.
Outthrows plus prohibitives may not exceed 10%.
- (37) SORTED OFFICE PAPER (SOP)**
Consists of paper, as typically generated by offices, containing primarily white and colored groundwood-free paper, free of unbleached fiber. May include a small percentage of groundwood computer printout and facsimile paper.
Prohibitive Materials may not exceed 1%.
Outthrows plus prohibitives may not exceed 5%.
- (38) (GRADE NOT CURRENTLY IN USE)**

CODE ITEM

- (39) MANIFOLD COLORED LEDGER (MCL)**
Consists of sheets, shavings, and cuttings of industrially-generated printed or unprinted colored or white groundwood-free paper. All stock must be uncoated and free of nonimpact printing. A percentage of carbonless paper is allowable.
Prohibitive Materials may not exceed 1/2 of 1%.
Outthrows plus prohibitives may not exceed 2%.
- (40) SORTED WHITE LEDGER (SWL)**
Consists of uncoated, printed or unprinted sheets, shavings, guillotined books, and cuttings of white groundwood-free ledger, bond, writing, and other paper which has similar fiber and filler content.
Prohibitive Materials may not exceed 1/2 of 1%.
Outthrows plus prohibitives may not exceed 2%.
- (41) MANIFOLD WHITE LEDGER (MWL)**
Consists of sheets, shavings, and cuttings of industrially-generated printed or unprinted white groundwood-free paper. All stock must be uncoated.
Prohibitive Materials may not exceed 1/2 of 1%.
Outthrows plus prohibitives may not exceed 2%.
- (42) (GRADE NOT CURRENTLY IN USE)**
- (43) COATED BOOK STOCK (CBS)**
Consists of coated groundwood-free paper, printed or unprinted in sheets, shavings, guillotined books and cuttings. A reasonable percentage of paper containing fine groundwood may be included.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 2%.
- (44) COATED GROUNDWOOD SECTIONS (CGS)**
Consists of printed, coated groundwood paper in sheets, sections, shavings or guillotined books. This grade may not include news quality groundwood paper.
Prohibitive Materials: None permitted.
Outthrows plus prohibitives may not exceed 2%.
- (45) LIGHTLY PRINTED BLEACHED BOARD CUTTINGS**
Consists of groundwood-free printed bleached board cuttings, free from misprint sheets, cartons, wax, greaseproof lamination, metallic, and inks, adhesives or coatings that are insoluble.
Prohibitive Materials may not exceed 1/2 of 1%.
Outthrows plus prohibitives may not exceed 2%.
- (46) PRINTED BLEACHED BOARD**
Consists of groundwood-free misprint sheets, cartons and cuttings of bleached board, free from wax, greaseproof lamination, metallic, and inks, adhesives or coatings that are insoluble.
Prohibitive Materials may not exceed 1%.
Outthrows plus prohibitives may not exceed 2%.

CODE ITEM

(47) UNPRINTED BLEACHED BOARD

Consists of groundwood-free unprinted, untreated bleached board cuttings, sheets or rolls, free from wax, greaseproof lamination and adhesives or coatings that are insoluble.

Prohibitive Materials: None permitted.

Outthrows plus prohibitives may not exceed 1%.

(48) #1 BLEACHED CUP STOCK (#1 CUP)

Consists of untreated cuttings or sheets of coated or uncoated cup base stock. Cuttings with slight bleed may be included. Must be free of wax, poly, and other coatings that are insoluble.

Prohibitive Materials: None permitted.

Outthrows plus prohibitives may not exceed 1/2 of 1%.

(49) #2 PRINTED BLEACHED CUP STOCK (#2 CUP)

Consists of printed, untreated formed cups, cup die cuts, and misprint sheets of coated or uncoated cup base stock. Glues must be water soluble. Must be free of wax, poly, and other coatings that are insoluble.

Prohibitive Materials: None permitted.

Outthrows plus prohibitives may not exceed 1%.

(50) UNPRINTED BLEACHED PLATE STOCK

Consists of groundwood-free bleached coated or uncoated, untreated and unprinted plate cuttings and sheets.

Prohibitive Materials: None permitted.

Outthrows plus prohibitives may not exceed 1/2 of 1%.

(51) PRINTED BLEACHED PLATE STOCK

Consists of groundwood-free bleached coated or uncoated, untreated printed plates and sheets. Must be free of coatings or inks that are insoluble.

Prohibitive Materials: None permitted.

Outthrows plus prohibitives may not exceed 1%.

(52) ASEPTIC PACKAGING AND GABLE-TOP CARTONS

Consists of liquid packaging board containers including empty, used, polyethylene (PE)-coated, printed one-side aseptic and gable-top cartons containing no less than 70% bleached chemical fiber and may contain up to 6% aluminum foil and 24% PE film.

Prohibitive Materials may not exceed 2%.

Outthrows plus prohibitives may not exceed 5%.

(54) MIXED PAPER (MP)

Consists of all paper and paperboard of various qualities not limited to the type of fiber content, sorted and processed at a recycling facility.

Prohibitive Materials may not exceed 2%.

Outthrows may not exceed 3%.

CODE ITEM

(56) SORTED RESIDENTIAL PAPERS & NEWS (SRPN)

Consists of sorted newspapers, mail, magazines, printing and writing papers and other acceptable papers generated from residential programs (such as residential household and apartment collections and drop-off centers) sorted and processed at a recycling facility. Containerboard and brown grades (OCC, Kraft bags, boxboard and Kraft carrier board) will be considered as "Outthrows." Due to some technical questions, a clarification to the language above was made in August 2019.

Prohibitive Materials may not exceed 2%.

Outthrows may not exceed 3%.

(58) SORTED CLEAN NEWS (SCN)

Consists of sorted newspapers from source separated collection programs, converters, drop-off centers and paper drives containing the normal percentages of rotogravure, colored and coated sections. May contain inserts that would normally be included in the newspaper in the proper proportions. Grade must be free of excessive ink, brown grades and non-paper material. (Some mills may require pack to be free of flexographic inks.)

Prohibitive Materials may not exceed 1/2 of 1%.

Outthrows plus prohibitives may not exceed 1%.

Other papers may not exceed 10%

SPECIALTY GRADES

The grades listed below are produced and traded in carload and truckload quantities throughout the United States, and because of certain characteristics (i.e., the presence of wet strength, polycoatings, plastic, foil, carbon paper, hot melt glue), are not included in the regular grades of paper stock. However, it is recognized that many mills have special equipment and are able to utilize large quantities of these grades. Since many paper mills around the world do use these specialty grades, they are being listed with appropriate grade numbers for easy reference.

The Paper Stock Industries Chapter of ReMA is not establishing specific specifications, which would refer to such factors as the type of wet strength agent used, the percentage of wax, the amount of polycoating, whether it is on top of or under the printing, etc. The specification for each grade should be determined between Buyer and Seller, and it is recommended that purchase be made based on sample.

These specialty grades are as follows:

- 1—S White Waxed Cup Cuttings
- 2—S Printed Waxed Cup Cuttings
- 3—S Poly Coated Cup Stock
- 4—S Polycoated Bleached Kraft—Unprinted
- 5—S Polycoated Bleached Kraft—Printed
- 6—S Polycoated Milk Carton Stock
- 7—S Polycoated Diaper Stock
- 8—S Polycoated Boxboard Cuttings
- 9—S (This Grade No Longer in Use)
- 10—S Printed and/or Unprinted Bleached Sulphate Containing Foil
- 11—S Waxed Corrugated Cuttings
- 12—S Wet Strength Corrugated Cuttings
- 13—S (This Number Not Currently in Use)
- 14—S Beer Carton Scrap
- 15—S Contaminated Bag Scrap
- 16—S Insoluble Glued Free Sheet Paper and/or Board (IGS)
- 17—S White Wet Strength Scrap
- 18—S Brown Wet Strength Scrap
- 19—S Printed and/or Colored Wet Strength Scrap
- 20—S File Stock
- 21—S (This Number Not Currently in Use)
- 22—S Ruled White
- 23—S Flyleaf Shavings Containing Hot Melt Glue
- 24—S (This Number Not Currently in Use)
- 25—S Books with Covers
- 26—S (This Number Not Currently in Use)
- 27—S (This Number Not Currently in Use)
- 28—S (This Number Not Currently in Use)
- 29—S (This Number Not Currently in Use)
- 30—S Plastic Windowed Envelopes
- 31—S Textile Boxes
- 32—S Printed TMP
- 33—S Unprinted TMP
- 34—S Manila Tabulating Cards
- 35—S Sorted Colored Ledger
- 36—S Computer Printout (CPO)
- 37—S Silicone Release Liner

GLOSSARY OF PAPER STOCK TERMS

The following is a glossary of paper stock terms used within section VI, Grade Definitions, of the Guidelines for Paper Stock. These terms are not intended as a dictionary, but as a guide to help the Circular user better understand specific grade definitions as used in the recovered paper industry.

ADHESIVES: Bonding substances that are non-water soluble are considered contaminants in pulp subs, groundwood and deinking grades.

BEATER-DYED: Paper dyed or colored during the paper manufacturing process.

BLEACHED: Paper that has been whitened by chemicals.

BOARDS: Paperboard 0.006 inch or thicker.

BOGUS: Paper of inferior quality to a standard grade.

BOXBOARD: Paperboard made from a variety of recovered fibers having sufficient folding properties and thickness to be used to manufacture folding or set-up boxes.

CHEMICAL WOOD-FIBER PULP: Generic for cellulose fiber isolated and purified by a chemical digestive process.

CHIPBOARD: Uncoated, non-folding paperboard made from a variety of recovered papers, having sufficient strength and structural properties to be used to manufacture game boards, book covers, notebook backing and similar products.

COATINGS: A layer of adhesives, clays, varnish or any barrier applied to paper.

CONTAINERBOARD: Linerboard and corrugated medium used to manufacture shipping containers.

CORES: Paper tubes on which rolls of paper may be wound for shipment.

CORRUGATED CONTAINERS: Shipping containers made with kraft paper linerboard and corrugated medium.

CUTTINGS: Paper stock by-product of paper converting operations.

FILLER/FILLED: Denotes papers that have minerals (clays or other pigments) added for improving quality or color.

FLYLEAF/SHAVINGS: Trim scrap from printing operations.

FREESHEET: Paper that contains less than 10% groundwood fiber (synonym: groundwood-free).

GROUNDWOOD: Paper made with fibers produced without chemical pulping.

GILT: Metallic (gold or silver) inks used in printing.

HOGGED: Paper that has been mechanically torn or ripped to reduce its original size.

HOT-MELT: A type of glue or adhesive applied while hot/ warm. Considered a contaminant in some grades.

IMPACT (PRINTING): A paper printing process that physically applies ink to the paper surface.

INSOLUBLE GLUES: Glues that won't dissolve (break down) in water.

JUTE: Strong, long-fibered pulp made from hemp.

KRAFT: Paper made from sulfate pulp (synonyms: brown and strong).

LAMINATED: Paper manufactured by fusing one or more layers of paper together.

LINERBOARD: Outside layers of a combination board used to manufacture corrugated shipping containers.

MANIFOLD: May denote continuous forms or business forms with several parts (may be interleaved with carbon paper or be carbonless papers).

MEDIUM: The inner corrugated fluted material used to manufacture corrugated shipping containers.

NON-IMPACT: Papers having printing images formed without impact.

OFF-SHORE/ASIAN: Denotes corrugated shipping containers manufactured overseas and containing bogus liners or medium. (Color is somewhat lighter/more yellow than North American produced materials).

PAPERBOARD: Denotes paper products used for packaging (corrugated boxes, folding cartons, set-up boxes, etc.).

ROTOGRAVURE: A paper printing (intaglio) process typically used to create the highest quality of smoothness on coated and uncoated papers. Excess quantities are considered an outthrow in grades #7, #8, and #9.

SECTIONS: Unbound, unused printed material with full ink coverage.

SHAVINGS: Trim from converting and bindery operations.

SIGNATURES: A section of book obtained by folding a single sheet of printing paper.

SLABBED: Type of paper stock normally generated by cutting rolls.

SULFITE: Papers and boards made from pulps made from an acid process.

SULPHATE: Papers and boards made from alkaline processed pulps.

TEST LINER: Liners, which are the outer ply of any kind of paperboard, containing 100% recycled material.

TMP: Thermomechanical pulp.

TREATED: Paper manufactured with additives.

TRIM: Cuttings of paper stock generated at converting or bindery operations which normally have little or no printing.

ULTRA-VIOLET (UV) INKS/COATINGS: Papers having inks or coatings dried by utilizing an ultraviolet radiation method. Considered a contaminant in deinking grades.

WET STRENGTH: Papers that have been treated with a moisture-resistant chemical that inhibits pulping.

Guidelines for Plastic Scrap: P-2025

Baled Recycled Plastic Scrap Commercial Guidelines

GENERAL INFORMATION

Commercial Guidelines for Baled Recycled Plastic Scrap were developed to provide industry-wide quality standards. These standards will facilitate commodity trading of these materials. They will also focus suppliers of such material on the quality requirements of their customers.

Product

These guidelines are designed with the potential for dealing with all recycled plastic in bale form. Initial specifications refer only to bottles. The code framework allows for generation of guidelines for all types of plastic packaging materials (including rigids and flexibles) with room for expansion to other plastic products and resins including those which are used to produce durable goods. Guidelines for those products may be added at a later date.

Bale Density

Bales shall be compressed to a minimum density of 10 pounds per cubic foot and a maximum density to be determined by individual contract between Buyer and Seller. Increased density may improve transportation efficiency, but over-compression may adversely affect the ability of a Buyer to separate, sort, and reprocess the material.

Bale Tying Material

Bale wires, ties, or straps shall be made of non-rusting or corroding material.

Bale Integrity

Bale integrity must be maintained through loading, shipping, handling, and storage.

Allowable Contamination

Refer to each specification for allowable contamination levels. Unspecified materials must not exceed 2% of total bale weight. This can be changed if agreed upon in writing and signed by both the buyer and the seller.

Prohibited Material

Certain materials are understood to be specified as "prohibited." Such materials will render the bale "non-specification" and may cause some customers to reject the entire shipment. These may include plastic materials which have a deleterious effect on each other when reprocessed, and materials such as agricultural chemicals, hazardous materials, flammable liquids and/or their containers, and medical waste.

Liquids

Plastic containers/materials should be empty and dry when baled. The bale should be free of any free-flowing liquid of any type.

General

Shipments should be essentially free of dirt, mud, stones, grease, glass, and paper. The plastic must not have been damaged by ultraviolet exposure. Every effort should be made to store the material above ground and under cover. A good faith effort on the part of the supplier will be made to include only rinsed bottles which have closures removed.

DEFINITIONS FOR PLASTIC MATERIALS

Baled

Loose material that is compressed and bound together.

Densified

Material that is compressed through mechanical means. Typically applies to foam (purged) and film (turned into "popcorn"). Densified material is typically sent on for additional processing.

Durable Goods

Electrical and electronic equipment, appliances, automobiles (called "transportation equipment" in ISO 15270), construction products (included in ISO 15270) and industrial equipment (included in ISO 15270).

Flake

A generic term that refers to size and shape. Typically consists of plastic bottles or plastic film typically ground into a chip.

Installed

Material that has been purchased by a consumer and used for its original purpose. Such material may be scrap from the installation process. The material may have reached the end of its serviceable life and has been removed from service. In distribution center or worksite environments, the packaging has been opened and exposed to environmental conditions causing a higher likelihood of contamination. This material can also be categorized as "post-consumer."

Mixed Load Plastic

Shredded plastic that contains various types of resins and requires mechanical sorting to reach final specification. Typically baled and not granulated. Types and grades included in the bale to be agreed to by buyer and seller.

Plastic Bottle

A rigid container which is designed with a neck that is smaller than the body. Normally used to hold liquids and emptied by pouring.

Plastic Film

A thin flexible sheet which does not hold a particular shape when unsupported.

Postconsumer

Products generated by a business or consumer that have served their intended end use and have been separated or diverted from the solid waste stream for the purpose of recycling.

Purge

Plastic that has been melted and has hardened. This material has no set shape or form.

Recovered Plastic

Plastic materials which have been recovered or diverted from the solid waste stream. Does not include materials generated from and commonly reused within an original manufacturing process.

Recycled Plastic

Plastics composed of either post-consumer or recovered material or both.

Regrind

A generic term that refers to hard rigid plastic typically ground into a chip. Typically consists of material that is the same grade, color and type. It can be used in extrusion or molding processes.

Rigid Plastic Container

A package (formed or molded container) which maintains its shape when empty and unsupported.

Shred

Size reduced material. The typical upper size can be between 3" to 12", although in some cases the upper size can be as small as about 1". Size range, characteristics should be agreed to between buyer and seller.

Shredded Plastic

Generic term. Material that contains a high plastic content. Typically contains 90% plastic content.

Shredder Residue

The remaining mixture after the majority of metals have been recovered from durable goods "shred." The mixture can contain plastics, rubber, wood, glass, rocks, dirt, paper, film, textiles, wires and other metals missed during the metal recovery process. The predominant single material is often plastic, which can vary from about 15% to about 90% depending on the type of durable goods and the steps taken in the metal separation process. Size range, characteristics should be agreed to between buyer and seller.

Uninstalled

Can be found in multiple environments such as worksite, distribution centers or OEM facilities. The material has not been used due to a defect or other circumstance. It can be obsolete or surplus material. Material is that recovered from the distribution chain can also be categorized as "post-consumer." Material recovered before the distribution chain can be categorized as "pre-consumer."

Common issues for this category:

The following list applies to all materials listed in this category.

- Caps, enclosures, and labels are acceptable.
- Product need not be washed, but preferred.

PET Bottles (No PET Thermoforms)

DESCRIPTION: Any whole Polyethylene Terephthalate (PET, #1) postconsumer bottle or jar with a screw-neck top that contains the ASTM D7611 "#1, PET or PETE" resin identification code and that is clear, transparent green, or transparent light blue. All bottles should be free of contents or free flowing liquids. Closures (caps, lids, rings, and labels) may be left on bottles.

PRODUCT: Polyethylene Terephthalate Bottles

SOURCE: Post-consumer material collected primarily from residential sources, may also include some material that has met its intended use from commercial establishments.

PET Bale Grade	Grade A	Grade B	Grade C
Total PET bottle fraction by weight	94% or above	83–93%	73–82%

"PET fraction" refers to the total weight of PET bottles in a PET bale, inclusive of caps and labels when still attached to PET containers, as a percentage of the total weight of that bale.

There are 10 U.S. states with container deposit laws in place; all include a subset of PET containers. It is assumed that deposit bales will contain a high fraction of PET and that the grading scale above applies to all PET bales, including deposit. However, because the container mix, collection and aggregation process is defined through state statute, deposit bale specifications are not specifically addressed in this document.

CHECK WITH YOUR BUYER(S) as to their allowances for:

- Any other Color PET Containers (including fluorescents and opaques)

CONTAMINATION: Total contaminants should not exceed the percentages, by weight, as defined by PET bale grade chart above.

ALLOWABLE CONTAMINANTS AT LOW LEVELS: These contaminants are tolerable at low levels. The following contaminants should not exceed 2% by weight of any of the following "individual" contaminants, unless noted otherwise.

- HDPE (#2), LDPE (#4), PP (#5) rigid packaging
- Clear PET (#1) Thermoformed Plastic (e.g., clamshells, bakery trays, covers, deli containers, drink cups)
- Aluminum Cans
- Loose paper or cardboard (OCC)
- Liquid residues

CONTAMINANTS NOT ALLOWED: If present, these contaminants may result in rejection.

- PVC (#3) in any form
- Chemically incompatible low temperature melting materials, including PS (#6), PETG, and PLA, as rigid or foam in any product.
- Any #7 plastics, including polycarbonate bottles
- Any non-packaging products
- Any bulky rigid plastics
- Any plastic bags or plastic film
- Any plastic foam
- Any Item containing degradable additives

- Containers which held hazardous materials, such as flammable, corrosive, or reactive products, pesticides, or herbicides, including motor oil bottles
- Other metal, wood, glass
- Batteries
- Bio-medical waste items (e.g., syringes, sharps, gloves, masks)
- Rocks, stones, mud, oils and grease

GENERAL: Refer to the General Information section for additional information.

PET Bottles With Thermoforms

DESCRIPTION: Any whole Polyethylene Terephthalate (PET, #1) postconsumer bottle or jar with a screw-neck top that contains the ASTM D7611 “#1, PET or PETE” resin identification code and that is clear, transparent green, or transparent light blue. All bottles should be free of contents or free flowing liquids. Closures (caps, lids, rings, and labels) may be left on bottles. **This specification allows inclusion of PET thermoforms of more than two percent, but not to exceed 10 percent of bale, by weight. PET thermoforms are defined as any whole, extrusion grade, clear polyethylene terephthalate (PET) package labeled with the ASTM D7611 “#1, PET or PETE” resin identification code, including and not limited to egg cartons, baskets, clamshell containers, cups, lids, cake domes, covers, blister pack without paperboard backing, tubs, deli containers, trays and folded PET sheet containers. All thermoform pieces must be optically sorted (as PET).**

PRODUCT: Polyethylene Terephthalate Bottles with Thermoforms

SOURCE: Post-consumer material collected primarily from residential sources, may also include some material that has met its intended use from commercial establishments.

PET Bale Grade	Grade A	Grade B	Grade C
Total PET bottle fraction by weight	94% or above	83–93%	73–82%

“PET fraction” refers to the total weight of PET bottles in a PET bale, inclusive of caps and labels when still attached to PET containers, as a percentage of the total weight of that bale.

“CHECK WITH YOUR BUYER(S) as to their allowances for: fluorescents and opaques

CONTAMINATION: Total contaminants should not exceed the percentages, by weight, as defined by PET bale grade chart above.

ALLOWABLE CONTAMINANTS AT LOW LEVELS: These contaminants are tolerable at low levels. The following contaminants should not exceed 2% by weight of any of the following “individual” contaminants, unless noted otherwise.

- HDPE (#2), LDPE (#4), PP (#5) rigid packaging
- Aluminum cans
- Loose paper or cardboard (OCC)
- Liquid residues

CONTAMINANTS NOT ALLOWED: If present, these contaminants may result in rejection.

- PVC (#3) in any form
- Chemically incompatible low temperature melting materials, including PS (#6), PETG, and PLA, as rigid or foam in any product.
- Any #7 plastics, including polycarbonate bottles
- Any non-packaging products
- Any bulky rigid plastics
- Any plastic bags or plastic film
- Any plastic foam
- Any Item containing degradable additives
- Containers which held hazardous materials, such as flammable, corrosive, or reactive products, pesticides, or herbicides, including motor oil bottles
- Other metal, wood, glass
- Batteries
- Bio-medical waste items (e.g., syringes, sharps, gloves, masks)
- Rocks, stones, mud, oils and grease

GENERAL: Refer to the General Information section for additional information.

PET Thermoforms

DESCRIPTION: Any whole, extrusion grade, clear or transparent light blue polyethylene terephthalate (PET) postconsumer package labeled with the ASTM D7611 “#1, PET or PETE” resin identification code, not including bottles and jars, but including and not limited to egg cartons, baskets, clamshell containers, cups, lids, cake domes, covers, blister pack without paperboard backing, tubs, deli containers, trays and folded PET sheet containers. All packages should be free of contents or free flowing liquids. Closures (caps, lids, rings, and labels) may be included.

All thermoform pieces must be optically sorted (as PET), and no other thermoform shall come from any other sorting stations. (This is specified to prevent lookalike thermoform—PS, PLA, PVC—from being mixed with PET.)

PRODUCT: Polyethylene Terephthalate Thermoform Plastic

SOURCE: Post-consumer material collected primarily from residential sources, may also include some material that has met its intended use from commercial establishments.

“CHECK WITH YOUR BUYER(S) as to their allowances for: transparent green, or any other color (other than light blue).

CONTAMINATION: Total contaminants should not exceed 6% by weight.

ALLOWABLE CONTAMINANTS AT LOW LEVELS: These contaminants are tolerable at low levels. The following contaminants should not exceed 2% by weight of any of the following “individual” contaminants, unless noted otherwise.

- HDPE (#2), LDPE (#4), PP (#5) rigid packaging
- PS (#6) and Other (#7) rigid plastic, including PLA plastic
- Polyethylene Terephthalate Glycol (PETG)
- PVC (#3)—maximum 1%
- Aluminum cans
- Loose paper or cardboard (OCC)

- Liquid residues

CONTAMINANTS NOT ALLOWED: If present, these contaminants may result in rejection.

- Any non-packaging products
- Any bulky rigid plastics
- Any plastic bags or plastic film
- Any plastic foam
- Items containing degradable additives
- Containers which held hazardous materials, such as flammable, corrosive, or reactive products, pesticides, or herbicides, including motor oil bottles
- Other metal, wood, glass
- Batteries
- Bio-medical waste items (e.g., syringes, sharps, gloves, masks)
- Rocks, stones, mud, oils and grease

GENERAL: Refer to the General Information section for additional information.

HDPE Color Bottles & Select Containers

DESCRIPTION: Any high-density polyethylene (HDPE) blow-molded bottle or blow-molded jar/canister, containing the ASTM D7611 “#2, HDPE” resin identification code, as well as PE squeeze tube and HDPE rigid can and bottle carriers, all primarily pigmented and opaque, and generated from a curbside, dropoff, or other public or private recycling collection program. Bottles are blow-molded and defined as containers that have a neck or mouth that is smaller than the base. HDPE jars/canisters are blow-molded with a mouth similar dimension to the base (e.g. coffee or cleaning wipes containers). PE squeeze tubes are compatible containers with a rigid shoulder/closure and squeezable body pinched off at the other end. HDPE rigid can and bottle carriers are made from bottle grade HDPE.

All bottles, jars/canisters and tubes should be free of contents or free flowing liquids. While including closures (caps, lids, and rings) on bottles is acceptable, removal of closures is also acceptable. Loose caps and closures should not be added to the bale.

PRODUCT: Polyethylene Bottles, jars/canisters, and tubes

SOURCE: Post-consumer material collected primarily from residential sources, may also include some material that has met its intended use from commercial establishments.

CHECK WITH YOUR BUYER(S) as to their allowances for:

- HDPE motor oil or other automotive fluid bottles
- Non-bottle HDPE container/item using fractional melt HDPE resin:
 - HDPE Thermoforms

CONTAMINATION: Total contamination should not exceed 5% by weight.

ALLOWABLE CONTAMINANTS AT LOW LEVELS: These contaminants are tolerable at low levels. The following contaminants should not exceed 2% by weight of any of the following “individual” contaminants, unless noted otherwise.

- Injection molded HDPE (#2) containers (e.g., tubs, buckets)

- Any non-HDPE rigid plastic bottle, container, or packaging, including PET (#1), LDPE (#4), PP (#5), PS (#6), Other (#7) and compostable plastic (e.g., PLA and PHA) (2% maximum of all combined)
- Loose paper or cardboard (OCC)
- Liquid residues
- Aluminum cans

CONTAMINANTS NOT ALLOWED: If present, these contaminants may result in rejection.

- Any item with degradable additives
- Containers which held hazardous materials, such as flammable, corrosive, or reactive products, pesticides, or herbicides
- Any bulky rigid plastic
- Any plastic bags or film
- Any plastic foam
- Other metal, wood, glass
- Batteries
- Electronics scrap, including items with circuit boards or battery packs
- Bio-Medical non-bottle waste/items (e.g., syringes, sharps, gloves, masks)
- Rocks, stones, mud, oils, grease

GENERAL: Refer to the General Information section for additional information.

HDPE Natural Bottles

DESCRIPTION: Any whole, blow-molded, high-density polyethylene (HDPE) bottle containing the ASTM D7611 “#2, HDPE” resin identification code that is unpigmented, and was generated from a curbside, drop-off, or other public or private recycling collection program. Bottles are defined as containers that have a neck or mouth that is smaller than the base.

PRODUCT: Polyethylene Bottles

SOURCE: Post-consumer material collected primarily from residential sources, may also include some material that has met its intended use from commercial establishments.

All bottles should be free of contents or free flowing liquids. While including closures (caps, lids, and rings) on bottles is acceptable, removal of closures is also acceptable. Loose caps and closures should not be added to the bale.

Cooking oil in natural HDPE bottles should be sorted into the Color HDPE Bottle bale.

ITEMS RESULTING IN A DOWNGRADE TO COLOR HDPE BALE: Inclusion of the below items will downgrade a Natural Bottle Bale to a Color HDPE Bottle Bale.

- Pigmented white and yellow HDPE (#2) milk jugs
- Other pigmented HDPE (#2) bottles and containers

CONTAMINATION: Total contamination should not exceed 5% by weight.

ALLOWABLE CONTAMINANTS AT LOW LEVELS: These contaminants are tolerable at low levels. The following

contaminants should not exceed 2% by weight of any of the following "individual" contaminants, unless noted otherwise.

- Liquid residues
- Loose paper or cardboard (OCC)
- Aluminum cans
- Any other HDPE (#2) rigid plastic
- Any non-HDPE rigid plastic bottle, container, or packaging, including PET (#1), LDPE (#4), PP (#5), PS (#6), Other (#7) and compostable plastic (e.g., PLA and PHA) (2% maximum of all combined)

CONTAMINANTS NOT ALLOWED: If present, these contaminants may result in rejection.

- Any item with degradable additives
- Containers which held hazardous materials, such as flammable, corrosive, or reactive products, pesticides, or herbicides
- Any PVC (#3) rigid plastic bottle, container, or packaging
- Any bulky rigid plastic
- Any plastic bags or film
- Any plastic foam
- Other metal, wood, glass
- Batteries
- Electronics scrap, including items with circuit boards or battery packs
- Bio-Medical non-bottle waste/items (e.g., syringes, sharps, gloves, masks)
- Rocks, stones, mud, oils, grease

GENERAL: Refer to the General Information section for additional information

HDPE Injection Bulky Rigid Plastics

DESCRIPTION: Any injection grade high density polyethylene (#2 HDPE) rigid plastic, typically found to be wide mouthed containers and/or oversized items generated through a positive sort from curbside, drop-off or other public or private recycling collection program. Examples include carts, crates, buckets, baskets, or other large all injection HDPE items. Small injection molded containers are acceptable. Pallets or other injection molded large items from commercial sources can be included. Metal such as axels and bolts must be removed. Buckets/pails with metal handles and all HDPE plastic toys without metal rods, screws or containing batteries are acceptable.

Blow molded containers of any size should not be included (e.g., 55-gallon drums or 2 gl syrup containers).

PRODUCT: Buckets, Pails, Oversized Rigid Plastics

SOURCE: Post-Consumer Material collected primarily from residential sources, may also include some material that has met its intended use from commercial establishments.

CONTAMINATION: Total contamination should not exceed 5% by weight.

ALLOWABLE CONTAMINANTS AT LOW LEVELS: These contaminants are tolerable at low levels. The following contaminants should not exceed 2% by weight of any of the following "individual" contaminants, unless noted otherwise.

- Polypropylene rigid plastic (5% maximum)

- Any other non-HDPE rigid plastic, including PET (#1), PVC (#3), LDPE (#4), PS (#6), Other (#7) and compostable plastic (e.g., PLA and PHA) (4% maximum of all combined)
- Liquid or other residues
- Loose paper or cardboard (OCC)
- Aluminum cans

CONTAMINANTS NOT ALLOWED: If present, these contaminants may result in rejection.

- Any item with degradable additives
- Containers which held hazardous materials, such as flammable, corrosive, or reactive products, pesticides, or herbicide
- Any plastic bags or film
- Any plastic foam
- Other metal, wood, glass
- Batteries
- Electronics scrap, including items with circuit boards or battery packs
- Bio-Medical waste/items (e.g., syringes, sharps, gloves, masks)
- Rocks, stones, mud, oils, grease

PP Small Rigid Plastic

Description: Any polypropylene (PP) containers, packaging or products with the ASTM D7611 "#5, PP" resin identification code generated through a positive sort from curbside, drop-off or other public or private recycling collection program. Bottles, tubs, cups and other containers and packaging as well as non-container/packaging or products are accepted.

PRODUCT: Polypropylene Containers, Packaging and Products

SOURCE: Post-consumer Material collected primarily from residential sources, may also include some material that has met its intended use from commercial establishments.

CHECK WITH YOUR BUYER(S) as to their allowances for:

- Bulky PP items greater than 3 gallons equivalent size, (e.g., buckets, crates, waste bins, laundry baskets, large toys, and large storage bins). These items are accepted in the Mixed Rigid Bulky Bale.

CONTAMINATION: Total contamination should not exceed 15% by weight.

ALLOWABLE CONTAMINANTS AT LOW LEVELS: These contaminants are tolerable at low levels. The following contaminants should not exceed 2% by weight of any of the following "individual" contaminants, unless noted otherwise.

- High density polyethylene (#2) or low-density polyethylene (#4) rigid plastic (10%)
- PET (#1), PS (#6) rigid plastic (3% maximum of all combined)
- Any other non-PP rigid plastic, including Other (#7) and compostable plastic (e.g., PLA and PHA) (1%)
- Liquid or other residues
- Loose paper or cardboard (OCC)
- Aluminum cans

CONTAMINANTS NOT ALLOWED: If present, these contaminants may result in rejection.

- PVC (#3) in any form
- Any item with degradable additives
- Containers which held hazardous materials, such as flammable, corrosive or reactive products, pesticides or herbicide
- Any plastic bags or film
- Non-PP plastic foam
- Other metal, wood, glass
- Batteries
- Electronics scrap, including items with circuit boards or battery packs
- Bio-Medical waste/items (e.g., syringes, sharps, gloves, masks)
- Rocks, stones, mud, oils, grease

GENERAL: Refer to the General Information section for additional information.

Mixed Small Rigid Plastic

DESCRIPTION: Small rigid plastic items that are a mix of resins and generated in a positive sort from a curbside, drop-off, or other public or private recycling programs. Primary PP, PET and HDPE with some other resins. Items include bottles, non-bottle containers, other packaging and non-containers/packaging or products. PET and HDPE bottles are present to varying levels and are typically presorted out with some remaining. Items containing metal or electronics should be removed when possible.

PRODUCT: Small Bottle, Containers, Packaging and Products

SOURCE: Post-consumer Material collected primarily from residential sources, may also include some material that has met its intended use from commercial establishments.

CHECK WITH YOUR BUYER(S) as to their allowances for:

- Bulky rigid plastic items greater than 3 gallons equivalent size, (e.g., buckets, crates, waste bins, laundry baskets, large toys, large storage bins and lawn furniture). These items are accepted in the Mixed Rigid Bulky Bale

CONTAMINATION: Total contamination should not exceed 15% by weight.

ALLOWABLE CONTAMINANTS AT LOW LEVELS: These contaminants are tolerable at low levels. The following contaminants should not exceed 5% by weight of any of the following "individual" contaminants, unless noted otherwise.

- PS up to (10%)
- Rigid plastic of any other resin, not mentioned elsewhere in the specification
- Aluminum cans
- Liquid or other residues
- Loose paper or cardboard (OCC)

CONTAMINANTS NOT ALLOWED: If present, these contaminants may result in rejection. The following contaminants are not allowed at any level (zero percent allowed).

- Any PVC (#3) in any form
- Products with degradable additives
- Containers which held hazardous materials, such as flammable, corrosive or reactive products, pesticides or herbicide

- Any plastic bags or film
- Any plastic foam
- Other metal, wood, glass
- Batteries
- Electronics scrap, including items with circuit boards or battery packs
- Bio-Medical waste/items (e.g., syringes, sharps, gloves, masks)
- Rocks, stones, mud, oils, grease

GENERAL: Refer to the General Information section for additional information.

Mixed Bulky Rigid Plastic

DESCRIPTION: Any large rigid polypropylene (PP) high-density polyethylene (PE) and/or Low-Density Polyethylene (LDPE) plastic items that may have the ASTM D7611 resin identification codes #5 PP, #2 HDPE and/or #4 LDPE, generated through a positive sort from curbside, drop-off or other public or private recycling collection program. Examples include: buckets, crates, waste bins, laundry baskets, large toys, large storage bins, and lawn furniture or other large PP/HDPE items. Buckets/pails with metal handles are accepted. Small injection molded HDPE containers may be included. PP small items can also be included but are encouraged to be put in a PP Small Rigid bale.

PRODUCT: Bulky Rigid Plastic

SOURCE: Post-Consumer material collected primarily from residential sources, may also include some material that has met its intended use from commercial establishments.

CHECK WITH YOUR BUYER(S) as to their allowances for:

- Regarding inclusion of plastic items with metal such as axels and bolts and toys with electronic components and screws

CONTAMINATION: Total contamination should not exceed 15% by weight.

ALLOWABLE CONTAMINANTS AT LOW LEVELS: These contaminants are tolerable at low levels. The following contaminants should not exceed 2% by weight of any of the following "individual" contaminants, unless noted otherwise.

- HDPE bottles, canisters, or other blow molded containers.
- Any other non-PP or Non-HDPE rigid plastic (large or small) including PET (#1), PS (#6), Other (#7) and compostable plastic (e.g., PLA and PHA) (4% maximum of all combined)
- Liquid or other residues
- Loose paper or cardboard (OCC)
- Any plastic bags or film
- Metal, wood, glass

CONTAMINANTS NOT ALLOWED: If present, these contaminants may result in rejection.

- PVC (#3) in any form, including vinyl siding and white PVC pipe
- Coolers of any type
- Baby/child car seats
- Drums (e.g., 55gl HMW drum)
- Polycarbonate (PC) rigid plastic, including bottles

- Acrylonitrile butadiene styrene (ABS) rigid plastic, e.g. (computer housing)
- Any item with degradable additives
- Containers which held hazardous materials, such as flammable, corrosive or reactive products, pesticides or herbicide
- Any plastic foam, particularly EPS (expanded polystyrene)
- Batteries
- Electronics scrap, including items with circuit boards or battery packs (e.g., toys, computer products)
- Bio-Medical waste/items (e.g., syringes, sharps, gloves, masks)
- Rocks, stones, mud, oils, grease

GENERAL: Refer to the General Information section for additional information.

PLASTIC FILM SCRAP SPECIFICATIONS

General Non-Source-Specific Categories

PE Clear Film (Grade A)

DESCRIPTION: Any mix of clear or natural polyethylene film, Low-Density Polyethylene (LDPE) or Linear Low-Density Polyethylene (LLDPE), totaling at least 95% clear or natural polyethylene film is accepted. Films may be coded with ASTM D7611 resin identification code “#4, LDPE/LLDPE.” Includes stretch wrap, shrink wrap, and clear, natural bags.

PRODUCT: Polyethylene film

SOURCE: Sorted film generated after meeting its intended use from commercial establishments.

CONTAMINATION: Total contaminants should not exceed 5% by weight.

ALLOWABLE CONTAMINANTS AT LOW LEVELS: These contaminants are tolerable at low levels. The following contaminants should not exceed 1% by weight of any of the following “individual” contaminants, unless noted otherwise.

- Clear/natural HDPE (#2) film
- Lightly labeled (no more than 2 or 3 labels on each piece of film) or lightly printed film (less than 5% of surface covered in ink)
- Plastic Strapping and rubber bands
- Cardboard endcaps
- Moisture residues (2% maximum)

CONTAMINANTS NOT ALLOWED: If present, these contaminants may result in rejection.

- Heavily labeled or printed film
- Colored and heavily printed polyethylene films
- Any non-PE films, metallized films, or multi-material pouches
- PE film packaging exposed to hazardous materials, such as flammable, corrosive or reactive products, pesticides or herbicides
- Silicone coated film
- Film with oxo or bio-degradable additives, PVDC layers, or acrylic coatings

- Any rigid plastic bottle, container or packaging including PET (#1), HDPE (#2), PVC (#3), LDPE/LLDPE (#4), PP (#5), PS (#6), Other (#7) and compostable plastic (e.g., PLA and PHA)
- Any bulky rigid plastic
- Any plastic foam
- Food waste
- Free-flowing liquids
- Loose paper, cardboard (OCC)
- Textiles
- Metal, Wood, Glass
- Batteries
- Electronics scrap, including items with circuit boards or battery packs
- Bio-Medical waste/items (e.g., syringes, sharps, gloves, masks)
- Rocks, stones, mud, oils, grease

GENERAL: Refer to the General Information section for additional information.

PE Clear Film (Grade B)

DESCRIPTION: Any mix of polyethylene film, Low-Density Polyethylene (LDPE) or Linear Low-Density Polyethylene (LLDPE), totaling at least 80% clear or natural polyethylene film is acceptable. Films may be coded with ASTM D7611 resin identification code “#4, LDPE/LLDPE.” Up to 20% by weight of color and printed polyethylene film is acceptable.

PRODUCT: Polyethylene film

SOURCE: Sorted film generated after meeting its intended use from commercial establishments.

CONTAMINATION: Total contaminants should not exceed 10% by weight.

ALLOWABLE CONTAMINANTS AT LOW LEVELS: These contaminants are tolerable at low levels. The following contaminants should not exceed 2% by weight of any of the following “individual” contaminants, unless noted otherwise.

- HDPE (#2) film (10% allowable)
- Lightly labeled (no more than 2 or 3 labels on each piece of film) or lightly printed film (less than 5% of surface covered in ink)
- Plastic Strapping and rubber bands
- Rigid or foam PE (HDPE #2 or LDPE #4)
- Loose paper cardboard (OCC) including cardboard endcaps
- Moisture residues

CONTAMINANTS NOT ALLOWED: If present, these contaminants may result in rejection.

- Heavily labeled or printed film
- Any non-PE films, metallized films, or multi-material pouches
- PE film packaging exposed to hazardous materials, such as flammable, corrosive or reactive products, pesticides or herbicides
- Silicone coated film

- Film with oxo or bio-degradable additives, PVDC layers, or acrylic coatings
- Any rigid plastic bottle, container or packaging including PET (#1), HDPE (#2), PVC (#3), PS (#6), Other (#7) and compostable plastic (e.g., PLA and PHA)
- Any bulky rigid plastic
- Any non-PE plastic foam
- Food waste
- Free-flowing liquids
- Textiles
- Metal, Wood, Glass
- Batteries
- Electronics scrap, including items with circuit boards or battery packs
- Bio-Medical waste/items (e.g., syringe, sharps, gloves, masks)
- Rocks, stones, mud, oils, grease

GENERAL: Refer to the General Information section for additional information.

PE Film (Grade C)

Description: Any mix of clear/natural, color or printed polyethylene film, Low-Density Polyethylene (LDPE), Linear Low-Density Polyethylene (LLDPE), and/or High-Density Polyethylene (HDPE). Films may be coded with ASTM D7611 resin identification code “#4, LDPE/ LLDPE or #2 HDPE”. There is a wide variability of what is sold under this specification, which could include a high level of contamination. Buyers and sellers should be very explicit about their requirements and offerings.

GENERAL: Refer to the General Information section for additional information.

PE Color Film

DESCRIPTION: Any mixture of mixed color, clear/natural and printed Low-Density Polyethylene (LDPE) and Linear Low-Density Polyethylene (LLDPE) film with limited label contamination is acceptable. More than 20% by weight is expected to be color film. Films may be coded with ASTM D7611 resin identification code “#4, LDPE/LLDPE.”

PRODUCT: Color Polyethylene film

SOURCE: Sorted film generated after meeting its intended use from commercial establishments.

CONTAMINATION: Total contaminants should not exceed 5% by weight.

ALLOWABLE CONTAMINANTS AT LOW LEVELS: These contaminants are tolerable at low levels. The following contaminants should not exceed 2% by weight of any of the following “individual” contaminants, unless noted otherwise.

- HDPE (#2) film (5% allowable)
- Lightly labeled film (no more than 2 or 3 labels on each piece film)
- Plastic Strapping and rubber bands
- Cardboard endcaps
- Moisture residues

CONTAMINANTS NOT ALLOWED: If present, these contaminants may result in rejection.

- Heavily labeled film
- Any non-PE films, metallized films, or multi-material pouches
- PE film packaging exposed to hazardous materials, such as flammable, corrosive or reactive products, pesticides or herbicides
- Silicone coated film
- Film with oxo or bio-degradable additives, PVDC layers, or acrylic coatings
- Any rigid plastic bottle, container or packaging including PET (#1), HDPE (#2), PVC (#3), PP (#5), PS (#6), Other (#7) and compostable plastic (e.g., PLA and PHA)
- Any bulky rigid plastic
- Any non-PE plastic foam
- Food waste
- Free-flowing liquids
- Loose paper, cardboard (OCC)
- Textiles
- Metal, Wood, Glass
- Batteries
- Electronics scrap, including items with circuit boards or battery packs
- Bio-Medical waste/items (e.g., syringe, sharps, gloves, masks)
- Rocks, stones, mud, oils, grease

GENERAL: Refer to the General Information section for additional information.

Categories of Film from Specific Sources

PE Retail Mix Film

DESCRIPTION: Polyethylene stretch wrap, shrink wrap or other film generated by retailers back-of-house, and any polyethylene bag and overwrap accepted by retailers from their customers may be included.

Bags, wraps and film may be mixed color or printed and are a mix of High-Density Polyethylene (HDPE), Low-Density polyethylene (LDPE) and Linear Low-Density Polyethylene (LLDPE) films. Films may be coded with ASTM D7611 resin identification code “#2, HDPE” and “#4, LDPE/LLDPE.”

PRODUCT: Mixed PE Film

SOURCE: Post-consumer material collected from a mix of post-commercial and residential post-consumer sources.

CONTAMINATION: Total contaminants should not exceed 10% by weight.

ALLOWABLE CONTAMINANTS AT LOW LEVELS: These contaminants are tolerable at low levels. The following contaminants should not exceed 2% by weight of any of the following “individual” contaminants, unless noted otherwise.

- Any non-PE films, metallized, or multi-material pouches
- Loose paper, cardboard (OCC), including cardboard endcaps
- Plastic strapping and rubber bands
- Moisture residues

- Any rigid plastic bottle, container or packaging including PET (#1), HDPE (#2), PVC (#3), LDPE/LLDPE (#4), PP (#5), PS (#6), Other (#7) and compostable plastic (e.g. PLA and PHA)
- Hangers
- Cleaning wipes
- Twine or tape

CONTAMINANTS NOT ALLOWED: If present, these contaminants may result in rejection.

- PE films packaging or exposed to hazardous materials, such as flammable, corrosive or reactive products, pesticides or herbicides
- Silicone coated film
- Film with oxo or bio-degradable additives, PVDC layers, or acrylic coatings
- Any bulky rigid plastic
- Any plastic foam
- Food waste
- Free-flowing liquids
- Textiles
- Metal, Wood, Glass
- Batteries
- Electronics scrap, including items with circuit boards or battery packs
- Bio-Medical waste/items (e.g., syringe, sharps, gloves, masks)
- Rocks, stones, mud, oils, grease

GENERAL: Refer to the General Information section for additional information.

PE Furniture Mix Film

DESCRIPTION: Any mixture of natural Low-Density Polyethylene (LDPE) film used for sofa overwrap, bubble wrap, mattress bags, and Linear Low-Density Polyethylene (LLDPE) stretch film and polyethylene thin foam, which is white and gray foam backed with LDPE film. Color contribution can be only from the white foam, gray foam backed with LDPE film, and blue mattress bags. The mass shall consist of 70% to 80% LDPE and/ or LLDPE films and the remaining 20-30%, polyethylene foam. Films may be coded with ASTM D7611 resin identification code “#4, LDPE/LLDPE.”

PRODUCT: LDPE or LLDPE Film and Foam

SOURCE: Sorted Film and foam generated after meeting its intended use from commercial establishments

CONTAMINATION: Total contaminants should not exceed 10% by weight.

ALLOWABLE CONTAMINANTS AT LOW LEVELS: These contaminants are tolerable at low levels. The following contaminants should not exceed 5% by weight of any of the following “individual” contaminants, unless noted otherwise.

- Non-polyethylene other plastics such as non-woven PP, EPS, TPU
- HDPE (#2) film
- Lightly labeled (no more than 2 or 3 labels on each piece film) or lightly printed film (less than 5% of surface covered in ink)

- Loose paper, cardboard (OCC), including cardboard endcaps
- Moisture residues (2% maximum)
- Wood
- Miscellaneous small metal such as screws

CONTAMINANTS NOT ALLOWED: If present, these contaminants may result in rejection.

- Heavily labeled or printed film
- Any non-PE films, metallized, or multi-material pouches
- PE film packaging exposed to hazardous materials, such as flammable, corrosive or reactive products, pesticides or herbicides
- Silicone coated film
- Film with oxo or bio-degradable additives, PVDC layers, or acrylic coatings
- Any rigid plastic bottle, container or packaging including PET (#1), HDPE (#2), PVC (#3), LDPE/LLDPE (#4), PP (#5), PS (#6), Other (#7) and compostable plastic (e.g. PLA and PHA)
- Desiccant pouches
- Any bulky rigid plastic
- Food waste
- Free-flowing liquids
- Textiles
- Metal, Glass
- Batteries
- Electronics scrap, including items with circuit boards or battery packs
- Bio-Medical waste/items (e.g. syringe, sharps, gloves, masks)
- Rocks, stones, mud, oils, grease

GENERAL: Refer to the General Information section for additional information.

PE Agricultural Film (Grade A)

Any mixture of High-Density Polyethylene (HDPE), Low-Density Polyethylene (LDPE) and Linear Low-Density Polyethylene (LLDPE) film that has not been used on the ground for agriculture or farming and that has limited soil or vegetation contact is acceptable. Examples are greenhouse film and hoophouse film. Films may be coded with ASTM D7611 resin identification code “#2, HDPE” or “#4, LDPE/LLDPE.”

PRODUCT: PE Film

SOURCE: PE film from agricultural sources

CONTAMINATION: Total contamination should not exceed 20% by weight.

ALLOWABLE CONTAMINANTS AT LOW LEVELS: These contaminants are tolerable at low levels. The following contaminants should not exceed 5% by weight of any of the following “individual” contaminants, unless noted otherwise.

- PE film used on the ground for agriculture or farming
- Moisture residues
- Wood
- Paper or cardboard (OCC)

- Any rigid plastic bottle, container or packaging including PET (#1), HDPE (#2), PVC (#3), LDPE/LLDPE (#4), PP (#5), PS (#6), Other (#7) and compostable plastic (e.g. PLA and PHA)
- Plastic Strapping and rubber bands
- Rocks, stones, mud, dirt

CONTAMINANTS NOT ALLOWED: If present, these contaminants may result in rejection.

- Any non-PE films, metallized films, or multi-material pouches
- PE film packaging exposed to hazardous materials, battery packs such as flammable, corrosive, or reactive products, pesticides or herbicides
- Silicone coated film
- Film with oxo or bio-degradable additives, PVDC layers, or acrylic coatings
- Any bulky rigid plastic
- Any plastic foam
- Food waste
- Free-flowing liquids
- Textiles
- Metal, Glass
- Batteries
- Electronics scrap, including items with circuit boards or battery packs
- Bio-Medical waste/items (e.g., syringe, sharps, gloves, masks)
- Oils and Grease

GENERAL: Refer to the General Information section for more information.

PE Agricultural Film (Grade B)

Any mixture of High-Density Polyethylene (HDPE), Low-Density Polyethylene (LDPE) and Linear Low-Density Polyethylene (LLDPE) film collected after in-field agricultural use is acceptable.

Examples include mulch film, silage film, irrigation (drip) tubing, drip tape, dairy bags, almond film, vine/grape film and bunker silo film. Films may be coded with ASTM D7611 resin identification code “#2, HDPE” or “#4, LDPE/LLDPE.”

PRODUCT: PE Film

SOURCE: PE film from agricultural sources

CONTAMINATION: Total contamination should not exceed 50% by weight.

ALLOWABLE CONTAMINANTS AT LOW LEVELS: These contaminants are tolerable at low levels. The following contaminants should not exceed 5% by weight of any of the following “individual” contaminants, unless noted otherwise.

- Any non-PE films, metallized, or multi-material pouches
- Moisture residues
- Wood
- Paper or cardboard (OCC)
- Any rigid plastic bottle, container or packaging including PET (#1), HDPE (#2), PVC (#3), LDPE/LLDPE (#4), PP (#5), PS (#6), Other (#7) and compostable plastic (e.g. PLA and PHA)
- Plastic Strapping and rubber bands
- Rocks, stones, mud, dirt

CONTAMINANTS NOT ALLOWED: If present, these contaminants may result in rejection.

- PE film packaging exposed to hazardous materials, such as flammable, corrosive or reactive products, pesticides or herbicides
- Silicone coated film
- Film with oxo or bio-degradable additives, PVDC layers, or acrylic coatings
- Any bulky rigid plastic
- Any plastic foam
- Food waste
- Free-flowing liquids
- Textiles
- Metal, Glass
- Batteries
- Electronics scrap, including items with circuit boards or
- Bio-Medical waste/items (e.g., syringe, sharps, gloves, masks)
- Oils and Grease

GENERAL: Refer to the General Information section for more information.

PE MRF Film

Description: Mix of polyethylene bag and overwrap collected from consumers and businesses and sorted at Material Recovery Facilities (MRF), often collected through curbside collection.

Bags, wraps, and films may be mixed color or printed and are a mix of High-Density

Polyethylene (HDPE), Low-Density Polyethylene (LDPE) and Linear Low-Density Polyethylene (LLDPE). Films may be coded with ASTM D7611 resin identification code “#2, HDPE” and “#4, LDPE/LLDPE.”

PRODUCT: PE Film

SOURCE: Residential post-consumer film collected at Material Recovery Facilities.

CONTAMINATION: Total contamination should not exceed 35% by weight.

ALLOWABLE CONTAMINANTS AT LOW LEVELS: These contaminants are tolerable at low levels. The following contaminants should not exceed 5% by weight of any of the following “individual” contaminants, unless noted otherwise.

- Non-PE films, metallized, or multi-material pouches (2% maximum)
- Organic/food waste (1% maximum)
- Loose paper, cardboard (OCC), including cardboard endcaps
- Any rigid plastic bottle, container or packaging including PET (#1), HDPE (#2), PVC (#3), LDPE/LLDPE (#4), PP (#5), PS (#6), Other (#7) and compostable plastic (e.g. PLA and PHA)
- Plastic strapping and rubber bands
- Labels
- Aluminum cans

CONTAMINANTS NOT ALLOWED: If present, these contaminants may result in rejection.

- PE film packaging exposed to hazardous materials, such as flammable, corrosive or reactive products, pesticides or herbicides
- Silicone coated film
- Film with oxo or bio-degradable additives, PVDC layers, or acrylic coatings
- Any bulky rigid plastic
- Any plastic foam
- Free-flowing liquids
- Textiles
- Metal, Wood, Glass
- Batteries
- Electronics scrap, including items with circuit boards or battery packs
- Bio-Medical waste/items (e.g., syringe, sharps, gloves, masks)
- Rocks, stones, mud, oils, grease

GENERAL: Refer to the General Information section for more information.

Specialty PE Film Grades

Some specialty grades are regularly traded and use the following names. This list is not comprehensive.

- PE Garment Bag Film
- PE Banana Film
- PE Mulch Bag Film
- PE Cotton Wrap Film
- PE Tire Wrap Film

Rigid PVC—Siding

DESCRIPTION: Typically consists of PVC siding used in residential applications. May contain PVC downspouts. Not all siding is PVC and may contain PE variants, which are typically molded. Recyclability increases with additional color segregation.

PRODUCT: PVC Bale

SOURCE: Installed or Uninstalled Material

TECHNICAL INFORMATION: Hardness Level > 65D.

Rigid PVC does not contain plasticizer and will typically measure above 65 on the Shore D scale.

EXPLANATION OF THE SHORE SCALE: Shore durometer measurement devices can be used to measure the indentation of a prescribed needle into the material. The test method conforms to ASTM D2240.

CONTAMINATION: Prohibitives—Material not accepted at any level, 0% allowed.

- a. PET plastic of any form
- b. Insulation
- c. Medical and hazardous waste
- d. Lead or cadmium stabilized rigid PVC materials,
- e. Materials containing asbestos fillers or reinforcement.
- f. Used household soil or waste plumbing lines with visible bioresidue. (May have debris and paper)
- g. CPVC—should be separated and marketed separately—typically includes pipe and molded fittings and runners;

Contamination material allowed at small percentages:

- a. Plastics other than PVC such as HDPE, LDPE, PP, PS
- b. Foamed PVC
- c. Liquids
- d. Paper & Cardboard
- e. Ferrous and Non-Ferrous Metals
- f. Rocks, Stones, Mud, Dirt
- g. Wood, Glass, Oils, Grease

GENERAL: Refer to the General Information section for additional information.

Rigid PVC—Pipe

DESCRIPTION: PVC pipe that is round in shape and can be green, white, blue, purple and grey in color.

Comes from installed and un-installed sources or scrap. Is mainly used in water plumbing applications. Care should be taken when compressing the bale as too much pressure will crush material and make identification and inspection difficult. Recyclability increases with additional color segregation.

PRODUCT: PVC Bale

SOURCE: Installed or Uninstalled Material

TECHNICAL INFORMATION: Hardness Level > 65D.

Rigid PVC does not contain plasticizer and will typically measure above 65 on the Shore D scale.

EXPLANATION OF THE SHORE SCALE: Shore durometer measurement devices can be used to measure the indentation of a prescribed needle into the material.

The test method conforms to ASTM D2240.

CONTAMINATION: Prohibitives—material not accepted at any level, 0% allowed.

- a. CPVC (typically gray electrical conduit)
- b. PET plastic of any form
- c. Medical and hazardous waste
- d. Lead or cadmium stabilized rigid PVC materials,
- e. Materials containing asbestos fillers or reinforcement.
- f. Used household soil or waste plumbing lines with visible bioresidue. (May have debris and paper)
- g. ABS

Contamination material allowed at small percentages:

- a. Plastics other than PVC such as HDPE, LDPE, PP, PS
- b. Foamed PVC
- c. Liquids
- d. Paper & Cardboard
- e. Ferrous and Non-Ferrous Metals
- f. Rocks, Stones, Mud, Dirt
- g. Wood, Glass, Oils, Grease

GENERAL: Refer to the General Information section for additional information.

Rigid PVC—Window Profiles

DESCRIPTIONS: Typically consists of window and door frames. Sourced primarily from door and window manufacturers.

PRODUCT: PVC Bale

SOURCE: Installed or Uninstalled Material

TECHNICAL INFORMATION: Hardness Level > 65D. Rigid PVC does not contain plasticizer and will typically measure above 65 on the Shore D scale.

Explanation of the Shore Scale: Shore durometer measurement devices can be used to measure the indentation of a prescribed needle into the material. The test method conforms to ASTM D2240.

CONTAMINATION: Prohibitives—material not accepted at any level, 0% allowed.

- a. Loose rubber weather stripping
- b. Glass
- c. Metal
- d. PET plastic of any form
- e. Medical and hazardous waste
- f. Lead or cadmium stabilized rigid PVC materials,
- g. Materials containing asbestos fillers or reinforcement.
- h. Used household soil or waste plumbing lines with visible bioresidue. (May have debris and paper)
- i. CPVC—should be separated and marketed separately—typically includes pipe and molded fittings and runners;

Contamination material allowed at small percentages:

- a. Plastics other than PVC such as HDPE, LDPE, PP, PS
- b. Foamed PVC
- c. Liquids
- d. Paper & Cardboard
- e. Ferrous and Non-Ferrous Metals
- f. Rocks, Stones, Mud, Dirt
- g. Wood, Glass, Oils, Grease

GENERAL: Refer to the General Information section for additional information.

Flexible PVC

DESCRIPTION: Typically consists of molding, weather stripping, flexible tubing, purging, battery covers, medical tubing, auto decals, flexible films and sheeting. It is typically resistant to chemicals, non-porous and extruded. It can be found in long profiles and can be wound onto a reel.

PRODUCT: PVC Bale

SOURCE: Post-Consumer or Post Industrial (including Pre-consumer)

TECHNICAL INFORMATION: Durometer Level less than 90A

Explanation of the Durometer Scale: Explanation of the Shore Scale: Shore durometer measurement devices can be used to measure the indentation of a prescribed needle into the material. The test method conforms to ASTM D2240. Flexible PVC is typically measured using the A scale.

CONTAMINATION: Prohibitives—material not accepted at any level, 0% allowed.

- a. PET plastic of any form
- b. Medical and hazardous waste

- c. Contamination material allowed at small percentages
- d. Plastics other than PVC such as HDPE, LDPE, PP, PS
- e. Rigid PVC
- f. Liquids
- g. Paper & Cardboard
- h. Ferrous and Non-Ferrous Metals
- i. Glue, adhesives, sticky tape
- j. Co-extruded materials
- k. Reinforcement weaves and fabrics

GENERAL: Refer to the General Information section for additional information.

Guidelines for Electronics Scrap: ES-2023

Electronics Scrap

GENERAL INFORMATION

Commercial Guidelines for Electronics Scrap were developed to provide industry-wide quality standards. These standards will facilitate commodity transactions domestically and internationally. Transactions covering shipments to or from other countries may be in accordance with these standards and may be modified by mutual agreement between Buyer and Seller.

ELECTRONIC SCRAP DEFINITIONS

The following E-Recycling definitions will facilitate a more consistent language for both domestic as well as international transactions.

“End-Of-Life Electronic Products”

EOL Electronic Products are either obsolete for their intended purpose or no longer useful by the current user and lack any significant market value as an operational unit. These products are represented by any of the following categories of electronic products:

IT AND TELECOMMUNICATIONS ELECTRONIC EQUIPMENT INCLUDING:

- Centralized data processing:
 - Mainframes
 - Minicomputers
 - Printer units
- Personal computing:
 - Personal computers (CPU, mouse, screen and keyboard included)
 - Laptop computers (CPU, mouse, screen and keyboard included)
 - Notebook computers
 - Notepad computers
 - Printers
- Copying equipment
- Electrical and electronic typewriters
- Pocket and desk calculators
- Other products and equipment for the collection, storage, processing, presentation or communication of information by electronic means:
 - User terminals and systems
 - Facsimile
 - Telex
- Telephones
 - Pay telephones
 - Cordless telephones
 - Cellular telephones
 - Answering systems

- Other products or equipment for transmitting sound, images or other information by telecommunications

CONSUMER ELECTRONIC EQUIPMENT INCLUDING:

- Radio sets
- Television sets
- Video cameras
- Video recorders
- Eli-h recorders
- Audio amplifiers
- Musical instruments and other products or equipment for the purpose of recording or reproducing sound or images, including signals or other technologies for the distribution of sound and image by telecommunications

TOYS, LEISURE AND SPORTS ELECTRONIC EQUIPMENT INCLUDING:

- Electric trains or car racing sets
- Hand-held video game consoles
- Video games
- Computers for biking, diving, running, rowing, etc.
- Sports equipment with electric or electronic components
- Coin slot machines

MEDICAL DEVICES (EXCEPT ALL IMPLANTED AND INFECTED PRODUCTS AND RADIOACTIVE COMPONENTS) INCLUDING:

- Radiotherapy equipment
- Cardiology
- Dialysis
- Pulmonary ventilators
- Nuclear medicine
- Laboratory equipment or in-vitro diagnostics
- Analyzers
- Freezers
- Fertilization tests
- Other appliances for detecting, preventing, monitoring, treating, or alleviating illness, injury or disability

MONITORING AND CONTROL INSTRUMENTS INCLUDING:

- Smoke detectors
- Heating regulators
- Thermostats
- Measuring, weighing or adjusting appliances for household or as laboratory equipment
- Other monitoring and control instruments used in industrial installations (e.g. Irra control panels)

“E-Recycling”

E-Recycling is any process by which End-of-Life (EOL) electronic products which would otherwise become solid waste are collected, separated, reused or processed and returned to use in the form of raw materials or products.

“E-Demanufacturing”

Demanufacturing is the process of separating EOL electronic products (electronic materials) into metallic and nonmetallic parts that can be reused or recycled.

“E-Dismantler”

Dismantler is a person who engages in the manual demanufacturing of EOL electronic products (electronic materials) to reuse or recycle components and commodities contained within.

“E-Dismantling”

Dismantling is the manual demanufacturing of EOL electronic products (electronic materials) to reuse or recycle components and commodities contained within.

“E-Processor”

Processor is a person who engages in the mechanical demanufacturing of EOL electronic products (electronic materials) to reuse or recycle various commodities contained within.

“E-Processing”

Processing is the mechanical demanufacturing of EOL electronic products (electronic materials) to recover various commodities contained within.

“E-Broker”

Broker is a person who engages in the buying, selling, and trading of electronic products (electronic materials) without demanufacturing.

“E-Brokering”

Brokering is the buying, selling, and trading of electronic products (electronic materials) without demanufacturing.

ELECTRONICS SCRAP METALS—EM

Preface: The following metals specifications are directed to processing plants generating value-added commodities for consumers producing metal products. All the specifications below are subject to final terms and conditions as agreed between buyer and seller.

EM1—Eddy-Current (EC) Aluminum

Shall consist of the shredded aluminum fraction generated by EC separation of electronic products being predominately aluminum. Bulk density to be a minimum of 30 pounds per cubic foot (subject to terms between buyer and seller). Material may contain agreed-upon amounts of zinc and copper but shall not contain more than a total 5% maximum of nonmetallics, of which no more than 1% shall be rubber and plastics. To be free of excessively oxidized material and any sealed or pressurized items. Any variation to be sold by special arrangement between buyer and seller. Note: Refer to ISRI nonferrous specifications for Tweak or Twitch.

EM2—Eddy-Current (EC) Scrap

Shall consist of a combination of nonferrous metals that should be predominately aluminum but may contain statistically significant percentages of zinc or other nonferrous metals. Bulk density to be a minimum of 30 pounds per cubic foot and subject to terms between buyer and seller. Material to be bought/sold under this guideline shall be identified as EM2 with a number to follow indicating the estimated percentage of nonferrous metal (e.g., EM2-90 means the material contains approximately 90% nonferrous metal content). May also be screened to permit description by specific size ranges. Note: Refer to ReMA's ISRI nonferrous specification for Zorba.

Note: Specifications for clean aluminum scrap produced by demanufacturing or pretreating EOL scrap prior to shredding can be found under REMA's ISRI Guidelines for Nonferrous Scrap. For aluminum streams that contain less than 85% aluminum, consult the general aluminum scrap specifications.

EM3—Circuitboards and Shredded Circuitboards from the Processing of End-of-Life Electronics

Shall consist of whole or shredded copper/precious metal-bearing populated or unpopulated circuitboards from the manual dismantling of electronic products. May also consist of shredded circuitboards from end-of-life electronic product processing systems with a maximum piece size of 2 inches. Maximum acceptable metal contamination: aluminum, 5%; ferrous, 2%; zinc, 2%; magnesium, 1%; and beryllium, 200 ppm. Other elements subject to agreement between buyer and seller. Maximum plastic content: 40%. Typically sold on an assay basis and classified into different categories denominated by the gold levels contained in the material. Major classifications are:

- 1) <50 grams per mt
- 2) <200 g/mt
- 3) >200 g/m

EM4—Light Iron

Shall consist of whole No. 1 and whole No. 2 wrought iron and/or steel scrap and No. 1 busheling from the manual dismantling of electronic products. Refer also to 200, 204, and 207 Guidelines for Ferrous Scrap.

EM5—Iron Frag

Shall consist of shredded No. 1 and No. 2 whole wrought iron and/or steel scrap and No. 1 busheling from end-of-life electronic product processing systems. Refer also to 210 and 211 Guidelines for Ferrous Scrap.

ELECTRONICS SCRAP GLASS AND CRT CULLET SPECIFICATIONS

SHIPPING/PACKAGING/LABELING—All shipments shall be packaged, labeled, and transported in accordance with all applicable transportation laws and packed in a manner that prevents releases to the environment and protects the health and safety of workers handling the material at generating or receiving facilities.

WHOLE MONITORS/TVS WITH OR WITH CORDS. The equipment is intact with housing. Minimal to no disassembly has occurred.

WHOLE INTACT TUBES with gun and vacuum intact or released and with or without the band.

WHOLE TUBES without gun and with or without the band.

PROCESSED TUBES to include both funnel and panel glass. Particle size will be determined by contract between shipper and smelter or treatment facility. Material should be free of all loose metals, bands, and shadow masks. May or may not be cleaned prior to shipping.

LEADED FUNNEL GLASS AND FRIT for smelting or other recovery/treatment. This material may include up to 10% panel glass. May or may not be cleaned prior to shipment. Particle size

will be determined by contract between shipper and smelter or treatment facility.

PANEL GLASS (minimal or lead free) for multiple uses including construction, sand blasting, art glass, etc. May or may not be cleaned prior to shipment. Particle size will be determined by contract between shipper and receiving facility.

CLEAN PANEL GLASS with metal oxide concentrations of less than 5 ppm, free of coatings.

ELECTRONICS SCRAP PLASTICS

APPLICABLE TO ALL SPECS:

- All specifications are subject to final terms and conditions as agreed to between the buyer and the seller
- Plastic should not contain hazardous materials, medical waste or free-flowing liquid
- Contamination includes: painted/coated; laminated; metals; dirt; and wood

Baled Specs:

BALED CRT TV PLASTIC

- From disassembled CRT TVs
- 36,000 +/- pounds per 40 ft. HC or tractor trailer
- Maximum Contamination < or = 2.0% by weight

BALED LIGHT COLORED CRT MONITOR PLASTIC

- From disassembled light colored (white, beige) CRT computer monitors
- 36,000 +/- pounds per 40 ft. HC or tractor trailer
- Maximum Contamination < or = 2.0% by weight

BALED DARK COLORED CRT MONITOR PLASTIC

- From disassembled dark (black, dark grey) colored CRT monitors
- 36,000 +/- pounds per 40 ft. HC or tractor trailer
- Maximum Contamination < or = 2.0% by weight

BALED DARK COLORED FLAT PANEL MONITOR PLASTIC

- From disassembled dark (black, dark grey) colored LED and LCD monitors
- 36,000 +/- pounds per 40 ft. HC or tractor trailer
- Maximum Contamination < or = 2.0% by weight

BALED DARK COLORED PRINTER PLASTIC

- From disassembled dark (black, dark grey) colored printers
- 36,000 +/- pounds per 40 ft. HC or tractor trailer
- Maximum Contamination < or = 2.0% by weight

BALED LIGHT COLORED PRINTER PLASTIC

- From disassembled light (white, beige) colored printers
- 36,000 +/- pounds per 40 ft. HC or tractor trailer
- Maximum Contamination < or = 2.0% by weight

BALED DARK COLORED MIXED ELECTRONICS PLASTIC

- From disassembled dark (black, dark grey) mixed electronics equipment
- 36,000 +/- pounds per 40 ft. HC or tractor trailer
- Maximum Contamination < or = 2.0% by weight

BALED LIGHT COLORED COPIER PLASTIC

- From disassembled light (white, beige) colored copiers

- 36,000 +/- pounds per 40 ft. HC or tractor trailer
- Maximum Contamination < or = 2.0% by weight

BALED DARK COLORED COPIER PLASTIC

- From disassembled dark (black, dark grey) colored copiers
- 36,000 +/- pounds per 40 ft. HC or tractor trailer
- Maximum Contamination < or = 2.0% by weight

BALED LIGHT COLORED MIXED ELECTRONICS PLASTIC

- From disassembled light colored (white, beige) electronics equipment
- 36,000 +/- pounds per 40 ft. HC or tractor trailer
- Maximum Contamination < or = 2.0% by weight

BALED MIXED COLOR ELECTRONICS PLASTIC

- From disassembled mixed (all colors) colored electronics equipment
- 36,000 +/- pounds per 40 ft. HC or tractor trailer
- Maximum Contamination < or = 2.0% by weight

Shredded Specs:

SHREDDED CRT TV PLASTIC

- From shredded or disassembled TVs
- 36,000 +/- pounds per 40 ft. HC or tractor trailer
- Maximum Contamination < or = 2.0% by weight

SHREDDED LIGHT COLORED CRT MONITOR PLASTIC

- From shredded or disassembled light (white, beige) colored monitors
- 36,000 +/- pounds per 40 ft. HC or tractor trailer
- Maximum Contamination < or = 2.0% by weight

SHREDDED DARK CRT MONITOR PLASTIC

- From shredded or disassembled dark (black, dark grey) colored monitors
- 36,000 +/- pounds per 40 ft. HC or tractor trailer
- Maximum Contamination < or = 2.0% by weight

SHREDDED DARK ELECTRONICS PLASTIC

- From shredded or disassembled dark (black, dark grey) colored electronics equipment
- 36,000 +/- pounds per 40 ft. HC or tractor trailer
- Maximum Contamination < or = 2.0% by weight

SHREDDED LIGHT ELECTRONICS PLASTIC

- From shredded or disassembled light (white, beige) colored electronics equipment
- 36,000 +/- pounds per 40 ft. HC or tractor trailer
- Maximum Contamination < or = 2.0% by weight

SHREDDED MIXED COLOR ELECTRONICS PLASTIC

- From shredded or disassembled mixed (all colors) colored electronics equipment
- 36,000 +/- pounds per 40 ft. HC or tractor trailer
- Maximum Contamination < or = 2.0% by weight

Guidelines for Tire Scrap: TS-2023

Rubber From Scrap Tires

GENERAL INFORMATION

Items not covered in the specifications, and any variations in the specification are subject to special arrangement between Buyer and Seller. Percentages listed below are by weight.

DEFINITIONS

FINES consist of materials that pass a 4.75 mm sieve. These materials may include rubber, fiber, inorganic and organic matter, dirt, and other non-tire materials.

SIZES will be determined by sieving. Suitable sieve sizes will be selected. Nest the sieves in order of decreasing size of opening from top to bottom and place the sample on the top sieve. Agitate the sieves by hand or by mechanical apparatus for a sufficient period so that additional sieving does not result in substantial additional material passing through the sieves.

TDM refers to tire-derived material.

RUBBER PRIMARILY USED FOR CIVIL ENGINEERING

TDM 2-A

- All material must be smaller than 4";
- at least 90% must be smaller than 21/2";
- at least 50% must be larger than 11/2";
- at least 90% must be larger than 1/2";
- maximum of 1/2" protrusion of steel; and
- maximum of 1% fines.

TDM 2-B

- All material must be smaller than 4";
- at least 90% must be smaller than 21/2";
- at least 50% must be larger than 11/2";
- at least 90% must be larger than 1/2";
- at least 90% must not exceed 1" protrusion of steel; and
- maximum of 5% fines.

TDM 2-C

- All material must be smaller than 4";
- at least 90% must be smaller than 21/2";
- at least 50% must be larger than 11/2";
- at least 90% must be larger than 1/2"; and
- maximum of 5% fines.

TDM 3-A

- At least 90% must be smaller than 4";
- at least 75% must be larger than 11/2";
- at least 90% must be larger than 1/2";
- maximum of 1/2" protrusion of steel; and
- maximum of 1% fines.

TDM 3-B

- At least 90% must be smaller than 4";
- at least 75% must be larger than 11/2";
- at least 90% must be larger than 1/2";
- at least 90% must not exceed 1" protrusion of steel; and
- maximum of 5% fines.

TDM 3-C

- At least 90% must be smaller than 4";
- at least 75% must be larger than 11/2";
- at least 90% must be larger than 1/2"; and
- maximum of 5% fines.

TDM 5-A

- All material must be smaller than 8";
- at least 90% must be smaller than 6";
- at least 50% must be larger than 3";
- at least 90% must be larger than 1/2";
- maximum of 1" protrusion of steel; and
- maximum of 1% fines.

TDM 5-B

- All material must be smaller than 8";
- at least 90% must be smaller than 6";
- at least 50% must be larger than 3";
- at least 90% must be larger than 1/2";
- at least 90% must not exceed 2" protrusion of steel; and
- maximum of 5% fines.

TDM 5-C

- All material must be smaller than 8";
- at least 90% must be smaller than 6";
- at least 50% must be larger than 3";
- at least 90% must be larger than 1/2"; and
- maximum of 5% fines.

TDM 8-A

- At least 90% must be smaller than 12";
- at least 75% must be smaller than 8";
- at least 50% must be larger than 3";
- at least 75% must be larger than 11/2";
- maximum of 2" protrusion of steel; and
- maximum of 1% fines.

TDM 8-B

- At least 90% must be smaller than 12";
- at least 75% must be smaller than 8";
- at least 50% must be larger than 3";
- at least 75% must be larger than 11/2";
- at least 90% must not exceed 2" protrusion of steel; and
- maximum of 5% fines.

TDM 8-C

- At least 90% must be smaller than 12";
- at least 75% must be smaller than 8";
- at least 50% must be larger than 3";
- at least 75% must be larger than 1 1/2"; and
- maximum of 5% fines.

TDM 12-A

- At least 90% must be smaller than 18";
- at least 50% must be larger than 6";
- at least 75% must be larger than 1 1/2";
- maximum of 2" protrusion of steel; and
- maximum of 1% fines.

TDM 12-B

- At least 90% must be smaller than 18";
- at least 50% must be larger than 6";
- at least 75% must be larger than 1 1/2";
- at least 90% must not exceed 2" protrusion of steel; and
- maximum of 5% fines.

TDM 12-C

- At least 90% must be smaller than 18";
- at least 50% must be larger than 6";
- at least 75% must be larger than 1 1/2"; and
- maximum of 5% fines.

Guidelines for Metals Transactions

GENERAL INFORMATION

These Guidelines are intended as a reference to assist members in carrying out their business obligations in a manner consistent with accepted industry practices. While the Guidelines are not obligatory, it is suggested that potential problems and misunderstandings may often be avoided by following these recommended procedures, in conjunction with ReMA's ISRI scrap descriptions.

At times, the respective parties to a transaction may be unaware of the differences in trading practices of the other party. This diversity of interpretation often leads to misunderstandings, disputes, and in some instances expensive lawsuits. It is with the objective of providing members the means of avoiding such friction that ISRI has published these Guidelines, which are based on those practices most common and current in the industry.

On those points where it is impractical to provide recommendations, it is advised that the points be mutually agreed upon by the parties involved.

PART I: GUIDELINES FOR CONTRACTS

A contract is an agreement between two or more parties to perform a legally enforceable act.

Therefore, all contracts should be in writing and set forth in **specific** terms. Before signing a contract, one should carefully read and understand all terms of it. No discrepancies or ambiguities should exist at the time the contract is executed. If you receive a contract with terms that are objectionable, you should immediately notify the other party in writing of your objections. An attorney should be consulted when legal advice is needed.

It should be kept in mind that if a dispute arises under a contract, and a court is called in to interpret its terms, certain general rules will be applied. First, contracts will be construed as a "whole," and specific clauses will be subordinated to the contract's general intent. Second, the courts will construe words according to their "ordinary" meaning unless it is clearly shown that they were meant to be used in a technical sense. Also, where provisions appear to be inconsistent, the courts will determine whether some of the provisions are printed (indicating a form contract), as compared to others which are written or typed. The latter kinds of provisions will prevail.

It should be remembered that where you and a Buyer (or Seller) have reached verbal agreement on a transaction, your failure to sign and return a contract which is sent to you in confirmation of that verbal agreement may not relieve you of the obligations of the terms and conditions enumerated in that contract.

These Guidelines were developed to cover routine transactions. It is essential that any unusual arrangements must be completely spelled out in a contract. With these factors in

mind, the following list of items is enumerated as a **Checklist** for you to follow, either in the construction of a contract, or for the review of another party's contract proposal. We cannot overemphasize the need for accuracy and specificity.

Checklist Items

(Be Specific At All Times)

I. PARTIES TO AGREEMENT:

Indicate full name and address of Buyer and Seller. Include name of individual person or persons involved. Buyer's and Seller's signatures are fundamental.

II. DATE OF CONTRACT:

- (a) Give date the initial agreement was reached
- (b) Give Contract Number.

III. DESCRIPTION OF MATERIAL:

Use NF code names or clearly describe what is being traded. Any allowable quality variation to be so stated. Ex: "X percent moisture allowed" or "Minimum CU content to be X percent" or "X percent painted material allowed."

IV. QUANTITY:

State exact quantity expected and indicate allowable tolerances or minimum/maximum limitations. Ex. "40,000 lbs. (5% More/Less allowed)" or "38,000 to 42,000 lbs."

V. PACKING:

State type of packing allowable and restrictions if such are required. Ex: "Bales not to exceed 60 inches"; "Bales not to exceed 3,500 lbs."

VI. DELIVERY:

Show complete address of shipping or delivery point, including where applicable, specific rail siding or junction, forwarding warehouse, and party to be notified. Ex: "FOB (Actual Point of Shipment) Chicago, Ill."; "FOB (Actual Point of Delivery) St. Louis. Mo."; "FAS Baltimore Container Yard"; "C&F Tokyo. Japan." If these details cannot be furnished at the time of writing of contract, it should state "shipping/delivery instructions to follow." State means of conveyance to be employed. State size and type of truck, rail car, container or number of shipments expected or permitted.

VII. SHIPMENT:

Time allowed for shipment or delivery should be clearly stated. Ex: "Shipment by Jan. 15, 2008 LATEST"; or "Delivery by Jan. 15, 2008." Indicate at whose option, Buyer's or Seller's, shipment shall be made in time period stated.

VIII. PRICE:

State price per unit. Ex: "\$20.00/CWT"; "20.00 Cents/Pound"; "\$400.00/Net Ton"; "\$440.92/ Metric Ton." and indicate where appropriate "Clean and Dry"; "Full Copper Content." If applicable, state exact processing, smelting, refining charge, or unit deductions for impurities. (Avoid the use of the word "penalties.")

IX. PAYMENT:

Terms of payment should be explicit. Ex: "Net 30 days after shipment"; "Net 15 days after mill receipt." Avoid phrases such as "usual"; "Net 30;" "Net Cash." Documents required to effect payment to be clearly stated. Ex: "Bill of Lading"; "Invoice"; "Weight Certificate." State how payment shall be made. If there is discussion of compensation for delayed payments, it should be included in the contract. If Letter of Credit is called for as a means of payment, it is advisable that the terms to be included in the Letter of Credit also be stated in the contract. When applicable, contract should state whether Buyer or Seller is responsible for payment of taxes, duties, or any other levies to which a shipment could be subjected. Contract should state whether the Seller's or Buyer's weights shall govern the basis of settlement.

X. ASSIGNMENT:

The contract may state whether the Buyer and/or the Seller has the right to assign the contract. If it does, it should emphasize that the obligation arising under the contract shall be equally binding on his assignee.

XI. NOTICE:

The Seller should specify how notice to be given under the contract should be received—i.e. by hand, by telegram, by certified or registered mail. One should also specify when notice is deemed to be received by the party to whom it is given.

XII. DISCLAIMER OF WARRANTIES:

Depending on the type of transaction, or the metal involved, the Seller may want to limit his liability by disclaiming any warranties of merchantability or of fitness for a particular purpose.

XIII. DEFAULT:

The contract should contain a provision setting forth the events which would result in a default of the contract. This provision might also contain a clause stipulating damages and/or setting forth available remedies (i.e. specific performance) in the event a default does, in fact, occur.

XIV. FORCE MAJEURE:

This item is related to the item of default, as indicated in paragraph XIII. Seller or Buyer may enumerate, either generally or specifically, what events (i.e. strikes, fires, accidents) constitute circumstances beyond its control and thereby absolve him/her of any liability for damages or delay.

XV. NON-WAIVER:

The Seller or Buyer should state in the contract that his/ her failure to insist upon strict performance in any given instance shall not be construed as a waiver or relinquishment for the future of any of the terms, covenants and conditions contained therein.

XVI. CLAIMS:

The Seller may specify that any claims involved in a metals transaction for contaminated materials, weight shortage, or for any other cause is waived by the Buyer unless brought to the Seller's attention within a certain number of days after delivery.

XVII. ARBITRATION AND APPLICABLE LAW:

The contract should set forth which state's or country's law will apply in the event of a legal dispute under the contract. It should also provide for arbitration procedure. (If ISRI Arbitration is desired, the contract should so stipulate.)

XVIII. BENEFIT:

The contract should stipulate on whom it is binding. For instance, the Seller or Buyer may want to specify that the contract inures to the benefit of the parties, their legal representatives, successors and assignees.

XIX. ENTIRE AGREEMENT:

This provision is especially important in the area of metals transactions, which frequently involve extensive preliminary negotiations. A clause may be inserted into the contract stating that the contract constitutes the parties' entire agreement and supersedes all prior agreements and understandings with respect to the subject matter of the contract.

XX. MODIFICATION:

A clause may be included in the contract stating that the contract's requirements can only be modified by a written instrument signed by the parties or their respective agents. This ensures that the parties' informal discussions will not later be construed as affecting an alteration of the contract.

PART II: PACKING, WEIGHING, SHIPPING AND RECEIVING

It is recommended that strict adherence to contract terms will minimize many of the potential problems in this area. If there is a question about any item, one should communicate with his/her Buyer/Seller and clarify the situation prior to shipping. Listed below are some specific guidelines to be used in avoiding the most frequently reported problems.

Packing (All Shipments)**SELLER'S RESPONSIBILITY:**

- Pack in the manner and form agreed. Example: In sound bales, briquettes, boxes, pallets, drums, loose, etc.
- Be sure that Buyer agrees with your definition of words and phrases, i.e. Bale, Briquette, Coil, etc. as well as allowed dimensions and weights of such.
- Material and packages should be securely tied or supported so that packages will hold in transit and normal handling.

BUYER'S RESPONSIBILITY:

- Advise Seller of any specific prohibitions, i.e. type or method of packing, size or weight of pieces, units or packages, etc.
- Be sure that Seller agrees with your definition of words and phrases, i.e. Bale, Briquette, Coil, etc., as well as allowed dimensions and weights of such.

Weighing, Shipping and Receiving (Truck Shipment)**SELLER'S RESPONSIBILITY:**

- Each package should be individually weighed and the entire truckload should be checkweighed for comparison. Reconcile or explain any differences. If truck is weighed during inclement weather or wind, make note of this on weight ticket.
- Trailers should be drop-weighed (both empty and loaded).
- All equipment should be inspected before loading, and cleaned or repaired where necessary to avoid loss or spillage.
- Open top trucks or trailers should be tarped or covered.
- Vans and closed trailers should be sealed and seal numbers indicated on all documents.

- f. If your customer requires appointments, make one in advance. Otherwise, as a courtesy, advise the Buyer of your anticipated delivery schedules.
- g. A complete manifest and packing list should accompany each shipment. This should clearly indicate the order number, items shipped, number and type of packages of each commodity, as well as the gross, tare and net weights of each package. This detailed information should be put into an envelope and attached to the inside wall of the truck or van. If this cannot be done, give a complete set of papers to the driver to deliver with the original Bill of Lading covering the shipment. At the very least, notify Buyer by telephone, telex or wire of these details on the day shipment leaves.
- h. Different lots should always be properly segregated and bulkheaded to avoid comingling. Each package should be tagged or marked to aid in proper identification and segregation at the receiving point.
- i. Be aware that someone at the delivery point will have to unload the shipment. Pay particular attention to door areas to assure that material is loaded safely. Proper care should be taken to ensure that the material can be unloaded in a safe and expedient manner.

BUYER'S RESPONSIBILITY:

- a. If Seller requires appointment prior to pickup, make one in advance. Otherwise, as a courtesy, advise the Seller of your anticipated pickup schedule.
- b. Trailers should be drop-weighed (both empty and loaded).
- c. Carefully check shipment advices and compare package count, seal numbers, weights.
- d. **Prior to unloading**, if a significant* weight difference is apparent, the Seller should be notified promptly and, if requested, another weight should be taken to determine if spillage or theft might have occurred.
- e. **After unloading**, promptly advise Seller of any significant* differences between advised and actual weights, segregation, classification or quality. (Note: Refer to Part IV of the circular for recommended procedures in handling quality problems.)
- f. Truck or trailer should be completely unloaded including any spilled material which should be picked up, weighed and identified as spilled from original containers. Buyers should cooperate in every way to help minimize losses.

Weighing, Shipping and Receiving (Rail Shipment)

SELLER'S RESPONSIBILITY:

- a. Each package should be individually weighed and the entire rail car should be checkweighed for comparison. Reconcile or explain any differences. If rail car is weighed during inclement weather or wind, make note of this on weight ticket.
- b. Railroad cars should be uncoupled and at rest (if possible) before weighing.
- c. All equipment should be inspected before loading, and cleaned or repaired where necessary to avoid loss or spillage.
- d. Railroad cars should be sealed and seal numbers indicated on all documents.
- e. A complete manifest and packing list should accompany each shipment. This should clearly indicate the order number, items shipped, number and type of packages of each commodity, as well as the gross, tare and net weights of each package. This detailed information should be put into an envelope and attached to the inside wall of the railroad car. If

this cannot be done, mail a complete set of papers to the Buyer on the day shipment leaves.

- f. Different lots should always be properly segregated and bulkheaded to avoid comingling. Each package should be tagged or marked to aid in proper identification and segregation at the receiving point.
- g. Be aware that someone at the delivery point will have to unload the shipment. Pay particular attention to door areas to assure that material can be unloaded in a safe and expedient manner.

BUYER'S RESPONSIBILITY:

- a. Railroad cars should be uncoupled and at rest (if possible) before weighing.
- b. Carefully check shipment advices and compare package count, seal numbers, weights.
- c. Prior to unloading, if a significant* weight difference is apparent, the Seller should be notified promptly and, if requested, another weight should be taken to determine if spillage or theft might have occurred.
- d. After unloading, promptly advise Seller of any significant* differences between advised and actual weights, segregation, classification or quality. (Note: Refer to Part IV of the circular for recommended procedures in handling quality problems.)
- e. Rail car should be completely unloaded including any spilled material which should be picked up, weighed and identified as spilled from original containers. Buyer should cooperate in every way to help minimize losses.

Weighing, Shipping and Receiving (Export/ Import Shipment)

SELLER'S RESPONSIBILITY:

- a. Each package should be individually weighed and the entire container load should be check-weighed for comparison. If container is weighed during inclement weather or wind, make note of this on weight ticket.
- b. Container and chassis should be drop-weighed, if possible, both empty and loaded.
- c. Prepare and send to Buyer a complete manifest and packing list indicating the order number, items shipped, number and type of packages of each commodity, as well as the gross, tare and net weights of each package and the seal numbers.
- d. If shipment is against a Letter of Credit, pay strict attention to all terms.
- e. Place seals on all container doors and indicate seal numbers on documentation.
- f. Material and packages should be properly stowed and braced to prevent movement during shipment.
- g. Be aware that someone at the delivery point will have to unload the shipment. Pay particular attention to door areas to assure that material is loaded safely. Proper care should be taken to ensure that the material can be unloaded in a safe and expedient manner.

BUYER'S RESPONSIBILITY:

- a. Container and chassis should be drop-weighed, if possible, both empty and loaded.
- b. Carefully check shipment advices and compare package count, seal numbers, weights.
- c. **Prior to unloading**, if a significant* weight difference is apparent, the Seller should be notified promptly and, if requested, another weight should be taken to determine if

spillage or theft might have occurred. Seller should be given opportunity to appoint surveyor or representative to verify weights.

- d. **After unloading**, promptly advise Seller of any significant* differences between advised and actual weights, segregation, classification or quality. (Note: Refer to Part IV of the circular for recommended procedures in handling quality problems.)
- e. Container should be completely unloaded including any spilled material which should be picked up, weighed and identified as spilled from original containers. Buyer should cooperate in every way to help minimize losses.

*For purposes of this section, the meaning of the word "significant" shall be determined by agreement between Buyer and Seller, depending on the commodities and their values.

PART III: TRANSPORTATION GUIDE

The mode and type of conveyance should be specified in the contract. If it has not been, then it is important that Buyer and Seller agree upon the mode and type to be used. These guidelines will assist in determining the appropriate means of transportation to employ.

A. Mode—Truck/Trailer

1. TYPE:
 - a. Dump
 - b. Removable sides
 - c. Van—open or closed
 - d. Dimensions of unit (20 ft., 40 ft., etc.)
 - e. Determine if truck/trailer capacity meets minimum weight specified on contract.

B. Mode—Rail Car

1. TYPE:
 - a. Box car or gondola
 - b. Size of door opening, i.e. single or double door
 - c. Special type D.F., Hi-Cube, etc.
 - d. Dimensions of car (40 ft., 50 ft., 60 ft., etc.)
 - e. Determine if rail car capacity meets minimum weight specified on contract.

C. Export Shipments

1. CONTAINER:
 - a. Type of container, i.e. closed, open-top, flat rack, Hi-cube, etc.
 - b. Size of container (20 ft., 35 ft., 40 ft., 45 ft., etc.)
 - c. Determine if container capacity meets minimum weight specified on contract.
2. BREAKBULK

PART IV: REJECTIONS—DOWNGRADES—CLAIMS

A brief explanation of these items will help one understand and implement the procedures recommended in this section.

REJECTIONS: Rejections can occur when a Buyer refuses to accept a shipment of material that does not conform to the description specified in the contract. Usually in such cases, the Buyer cannot utilize the material and the Seller is asked to remove

the material from the Buyer's place of delivery. A rejection can occur prior to unloading, but often the cause of the problem cannot be determined until the material has been off loaded and graded. Any part, or all, of the shipment may be subject to rejection.

DOWNGRADES: Downgrades can occur when all, or part, of the material in a shipment is not in conformity with the description specified in the contract. Often, in such cases, the Buyer can utilize the material and is willing to accept delivery of the material, subject to a price commensurate with its value.

CLAIMS: This term is used mostly in export-import movements, and is used generically to encompass both **rejections** and **downgrades**, as well as weight **shortages**.

Strict adherence to contract terms can minimize the common causes of these difficulties. However, if a problem arises, it should be given prompt attention and settlement should be attempted as quickly as is practical. It is essential that both parties cooperate and keep communications open to minimize expenses and to preserve the relationship. Negotiations should not be conflicting but mutually beneficial and fair. Listed below are some recommended steps to be taken when a problem arises.

Domestic Shipments

BUYER'S RESPONSIBILITIES:

- a. In the event of a rejection Buyer must notify Seller immediately by telephone or telex. If Seller fails to respond within two business days, Buyer may return material in most prudent manner. Subject to contract provisions, Buyer should promptly advise Seller concerning replacement of rejected material.
- b. In the event of a downgrade Buyer must notify Seller immediately by telephone or telex and afford Seller an opportunity to inspect the material prior to its use. If material is to be inspected by Seller or his/her representative, Buyer should agree to a mutually convenient time to do so.
- c. Buyer must give Seller option of removing material if he/she does not agree to downgrade. (All costs of unloading and reloading are for Seller's account.)

SELLER'S RESPONSIBILITIES:

- a. In the event of a rejection Seller should respond promptly and advise Buyer of his/her intentions. Seller must reply within two business days. Subject to contract provisions, he/she must advise Buyer promptly concerning replacement of rejected material.
- b. In the event of an unacceptable downgrade Seller must advise Buyer within two business days if he/she wishes to inspect material and agree upon a mutually convenient time to do so.
- c. If Seller wishes to remove downgraded material from Buyer's delivery point, he/she must advise Buyer promptly. (All costs of unloading and reloading are for Seller's account.)

Export-Import Shipments**BUYER'S RESPONSIBILITY:**

- a. In the event of a claim, time is of the essence and notification should be given to Seller within a reasonable period of time after arrival of vessel in receiving port.
- b. In the event of a claim, the material should be held intact until agreement has been reached. The acceptable portion of the material may be consumed and/or arrangements may be made to sample a portion of material, i.e., 10–25% with balance held intact pending resolution of claim.

SELLER'S RESPONSIBILITY:

- a. In the event of a claim, Seller should respond to Buyer's notification promptly by telephone, telex, wire, or cable.
- b. When a claim settlement has been agreed upon, terms of settlement must be followed promptly.

Inbound Residential Single Stream

GENERAL INFORMATION

Inbound Residential Single Stream is the material derived from a recycling method whereby residents of a community place allowed materials in a specifically designated receptacle to be left at a drop off point outside their residence. Materials in the receptacle are then collected by a recycler for processing at a Materials Recovery Facility. Organic and other materials that can be considered solid waste are not permitted in this material mix. Any other recyclable materials may be added or deleted based on the individual agreement between buyer (MRF) and seller (Hauler or Municipality).

DESCRIPTION

A commodity mix of certain materials placed in specifically designated receptacles to be left at a drop off point outside their residence.

PAPER

Uncoated White Office Paper, Printing and Writing Paper
Colored Paper
Newspaper
Magazines
Phonebooks
Junk Mail
Paperboard
Tissue boxes/rolls
Paper towel and toilet paper rolls
Cardboard
Brown or Kraft paper
Paper boxes/cartons
Pizza Boxes, remove food and liner
Paper cups

PLASTIC

Empty PET (#1), HDPE (#2), PP (#5)
Plastic Bottles, Jugs, Jars and Containers
Bulky Rigid Plastics Such as Crates, Buckets, Totes, Baskets
Tubs and Lids
HDPE rigid can and bottle carriers

METAL

Aluminum, tin, and steel beverage and product containers

GLASS

Bottles and jars of any color
All materials should be clean, loose, and dry.

CONTAMINATION

Contamination is defined as anything not considered acceptable in the specification.

- None permitted unless specifically agreed to in writing between buyer and seller.
- No bagged recyclables unless otherwise accepted in local curbside collection program.

The Following Items are Considered Contamination:

PAPER

Shredded Paper
Containers coated with wax, plastic or other materials (with the exception of that listed above)
Wallpaper
Material with excess food residue or other organic material

PLASTIC

Plastic Bags & Plastic Film
Expanded Polystyrene Foam (#6)
Multi-layered juice pouches
Plastic from electronics
Plastic marked as biodegradable or compostable

METAL

All metal (with the exception of that listed above)
Aerosol cans that are under pressure or partly filled

GLASS

All glass (with the exception of that listed above)
Drinking glasses, crystal or tableware
Mirrors
Non-container glass
Light bulbs
Windows

PROHIBITED MATERIALS

The term "Prohibited Materials" as used throughout this document is defined as items never allowed and includes any material that contains medical, organic, food, hazardous, poisonous, radioactive or toxic waste and other harmful substances or liquids.

Additional Examples of Prohibited Items Are:

- a. Sharps and Needles
- b. Batteries
- c. Radioactive materials
- d. Hazardous materials
- e. Corrosives
- f. Medical waste
- g. Pesticides, poisons, bio hazards
- h. Compressed gas cylinders
- i. Refrigerants
- j. PCB containing capacitors, transformers, ballast
- k. Asbestos
- l. Materials that may be damaging to equipment
- m. Materials containing information protected or regulated under any local, state or federal privacy or data security laws, including, but not limited to the Health Insurance Portability and Accountability Act of 1996, as amended, or other regulations or ordinances.
- n. Wax
- o. Electronics
- p. Large items such as tires, appliances, roofing materials
- q. Wood
- r. Ceramics
- s. Food Waste or other items that can otherwise be composted
- t. Rock, dirt, asphalt, concrete

Residential curbside recycling systems can offer a significant amount of variability. Please check with the recycling program coordinator for more information on what is considered acceptable in the jurisdiction.

Inbound Residential Dual Stream

GENERAL INFORMATION

Inbound Residential Dual Stream is the material derived from a recycling method whereby residents of a community place allowed materials in a specifically designated receptacle to be left at a drop off point outside their residence. Materials in the receptacle are then collected by a recycler for processing at a Materials Recovery Facility. Organic and other materials that can be considered solid waste are not permitted in this material mix.

Any other recyclable materials may be added or deleted based on the individual agreement between buyer (MRF) and seller (Hauler or Municipality).

DESCRIPTION

A commodity mix of certain materials placed in specifically designated receptacles to be left at a drop off point outside the residence resulting from Dual Stream collection systems that separate bins, or carts for Paper and Containers and/or collected in separate compartments on one or more trucks.

PAPER SEPARATED AT THE COLLECTION POINT

(Either stacked below or separate; not to be mixed with Containers)

Uncoated White Office Paper, Printing and Writing Paper

Colored Paper

Newspaper

Magazines

Phonebooks

Junk Mail

Paperboard

Tissue boxes/rolls

Paper towel and toilet paper rolls

Cardboard

Brown or Kraft paper

Paper boxes

Pizza Boxes, remove food and liner

Paper cups

(Not to be Mixed with Paper)

PLASTIC

Empty PET (#1), HDPE (#2), PP(#5)

Plastic Bottles, Jugs, Jars and Containers

Bulky Rigid Plastics Such as Crates, Buckets, Totes, Baskets

Tubs and Lids

Cartons

HDPE rigid can and bottle carriers

METAL

Aluminum and tin beverage and product containers

GLASS

Bottles and Jars of any color

All materials should be clean, loose, and dry.

CONTAMINATION

Contamination is defined as anything not considered acceptable in the specification.

- None permitted unless specifically agreed to in writing between buyer and seller.
- No bagged recyclables unless otherwise accepted in local curbside collection program.

The Following Items are Considered Contamination:

PAPER

Shredded Paper

Containers coated with wax, plastic or other materials (with the exception of that listed above)

Wallpaper

Material with excess food residue or other organic material

PLASTIC

Plastic Bags & Plastic Film Expanded Polystyrene Foam (#6)

Multi-layered juice pouches

Plastic from electronics

Plastic marked as biodegradable or compostable

METAL

All metal (with the exception of that listed above)

Aerosol cans that are under pressure or partly filled

GLASS

All glass (with the exception of that listed above)

Drinking glasses, crystal or tableware

Mirrors

Non-container glass

Light bulbs

Windows

PROHIBITED MATERIALS

The term "Prohibited Materials" as used throughout this document is defined as items never allowed and includes any material that contains medical, organic, food, hazardous, poisonous, radioactive or toxic waste and other harmful substances or liquids.

Additional Examples of Prohibited Items Are:

- a. Sharps and Needles
- b. Batteries
- c. Radioactive materials
- d. Hazardous materials
- e. Corrosives
- f. Medical waste
- g. Pesticides, poisons, bio hazards
- h. Compressed gas cylinders
- i. Refrigerants
- j. PCB containing capacitors, transformers, ballast
- k. Asbestos
- l. Materials that may be damaging to equipment
- m. Materials containing information protected or regulated under any local, state or federal privacy or data security laws, including, but not limited to the Health Insurance Portability and Accountability Act of 1996, as amended, or other regulations or ordinances.
- n. Wax
- o. Electronics
- p. Large items such as tires, appliances, roofing materials
- q. Wood
- r. Ceramics
- s. Food Waste or other items that can otherwise be composted
- t. Rock, dirt, asphalt, concrete

Residential curbside recycling systems can offer a significant amount of variability. Please check with the recycling program coordinator for more information on what is considered acceptable in the jurisdiction.

ReMA Arbitration Service

ReMA established an arbitration service as a means to enable members to use arbitration to resolve disputes.

ReMA arbitration is a voluntary procedure and must be agreed upon by both parties in the dispute. It is not required that both parties to the dispute be ReMA members.

The complete procedure for arbitration is set forth in ReMA's "Rules for Arbitration," which are available from Association headquarters in Washington, D.C. The rules contain the necessary form that must be completed to initiate arbitration. ReMA treats all filings, awards, and proceedings as confidential.

The rules are highlighted below:

1. Anyone may propose arbitration in a dispute, though at least one party must be a member of the association. Both parties must agree to the arbitration by signing a "Submission to Arbitrate" form and agreeing to abide by the applicable Arbitration Rules.
2. A panel of arbitrators has been established by the association. The arbitrators serve without compensation, except for reasonable expenses. The arbitration parties must draw their arbitrators from the panel. A maximum of three arbitrators can be issued in any proceeding; the parties are encouraged to use a single arbitrator.
3. There is a specific schedule of fees listed in the "Rules for Arbitration." Each party must deposit with the association in advance \$500 plus \$500 for each arbitrator. The total deposit for each party thus is either \$1,000 or \$2,000, depending on whether one arbitrator is to be used or three. A portion of the fee is refundable if not required to defray arbitrators' costs. The arbitrators may require the losing party to reimburse the prevailing party for its share of these costs.
4. The arbitration procedure usually includes a hearing, at which time the parties involved are required to appear, present their respective cases, and be available for questioning by the arbitrator(s). All physical evidence (contracts, correspondence, relevant comments, etc.) may be required to be submitted in advance to the arbitrators. A party in the arbitration may be accompanied by counsel but must inform the other party in advance and receive permission from the arbitrators. Witnesses may also be called to an arbitration hearing. There is also an optional procedure for conducting the arbitration without an oral hearing.
5. An award by the arbitrator(s) will be made promptly, within 20 days after hearings have been completed or final briefs submitted. The award is made in writing.
6. The rules state that the parties to the dispute shall be deemed to have consented that a judgment upon the award be entered in any court having jurisdiction over an action to enforce the award.

Members who wish to provide an automatic basis for the settlement of any disputes arising from a transaction are encouraged to provide in their contracts that the ReMA Arbitration Procedure shall prevail in the event of any ensuing controversy and that each party will take all necessary steps to initiate such arbitration. Members are urged to obtain and carefully read the "Rules for Arbitration" before proceeding.

For more information, contact isrispecs@isri.org